

University of Rajshahi

Rajshahi-6205

Bangladesh.

RUCL Institutional Repository

<http://rulrepository.ru.ac.bd>

Department of Physics

MPhil Thesis

1989

# A Study of Bonding and other Related Properties of Some Rutile type Oxide Crystals.

ISLAM, MD. KHADEMUL

University of Rajshahi

<http://rulrepository.ru.ac.bd/handle/123456789/938>

*Copyright to the University of Rajshahi. All rights reserved. Downloaded from RUCL Institutional Repository.*

A STUDY OF  
BONDING AND OTHER RELATED PROPERTIES  
OF  
SOME RUTILE TYPE OXIDE CRYSTALS.

A Thesis Submitted  
To  
The University of Rajshahi  
For  
The Degree of Master of Philosophy  
In  
P H Y S I C S

By  
MD. KHADEMUL ISLAM  
B.SC. (HONS). M.SC.

Under the Supervision of  
Prof. A.K.M. Azharul Islam  
Department of Physics  
Rajshahi University, Rajshahi.

Dated : 20.4.89


## DECLARATION

This is to declare that the major portion of the dissertation submitted for the degree of Master of Philosophy to Rajshahi University is based on my investigation and was carried out under the supervision of Professor A.K.M. Azharul Islam, Department of Physics, Rajshahi University.

The work embodied in this thesis has not already been submitted as a thesis in substance for any degree and has not been concurrently submitted in candidature for any other degree.



Professor A.K.M. Azharul Islam  
SUPERVISOR



Md. Khademul Islam  
CANDIDATE

## ABSTRACT

A theoretical analysis of the interionic potential in four rutile-type oxide crystals has been made within the framework of ionic model using eight repulsive interactions including one proposed in this work. The suitability of the new ~~interaction~~ potential as applied to these system is discussed. A new complete set of polarizability values of the ions concerned has also been derived. The lattice energy and pressure derivative of bulk moduli are evaluated for the entire family of crystals under study. The resulting values are compared with the available experimental data and other recent theoretical calculations.

We have also considered the question of the degree of ionicity of the compounds under study as there seems to be some controversy regarding these in literature. The present study indicates that the bonding in rutile is predominantly ionic, although some covalent contribution is present.

## ACKNOWLEDGEMENT

I humbly express my wholehearted gratitude and debt to Professor A.K.M. Azharul Islam, M.Sc., Ph.D. (London) D.I.C, C.Phys., Chairman, Department of Physics, Rajshahi University for his unfeigned supervision, for suggesting me the problem and for his inspiring and affectionate guidance throughout the course of the work. I also feel that without the contribution of his major time, the completion of this thesis would not have been possible .

I have the pleasure to express my deepest sense of gratitude to Professor M. Nazrul Islam for his keen interest, patience and unusual care during some fruitful discussions.

I am grateful to Professor Ahmad Hussain for his suggestions and encouragement during the period of the work. I am also grateful to Professor A.K. Basak, Administrator of the Computer Centre, Rajshahi University for giving the facilities of doing work at the Computer Centre.

I am particularly indebted to Dr.Ajoy Chatterjee

and Dr. Shafiqul Islam of the Department of Physics,  
for their many helpful suggestions.

Finally, I take pleasure in mentioning the name of  
M.Alfaz Uddin, and M.Enamul Haque, Assistant Profes-  
sors, who afforded me motivation for the work.

## CONTENTS

	Page No.
CHAPTER 1 : Introduction	1
1.1 General Introduction	1
CHAPTER 2 : Lattice energy and pressure derivative of bulk moduli	20
2.1 Introduction	20
A) Long range Coulomb energy	21
B) Evaluation of Madelung constant	22
C) Repulsive energy	23
D) van der Waals energy	25
E) Zero point energy	26
2.2 Pressure derivative of bulk moduli.	28
2.3 The energy from Born-Haber cycle	29
CHAPTER 3 : Repulsive Interactions	30
3.1 Origin of repulsive interaction	30
3.2 Different empirical forms	32
i) Born-Lande potential	32
ii) Born-Mayer potential	33
iii) Wasastjerna potential	35
iv) Hellmann potential	35
v) Huggins and Mayer potential	36
vi) Verwey potential	37
vii) Dick-Overhauser potential	37
viii) Varshni- Shukla potential	39

ix)	Benson - Dempsey potential	40
x)	Hefemeister and Flygar potential	41
xi)	Modified Varshni - Shukla potential	42
xii)	Hefemeister and Zahrt potential	42
xiii)	Gohel and Trivedi potential	43
xiv)	Prakash and Behari potential	44
xv)	Redington potential	45
xvi)	Katiyar potential	45
xvii)	Romano, Margheritis and Sinistri potential	46
xviii)	Thakur potential	47
xix)	Sharma, Kant and Misra potential	51
xx)	Mohammad potential	53
xxi)	Islam potential	56
xxii)	Harrison potential	58
xxiii)	Narayan - Ramaseshan potential	60
xxiv)	Satyanarayan potential	64
xxv)	Yadav potential	65
xxvi)	Buckingham potential	67
xxvii)	A new proposed potential	69

CHAPTER 4 :	van der Waals Interactions	71
4.1	Origin of van der Waals interaction	71
4.2	Derivation of van der Waals co-efficients	76



4.2.1 Dipole-dipole term, c	78
a) London formula	78
b) Slater and Kirkwood formula	80
c) Kirkwood and Muller formula	80
4.2.2 Dipole-quadrupole term, d	81
4.3.1 Origin of polarizability	84
4.3.2 Polarizability versus ion environment	86
4.3.3 Methods of calculation of polarizability	104
CHAPTER 5 : Calculation and Results	111
5.1 Derivation of repulsive constants	111
A) Born - Lande potential	114
B) Born - Mayer potential	115
C) Verwey potential	116
D) Varshni - Shukla potential	117
E) Gohel and Trivedi potential	117
F) Islam potential	119
G) Proposed new potential	120
H) Buckingham potential	121
5.2 Electronic polarizability and van der Waals constants	122
a) Electronic polarizability	122
b) van der Waals constants	126
5.3 Lattice sums	126
5.4 Effective number of electrons	126

5.5	Repulsive parameters and energy	131
5.6	Output results	135
5.6.1	Lattice energy	135
5.6.2	Pressure Derivative of Bulk Moduli	135
CHAPTER 6 :	Discussions and Conclusions	138
	References.	146

....

## CHAPTER 1

## INTRODUCTION

## 1.1 General Introduction :

A solid has an arrangement of atoms (or molecules) in which the atoms are arranged in some regular repetitious pattern in three dimensions. It can be classified according to a variety of criteria. Among the more significant of these is the description of a solid as being neither crystalline or amorphous. The sample of macroscopic crystalline solids have been chosen by chemists and physicists for studying the structures of matters, interatomic bonding and other related chemical properties on an atomic scale. All of the mechanisms which cause bonding between atoms derive from electrical attraction and repulsion. The differing strengths and differing types of bond are determined by the particular electronic structures of the atoms involved. The weak van der Waals(or residual) bond provides a universal weak attraction between closely spaced atoms and its influence is overridden when the conditions necessary for ionic, covalent or metallic bonding are also present.

An ionic bond may be thought of as the result of

the complete transfer of an electron from one atom to another. The alkali halides such as NaCl are typical members of the class of ionic solids. NaCl crystallizes as  $\text{Na}^+ \text{Cl}^-$ . The alkali metals such as sodium have a single valence electron outside a closed shell. Whereas halogens such as chlorine are one electron short of having a complete outer shell. An electron transfer from the alkali metal X to the halogen Y will result in closed shells for both  $\text{X}^+$  and  $\text{Y}^-$  ions. This happens in a salt XY. For example in NaCl, Na has an electronic configuration  $1s^2 2s^2 2p^6$  which is the same as that of neon, whereas Cl has  $1s^2 2s^2 2p^6 3s^2 3p^5$  which is the same as that of argon. Since these electronic configurations are very stable, it can be said that an ionic crystal consists of positive and negative ions. Besides alkali halides, ionic crystals can also be made of divalent and trivalent atoms for example  $\text{CaO}$ ,  $\text{MgCl}_2$ ,  $\text{Al}_2\text{O}_3$ ,  $\text{Na}_2\text{S}$  and  $\text{ZnO}$  etc.


Ions have the same electronic structure as the nearest inert gas atoms except that they are electrically charged. This charge is spherically distributed and represents the difference between the charge on the nucleus and the sum of the electronic charge surrounding it. When oppositely charged ions are brought together each ion tends to neutralize its charge by surrou-

nding itself with ions having an opposite charge. Because ions having like charges repel each other, the stable packing attained is determined by the relative sizes of the ions and their respective charges. A periodic array therefore results in which the environment of all similar atoms is the same and the sum of all positive and negative charges is up to zero so that the ionic solid is electrically neutral.

Ionic bond is fairly strong as known from the amount of work required to dissociate an ionic solid into its components. Binding energy of NaCl is 7.8 eV and binding energy of LiF is 10.4 eV. This strong binding means that ionic crystals are hard and have relatively high melting and boiling points. Normally they are transparent to visible light while they exhibit a single characteristic optical reflection peak in the infrared region. Crystals are quite soluble in ionizing solvents such as water, the solutions being highly dissociated with free ions. The valence electrons are also bound quite tightly to ionic nuclei so that electrical conductivity via electrons is not possible and ionic crystals are insulators at room temperature. At high temperatures ions themselves become more and more mobile and ionic conductivity becomes possible.

As a consequence of the spherical charge distribution ionic bond is non-directional. For special cases, ionic bonds have some directional characters. Ionic crystals usually crystallize in the relatively closed packed NaCl and CsCl structure.

In covalent bond two electrons become shared between the atoms which are being joined. The covalent bond, sometime referred to as a valence or homopolar bond, is an electron pair bond. The result of this sharing is that the electron charge density is high in the region between the two atoms. The hydrogen molecule,  $H_2$  serves as a simple example of the covalent bond. The other examples of covalent bond:

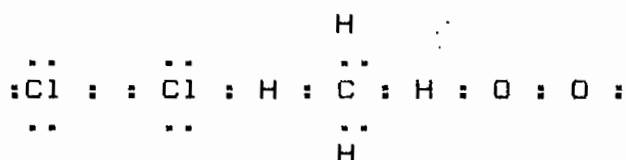

The dots between the atoms indicate the electron pair bond.

#### Characteristics of a Covalent bond:

1. Covalent bond has a saturation property. Let us consider the interaction of a hydrogen atom with a helium atom. An exchange of electrons between H and He with parallel spins result in repulsion, whereas an exchange with antiparallel spins violates the Pauli exclusion

principle. Therefore, covalent bonding exists only between atoms with unpaired spins. For example in  $\text{CH}_4$  for carbon to have unpaired spins, the four valence electrons must have the configuration  $2s^1 2p^3$  in contrast to the ground state configuration  $2s^2 2p^2$ . The four orbital wave functions are mixtures of the one  $2s$  and three  $2p$  wave functions called the  $sp^3$  hybrid orbital and they have electron distributions directed towards the four corners of a tetrahedron. Typical examples of crystals with nearly pure covalent bonds are diamond, silicon and germanium.

2. Covalent bonds are strongly directional in character i.e. the electrons tend to be concentrated along the lines joining the adjacent atoms.

3. Covalent crystals are usually hard brittle with quite high binding energies and thus have high melting and boiling points.

4. They are transparent to long wavelengths but opaque to shorter wavelength, the transition is abrupt and occur at a characteristic wavelength usually in the visible or infrared.

5. Covalent crystals are typical semiconductors whose electrical conductivity is quite sensitive to impurity

and change of temperature. In molecular crystals binding arises solely from dipolar forces between the atoms or molecules of the crystal. Even when an atom or molecule has no average dipole moment it will in general have instantaneous fluctuating dipole moment arising from instantaneous positions of the electrons in their orbitals. For example Germanium. Here unpaired bonds exist at the boundary of the structure. These unpaired bonds are generally referred to as dangling bonds and they are responsible for the fact that germanium and silicon surfaces are quite active chemically.

Covalent binding is all that is needed for Ge atoms to form a germanium crystal. This is not the case with  $\text{CH}_4$ . The bonds in  $\text{CH}_4$  are all used up. Thus no additional bond pairs can be formed with neighbouring  $\text{CH}_4$  molecules. The binding between such molecules comes from binding force arising from fluctuating dipole interaction called as van der Waals forces. It turns out that an atom or a molecule is polarizable not only under an external electric field but under the field of other atoms or molecule as well. As a result a very small electric dipole develops.

The instantaneous dipole moment is the source of an electrostatic dipole field which in turn may induce



a dipole moment in other atom or molecule. The interaction between the original and induced dipole moment is attractive and can serve to bind a crystal in the absence of ionic or covalent binding. Binding forces are usually quite weak, the binding energy due to them falls off as  $1/r$  where  $r$  is the distance between the dipoles .

Molecular crystals have small binding energy and consequently have low melting and boiling points. They are usually poor electrical conductors. Crystals of organic compounds are usually of this type as are the inert gases He ,Ne , A etc. in the solid state.

In metallic crystals free electrons are present. The outstanding characteristic of a metal is its high electrical conductivity.

The fig 1-9 shows the wave function of the valence electron in a sodium crystal indicated by solid line as compared to 3s wave function of a sodium atom indicated by dashed line. The wave function is not disturbed near the ion core but in the outer region it is considerably flattened and squeezed in by neighbouring valence electrons. Since the distribution of electrons in volume element  $4\pi r^2 dr$  is given by  $|\psi|^2 4\pi r^2 dr$  over 90% of the electron distribution is in this flat re-

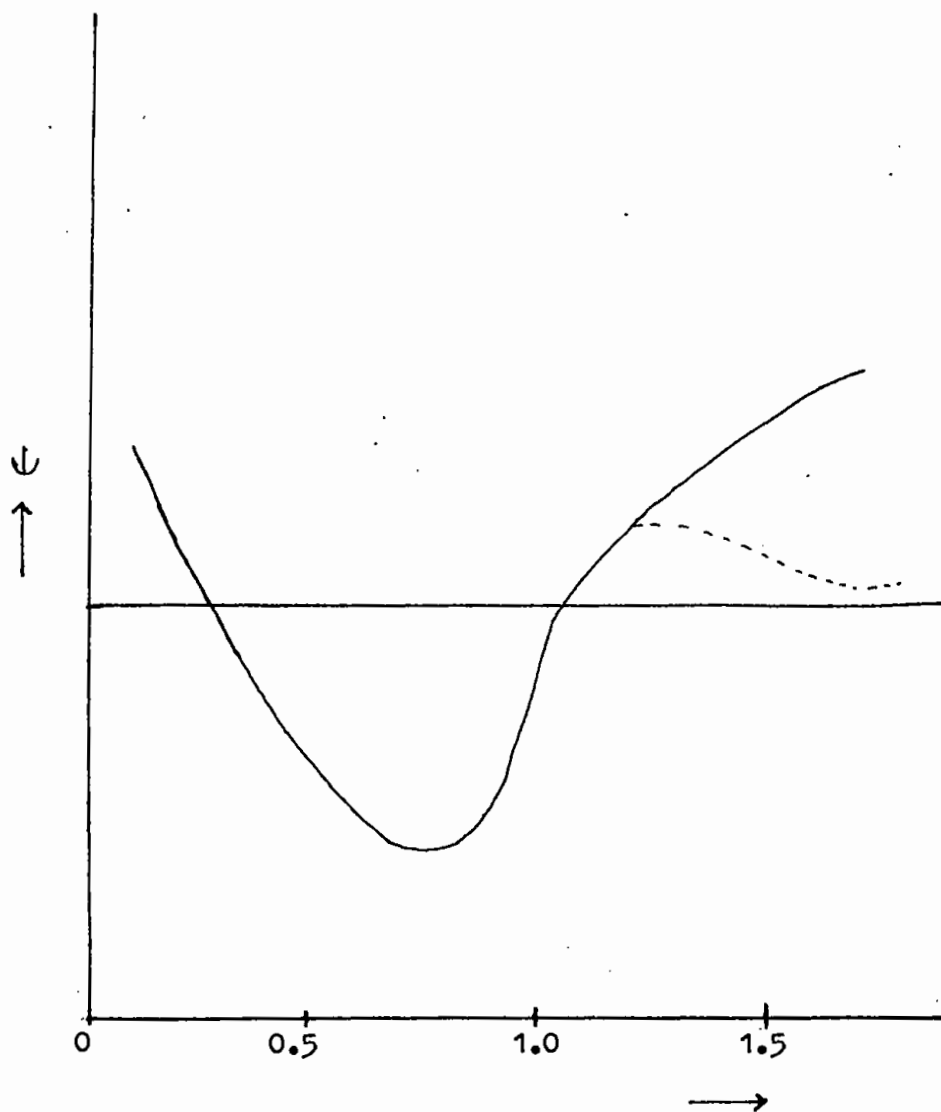


Fig. 1-0: Wave function of valence electrons 3 S wave function ( theoretical)


gion. The potential energy of the electron is obviously lowered because the average electron distribution is now close to the nucleus. The kinetic energy being proportional to  $\left\{ \frac{h}{2\pi} \frac{d\psi}{dr} \right\}$  is also reduced because of a smaller  $\frac{d\psi}{dr}$  in the flattened region. The reduction in the total energy constituted a bond between atoms in a metallic crystal.

In the case of metallic sodium the situation is changed for two essential reasons.


(i) First, each sodium atom has eight nearest neighbours in a body centred cubic structure. Therefore on the average, each atom forms only one eighth of an electron pair bond with one particular neighbour.

(ii) Secondly, as a result of electrostatic interactions the energy levels of the atom broaden out to form a band as the interatomic distance decreases.


The number of quantum states in each band is exactly equal to the number of atomic states multiplied by the number of atoms involved. If the model of covalent binding is adopted we see that quantum states are now available to the third sodium atom. From the view point of covalent bond the metallic bond is unsaturated one and hence there is no contradiction between the two view points.

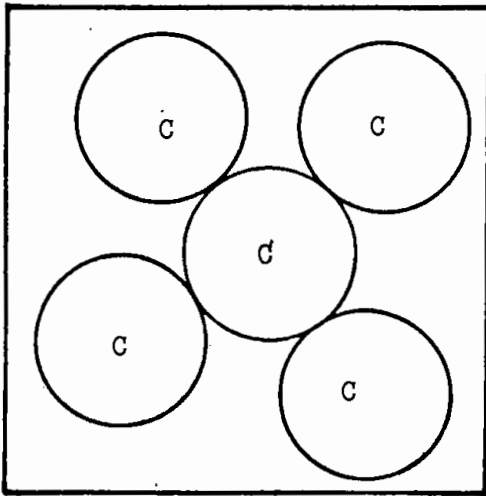


(a) Diamond (covalent)

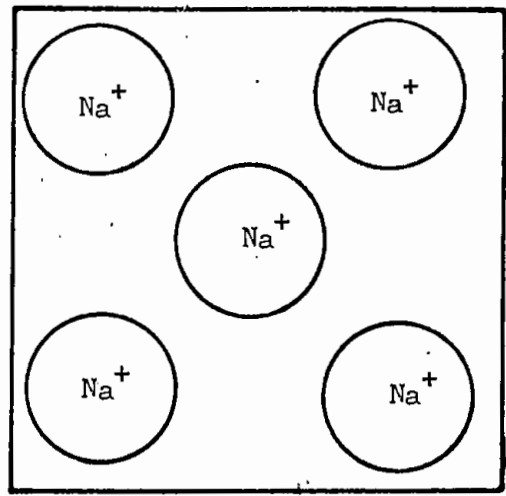

(b) Sodium (metallic)

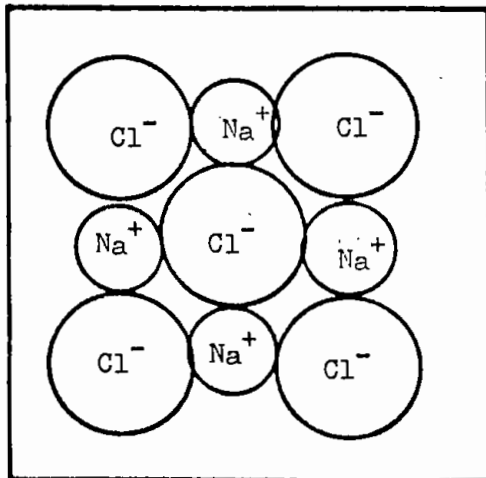

(c) Sodium chloride  
(ionic)

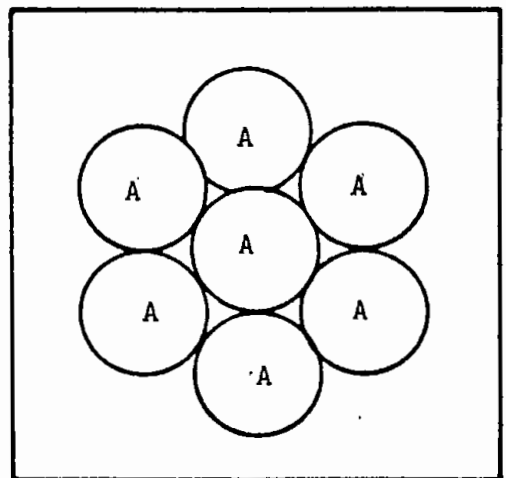

(d) Crystalline (argon  
(van der Waals))

Fig : 1-1 : The Principal types of crystalline bonding forces.

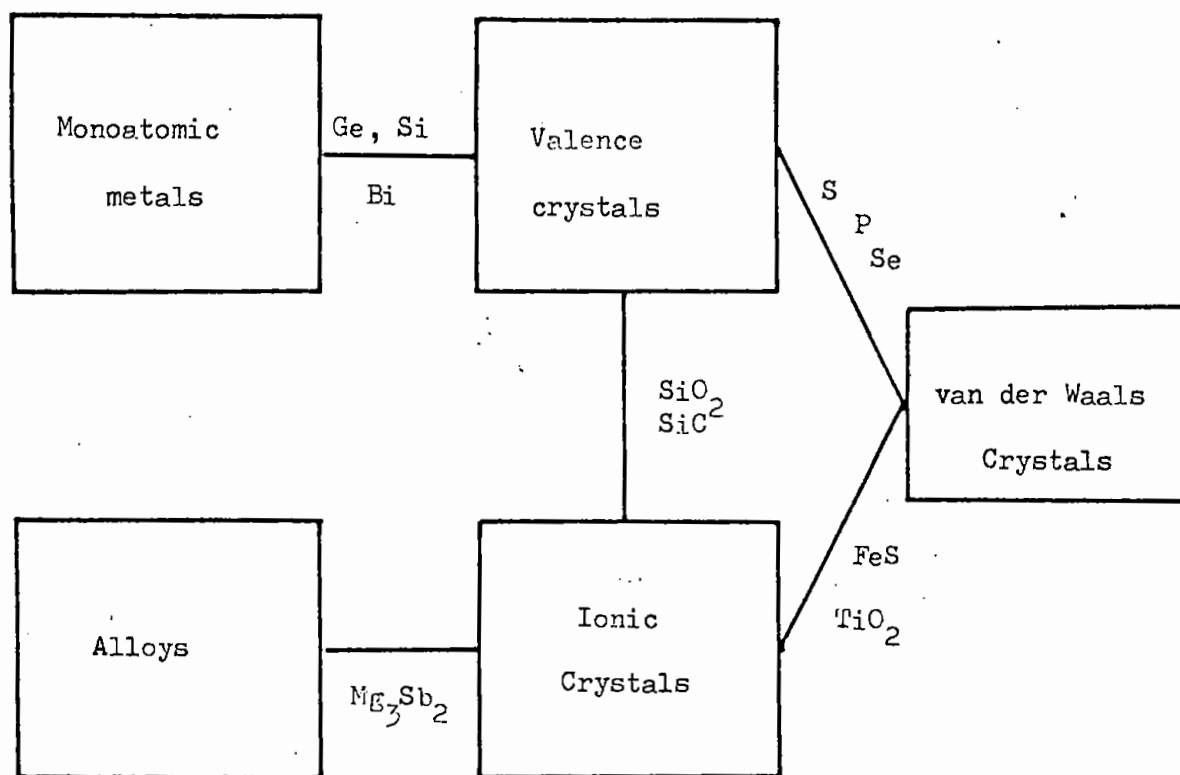


Fig. 1-2 : Classification of solids , Indicating intermediate cases

The transitions between crystal types is not sharp at all, e.g. tin can exist in two crystal forms one being metallic and the other covalent.

It should also be noticed that all semiconductors are not covalently bound. Crystals such as CuO, ZnO and CdS are more ionic than covalent but they have also energy bands as also Ge and Si when sufficient electrons are in the upper band these will behave like semiconductors. Other examples of transition cases include some metal alloys such as Mg, Sb, Zn and As which can be considered partly metallic and partly ionic and some molecular crystals such as S and P are partly molecular and partly covalent.

Metallic crystals have high electrical and thermal conductivity. They have high optical reflection and absorption coefficients. The binding energy of ideal metals such as alkali metals arise from the interaction of the free electron gas.

Hydrogen bond is formed by a hydrogen ion located between two anions. Since hydrogen has only one electron it can lose it to either of the two adjoining ions with the result that there is an equal probability of finding the electron on either ion. The positive hydro-

gen ion tends to draw the two anions more closely together than their normal separation in crystals so that such a shortening of their interatomic separation serves to indicate the presence of a hydrogen bond. It is noticed that the hydrogen bond is largely ionic in character being formed only between the most electronegative atoms, particularly F, O, and N. In the extreme ionic form of the hydrogen bond the hydrogen atom loses its electron to another atom in the molecule; the bare proton forms the hydrogen bond.

#### Crystal structure :

The study of the physical properties of the solid state began in the early years of this century. A century ago the study of crystals was concerned only with their external form and with symmetry relationships among the various co-efficients that describe the physical properties. All atoms are constructed of various elementary particles (electrons, protons, neutron etc) and a complete description of a solid would simultaneously specify the condition of all these particles. The solids have an arrangement of atoms (or molecules) in which the atoms are arranged in some regular repetitious pattern in three dimensions. Such solids are called crystals and the arrangement of atoms is termed the crystal structure. The logical relation

for crystal structure is,

Lattice + basis = crystal structure.

Where a lattice is a regular periodic arrangement of points in space. A lattice is a mathematical abstraction; the crystal structure is formed only when a basis of atom is attached identically to each lattice point. The set of points  $r'$  specified by  $r' = r + n_1 a + n_2 b + n_3 c$  for all values of the integers  $n_1, n_2, n_3$  defines a lattice. The structure of all crystals in terms of a single periodic lattice, but with a group of atoms attached to each lattice point. This group of atoms is called the basis; the basis is repeated in space to form the crystal.

A typical structure of simple ionic solid is illustrated in fig. 1-3 to 1-6. The structure is composed of a number of interpenetrating simple cubic or face-centered cubic Bravais lattices. With reference to the cube axes, the CsCl structure is composed of two sc lattices, one for each species of ions, shifted by a  $\left\{ \frac{1}{2}, \frac{1}{2}, \frac{1}{2} \right\}$  relative to one another, while the NaCl structure and the Zinc blende structure are composed of two fcc lattices, shifted by  $\left\{ \frac{1}{2}, \frac{1}{2}, \frac{1}{2} \right\}$  and  $\left\{ \frac{1}{2}, \frac{1}{2}, \frac{1}{2} \right\}$  respectively. Similarly, the CaF<sub>2</sub> structure is composed of three fcc lattices, one for one species of ions and



two for the other species, shifted with respect to the former by  $\{\frac{1}{4}, \frac{1}{4}, \frac{1}{4}\}$  and  $\{\frac{3}{4}, \frac{3}{4}, \frac{3}{4}\}$ . Finally, the  $\text{Cu}_2\text{O}$  structure is composed of six sc lattices, two for one species of ions, with their origins at  $\{\frac{1}{4}, \frac{1}{4}, \frac{1}{4}\}$  and  $\{\frac{3}{4}, \frac{3}{4}, \frac{3}{4}\}$  and four for the other species, with their origins at  $\{0,0,0\}$ ,  $\{\frac{1}{2}, \frac{1}{2}, \frac{1}{2}\}$ ,  $\{\frac{1}{2}, 0, \frac{1}{2}\}$ ,  $\{0, \frac{1}{2}, \frac{1}{2}\}$ . The unit cell of stoichiometric rutile is tetragonal and contains six ions per unit cell as shown in fig.(1-5). The crystals have the space-group  $p \frac{4_2}{m} \frac{2_1}{n} \frac{2}{m}$  with  $Z=2$ , the cations occupy equivalent position  $2\{a\}$  at  $\{0,0,0\}$  and  $\{\frac{1}{2}, \frac{1}{2}, \frac{1}{2}\}$  with site symmetry  $m m m$ , the anions reside in  $4(f)$  at  $\frac{1}{2}\{(X, X, 0), 1/2+X, 1/2-X, 1/2\}$ , with symmetry  $mm$ .

The existence of a stable bonding arrangement implies that the spatial configuration of positive ion cores and outer electrons has less total energy than any other configuration. The energy deficit of the configuration compared with isolated atoms is known as the cohesive energy and ranges in value from 0.1 ev atom for solids which can muster only the weak van der Waals bond to 7ev/atom or more in some covalent and ionic compounds and some metals. The cohesive energy constitute the reduction in potential energy of the bonded system minus the additional kinetic energy which the Heisenberg uncertainty principle tells us must re-

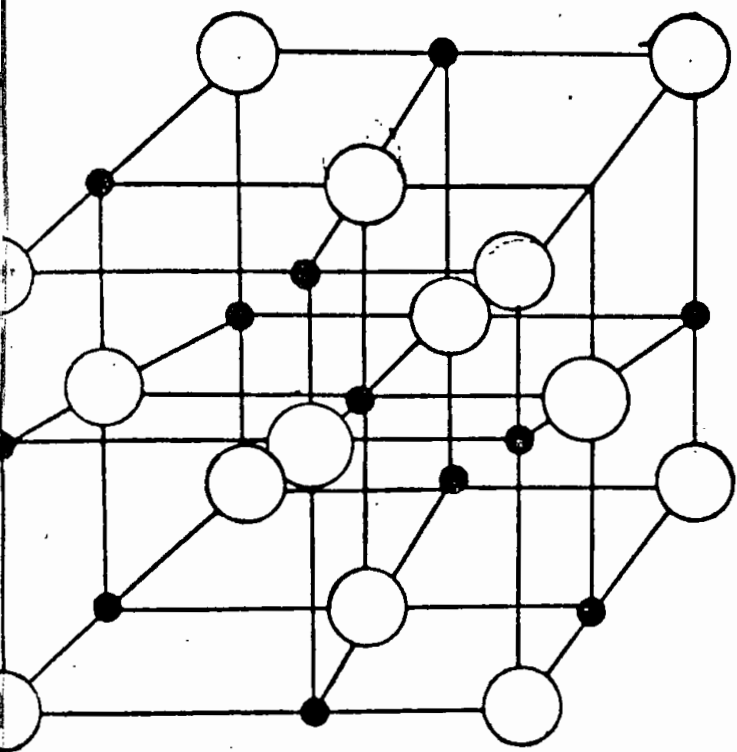


Fig. 1-3 : A lattice cell of sodium chloride structure.

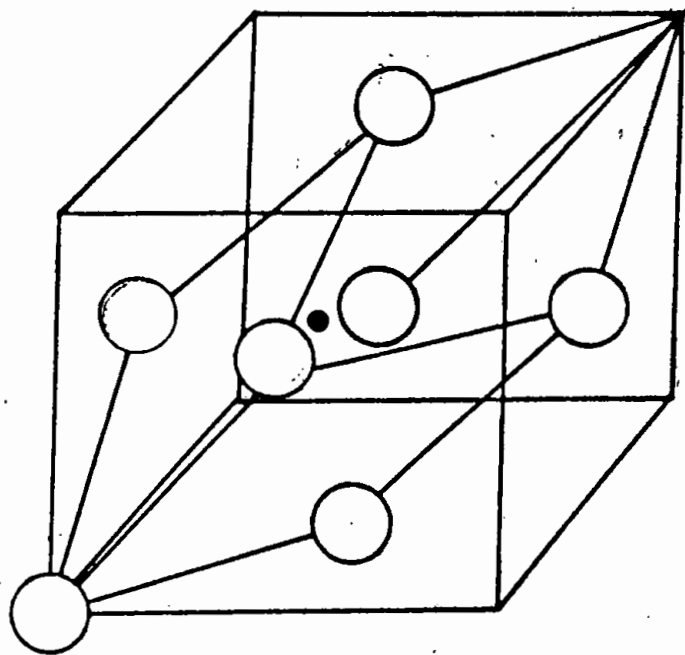


Fig. 1-4 : A unit cell of sodium chloride structure.



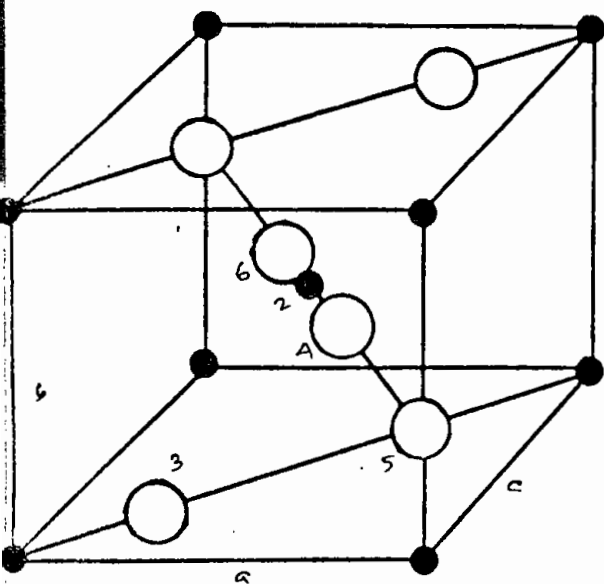


Fig. 1-5 : A lattice cell of rutile structure.



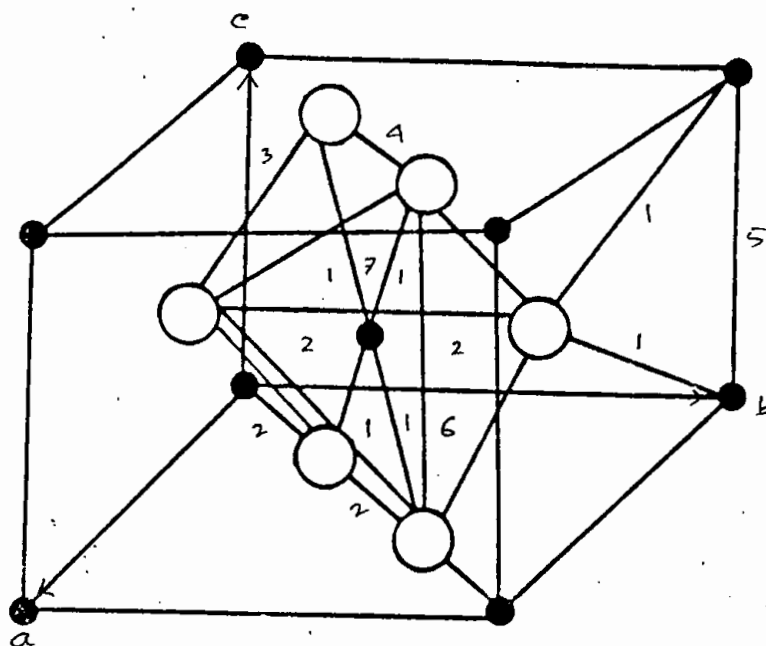


Fig. 1-6 : A unit cell of rutile structure.



sult from localization of the nuclei and outer shell electrons. It shall now be considered the forces which holds the atoms or constituent particles together in a crystalline solid. These forces or bonds are of prime important in understanding differences in the gross structures and characteristic of different solids. Since atoms contain charge particles, they exert forces on each other when brought together. It is due to the influence of these interatomic forces that the constituent particles of a crystal obtain the position corresponding to a minimum energy configuration and thus get bonded together. These interatomic forces were first observed in the field of crystal chemistry and studies on the composition and stabilization of molecules. It is significant to note that investigations of the nature and origin of the interatomic forces did not await the development of X-ray diffraction and crystal structure analysis techniques. Around the mideighteenth century, Desaguliers suggested that these forces were of an electrical nature. This theory was further improved upon by Berzelius in the early nineteenth century. The development of Bohr's theory on atomic structure in 1913 provided the physical basis for the interpretation of the interatomic forces. The discovery of X-ray diffraction and the subsequent advances in

crystal structure analysis provided the necessary means to find out the atomic configuration of molecules whose forms were previously conjectured on the basis of valency theories of chemistry. One significant fact that which emerged from the earliest analysis of the structure of crystals was that no essential distinction existed between the chemical forces which bound the atoms of the chemical molecules and the physical forces which held together the atoms in a crystal. This important finding was significant in two ways. First, it provided physicists with the means to explore the nature of the forces which bound the atoms in crystals by utilizing ideas from chemistry and suitably extending them. Secondly, it opened a way to the physical interpretation of the concept of chemical bonds pioneered by chemists. For the present purpose one shall be concerned with the first of the two aspects. The direct analogy which exists between the two forces also makes it evident as to why one classify the discussion on the bonding of atoms in crystals as chemical bonding.

Next we turn our attention to discuss ionic crystals. The nature of binding in ionic crystals have been a subject of extensive study over the past few decades [1-11]. These studies have been made possible accurate

study on the investigation of the nature of the bonds, cohesive energy and other related chemical properties. A number of attempts have been made to approximate the interionic potential in such crystals by assuming them to be composed of completely ionized atoms, and earlier models along these lines have been proposed by Born and Lande [1], Born and Mayer [2], Rittner [3], Varshni and Shukla [4] and Patel et. al. [5]. These evidences have been accepted as being reasonably successful in describing the ionic bond in diatomic, ionic molecules and crystals. Reviews of the progress in this field have been made by Sherman [6], Waddington [7], Ladd and Lee [8]. The improved in recent years has made possible study of bonding and other related chemical properties in ionic molecules and crystals by Kachhava and Saxena [9], Mathur and Singh [10], Pandey [11], Pandey and Saxena [12], Barr and Lidiard [13] and Redington [14].

Recently Ch. Satyanarayan [15] studied the static properties and stability of structure of ammonium halides. Ammonium halides are diamorphic, crystallizing in the CsCl-type crystal. Structure at low temperature and in the NaCl-type crystal structure at high temperature with the exception of  $\text{NH}_4\text{F}$  which crystallizes in the Wurtzite-type lattices [16]. A predominantly ionic character of binding in ammonium halides [17, 18], moti-

vated the recent researchers to concentrate on the studies of their static and dynamic properties. Bleick[16] computed the cohesive energies of ammonium halides. The van der Waals terms were computed by using London Margena(LM) formulas. But these formulas have been criticized because they are subject to considerable uncertainties. Attempts to compute the cohesive energies have been made by Ladd and Lee[19] ; by Murthy et. al.[17]. and by Singh et. al.[18] with varying degrees of success.

In recent years, a large number of potential energy functions have been applied to study the various thermodynamic properties of alkali halides, by Cubicciotti[20] , Sharma and Madan[21] ,Kachhava[22],Mishra and Sharma [23] and Sharma and Tripathi[24]. J.Shanker and G.D.Jain[25] have developed an interionic force model for mixed alkali halide crystals. Using empirical Born and Mayer exponential form. But it has some shortcomings in describing various properties. Therefore, Harrison [26] has presented a quantum mechanical treatment to calculate the cohesive energy and bulk modulus at NaCl - NaBr, KCl-KBr and KBr-KI mixed crystals.

Studies on the alkali halides provide a critical test of different interionic potentials mainly because

they exist in three different states viz. (i) molten states (ii) crystalline state and (iii) molecular state. The B-M form on alkali halide can not explain the molecular properties of diatomic alkali halides [3, 27]. Woodcock [28] proposed a composite form and applied in alkali halides molecules and crystals by calculating the binding energy and compressibility. This potential [28] has been also applied by Michielsen et. al. [29] in crystalline molecular and molten states. Some errors have been noticed in the treatment of Michielsen et.al. [29]. The errors are corrected by Woodcock[28].

An analysis of interionic potentials in  $\text{CaF}$ ,  $\text{SrF}$  and  $\text{BaF}$  crystals has been performed [30] by modifying the traditional Born model treatment. The cohesive energy, bulk modulus and its pressure derivative for alkaline earth fluoride crystals are calculated. The values are inconsistent in some cases. Alkali halides because of their wide-ranging importance as ionic crystals and molecules have been the subject of extensive studies. For the study of their structures and properties one generally prefer a model potential for them. These potentials are mainly based on electrostatic treatment of interionic interactions and are



very simple and suitable for applications in various fields of physico chemical intercepts. With this view a large number of attempts [2,3,27,31-34] have been performed for ionic molecules. Excellent results of these potentials have been given by Varshni and Shukla [27], and by Das and Saxena [35].

More than twenty compounds crystallize with rutile structure (oxide crystals). The structure consists of a primitive tetragonal lattice with six atoms per unit cell and belongs to the space group  $D_{4h}^{14}$  ( $P_4^{2/mnm}$ ). Such solids exhibit several unusual and interesting features [36] which deserve thorough investigation. Many physical properties of rutile-type compounds have been measured by Grants [37] and Rogers et. al. [38]. The rutile structure oxides with interesting dielectric, magnetic and chemical properties have thus been subjected to many investigations [1,2,28,39-46]. But the controversy about the degree of the ionic nature of these compounds has not yet been settled. Thus an attempt has been made for a thorough theoretical study of rutile structure oxides compounds in this thesis.

General introduction is discussed in chapter 1. Lattice energy and pressure derivative of Bulk moduli are described in chapter 2. The origin and different

empirical forms for repulsive potential (from 1918-1985) are discussed in chapter 3. The origin of van der Waals energy and derivation of van der Waals coefficients are presented in chapter 4. The origin of polarizability, a discussion of polarizability versus ion environment and methods of calculating polarizability are also presented in chapter 4. The calculations and results are discussed in chapter 5. Chapter 6 contains a discussion and a conclusion of the results obtained where it is shown that relatively simple theory with a new RPE function is moderately successful in explaining the properties of crystals under study.

## CHAPTER 2

## LATTICE ENERGY AND PRESSURE DERIVATIVE OF BULK MODULI.

## 2.1 Introduction:

The attractive electrostatic interaction between the negative charges of the electrons and the positive charges of the nuclei is extremely responsible for the cohesion of solids. To understand cohesion one compare the total energy of the solid with the energy of the same number of free neutral atoms at infinite separation. A crystal can only be stable if its total energy is lower than the total energy of the atoms or molecules when free. The difference (free atom energy) - (crystal energy) is defined as the lattice energy.

The total energy per molecule of a crystal relative to infinite separated ions is

$$U_T = U_{LR}^C + U_{SR}^R + U_{SR}^{vdW} + U_{ZP} \quad (2-1)$$

where  $U_{LR}^C$  = Long-range coulomb potential.

$$U_{SR} = U_{SR}^R + U_{SR}^{vdW}$$

$U_{SR}^R$  = short-range repulsive potential.

$U_{SR}^{vdW}$  = short-range van der Waals energy.

$U_{ZP}$  = Zero-point energy.

### A. Long-range Coulomb energy ( $U_{LR}^C$ ):

The Coulomb interaction energy of point like charges  $Z_{p0}$  and  $Z_{p0}$  pertaining to the pth ion in the lth unit cell and to the p'th ion in the reference cell is  $Z_p Z_p e^2 / (r_l + r_p - r_p)$ . The corresponding electrostatic energy of the crystal per molecule is then given by

$$U_{LR}^C = (2n)^{-1} \sum_{l,p,p'} Z_p Z_p e^2 / (r_l + r_p - r_p) \quad (2-2)$$

where the superscript in the summation indicates that the case  $l = 0$  is excluded for  $p = p'$ , and  $n$  is the number of molecules in the unit cell. Equation (2-2) can be rewritten in the form :

$$U_{LR}^C = -(Ze)^2 \alpha_R / R \quad (2-3)$$

where,  $Z$  is the largest common factor of the  $Z_p$ 's and  $R$  is a characteristic length of the crystal structure. The additional quantity  $\alpha_R$  the Madelung constant referred to the characteristic length  $R$  is defined as

$$\alpha_R = - \frac{R}{2n} \sum_p \varphi_p \psi(r_p) \quad (2-4)$$

Here  $\varphi_p = Z_p / Z$  and

$$R \psi(r_p) = \sum_l \sum_p \frac{\varphi_p}{|r_l + r_p - r_p| / R} \quad (2-5)$$

is the electrostatic self potential of the crystal at the lattice point  $r$  when the ionic charges are measured in units of  $Ze$  and the interionic distances in units of  $R$ . The Madelung constant is clearly independent of the absolute value of the ionic charges and of the absolute value of the cell edges; it depends only

on the crystal structure.

#### B. Evaluation of Madelung constant:

The Coulomb energy constant  $\alpha$  was made by Madelung [47]. The general method for lattice sum calculations was developed by Ewald [48] and Evjen and Frank [49] have given simple methods which arrange the counting in rapidly convergent ways.

The Madelung constant is defined as:

$$\alpha = \sum_j' \frac{(\pm)}{p_{ij}} \quad (2-6)$$

where  $p_{ij}$  is the quantity defined by the relation  $r_{ij} \equiv p_{ij} R$  where  $R$  is the nearest neighbour separation in the crystal. If one takes the reference ion as a negative charge the plus sign will be used for positive ions and the negative sign for negative ions. An equivalent definition is

$$-\frac{\alpha}{R} = \sum_j' \frac{(\pm)}{r_j} \quad (2-7)$$

where  $r_j$  is the distance of the  $j$ th ion from the reference ion and  $R$  is the nearest-neighbour distance.

For example one picks a negative ion as reference ion, and let  $R$  denote the distance between adjacent ions. Then

$$-\frac{\alpha}{R} = 2 \left( \frac{1}{R} - \frac{1}{2R} + \frac{1}{3R} - \frac{1}{4R} + \dots \right) \quad (2-8)$$

$\text{Na}^+$  ion at arbitrary zero position

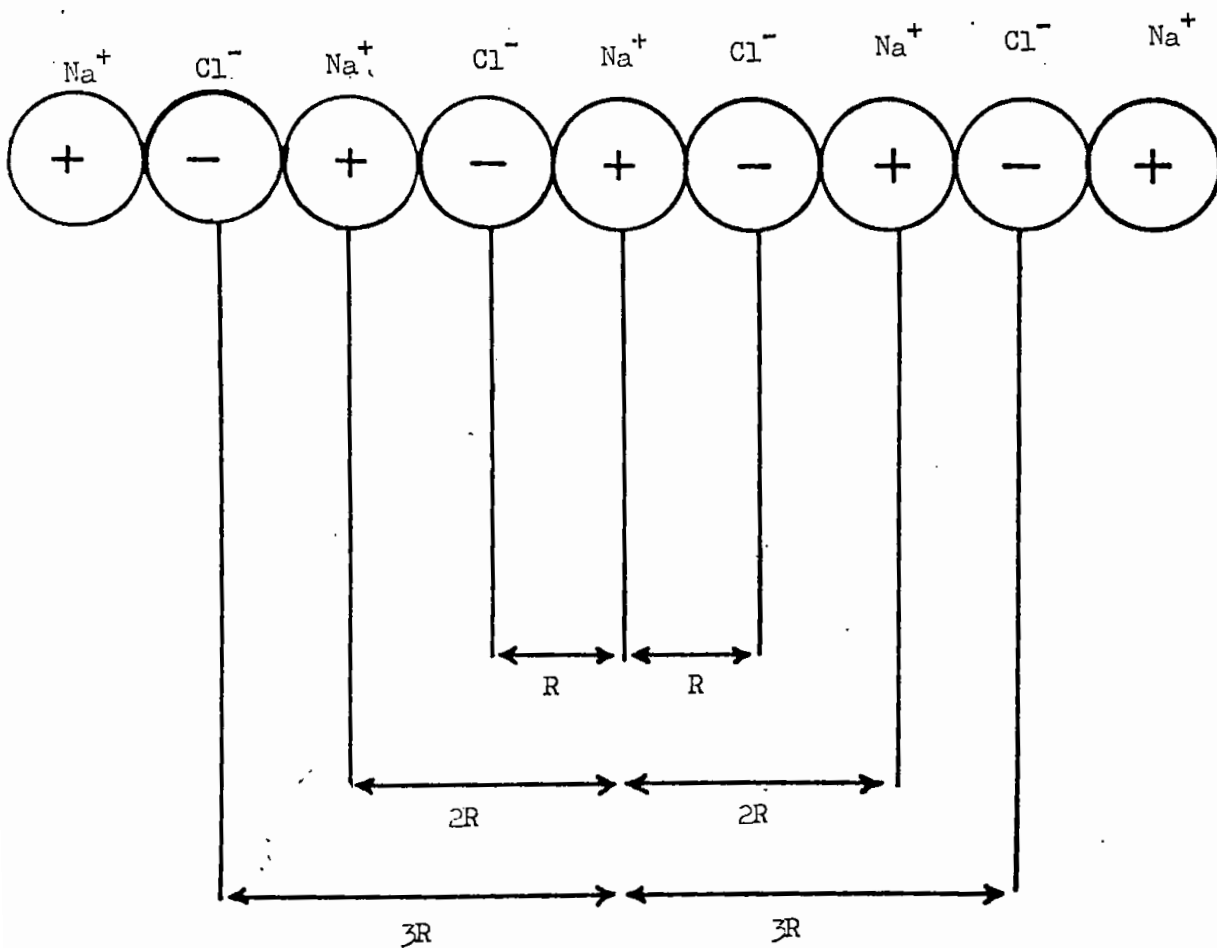


Fig. 2- 1 : One dimensional approximation to the NaCl structure.

the factor 2 occurs because there are two ions, one to the right and one to the left, at equal distance  $r_j$ . One sums this series by the expansion

$$\log(1+x) = x - \frac{x^2}{2} + \frac{x^3}{3} - \frac{x^4}{4} + \dots$$

Thus for the one-dimensional chain the Madelung constant  $\alpha = 2\log 2$ .

### C. Repulsive energy:

The equilibrium conditions for a solid can be satisfied only if the interatomic forces become repulsive at small interatomic distances. The short-range repulsion between atoms is connected with the role of the exclusion principle in opposing overlap of closed electron shells. This is explained simply in the case of two hydrogen atoms with parallel electron spins in their ground state by the comparison between the energy of the triplet state of the molecule computed by first order perturbation theory and the corresponding pseudo-classical energy. These are given respectively[50] by the mean value of the molecular Hamiltonian over the antisymmetrized product of hydrogen 1s wave functions and by the mean value of the molecular 1s wave function,

$$U_{SR}^R(r) = 2 U_H + \frac{e^2}{a_H} e^{-2r/a_H} \left( -\frac{a_H}{r} + \frac{5}{8} - \frac{3}{4} \frac{r}{a_H} - \frac{1}{6} \left( r/a_H \right)^2 \right) \quad (2-9)$$

Here  $U_H$  is the energy of the hydrogen atom in its ground state,  $r$  is the interatomic distance and  $a_H$  is the first Bohr radius. It is showed clearly that the repulsion is due largely to effects which are neglected in the pseudoclassical calculation. It is also seen that the repulsive energy of equation (2-9) in the range of large interatomic distance where this first order perturbation expression applies, decays almost exponentially with increasing interatomic distance, although with a logarithmic rate smaller than  $(\frac{a_H}{2})^{-1}$ . The analogous problem of the interaction between two hydrogen like ions, of net charge  $Z_1 e$  and  $Z_2 e$ , has been worked out by Pauling[51] in the same approximation. The resulting formula for the energy of the triplet state of the molecule involves, besides the Coulomb interaction energy of the net ionic charges, the repulsive energy of equation (2-9) multiplied by a factor approximately equal to  $1 + Z_1 + Z_2$ .

Further discussion about repulsive energy and its different empirical forms are presented in details in chapter 3.



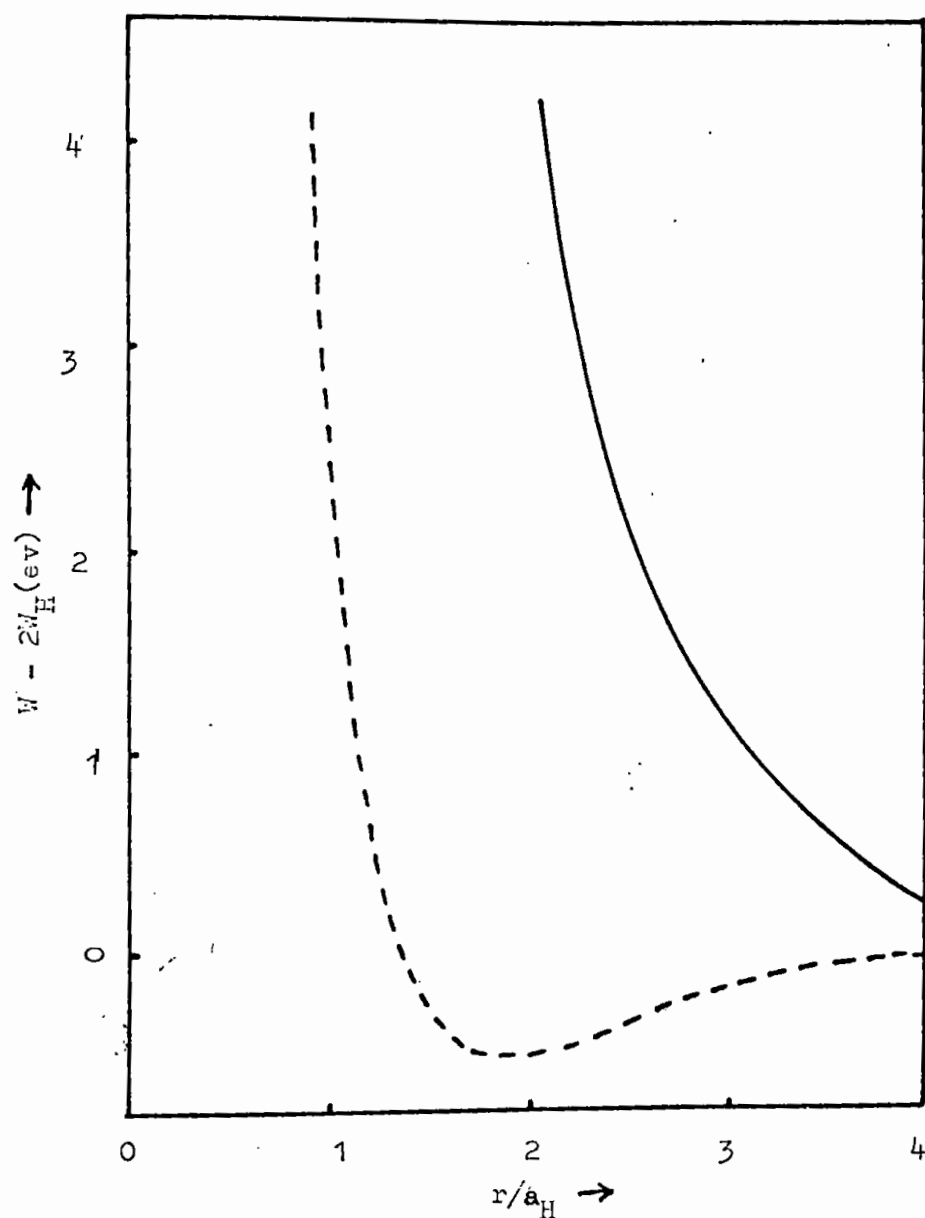


Fig. 2-2 : Interaction energy of the two hydrogen atoms with parallel electron spin in their ground state. The solid curves gives the energy of the triplet state of the molecule and dashed curve gives the pseudoclassical interaction energy.

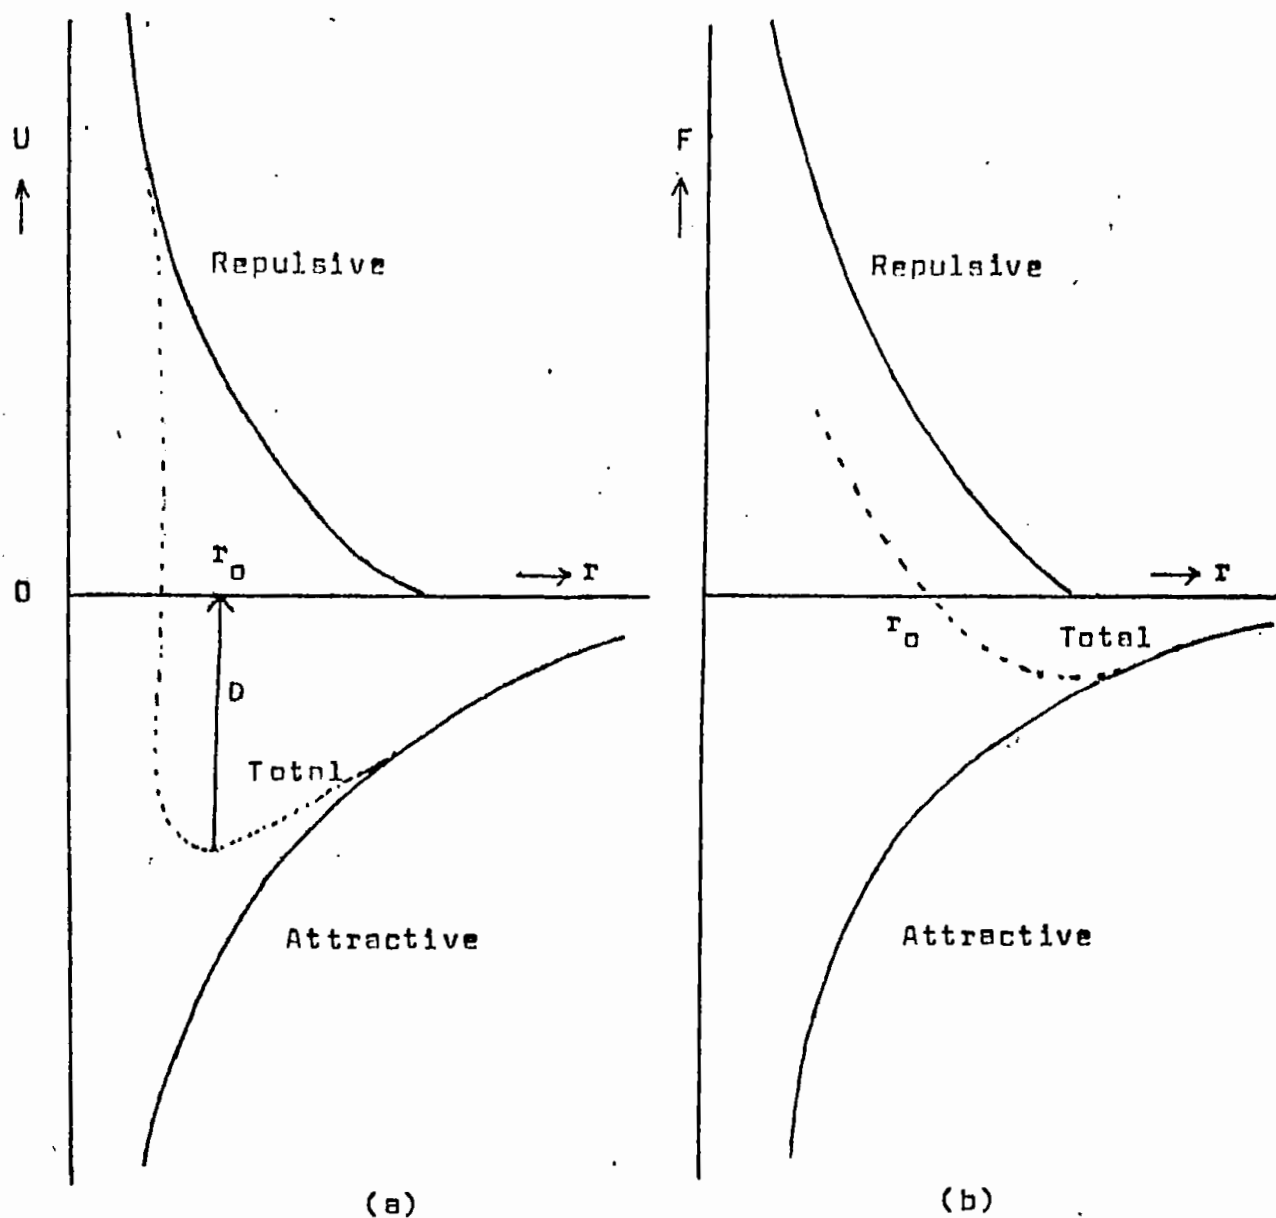


Fig. 2-3 : Schematic representation of the energy (a) and force (b) between two atoms as function of their separation  $r$ . The dashed curves are the sums of the attractive and repulsive curves.

#### D. van der Waals energy:

The existence of condensed phases for the rare gas elements shows that there are attractive interactions between closed shell atoms which are of a different nature from the Coulomb interactions between ions and from the overlap attractive interactions. The physical origin of these so called van der Waals forces is connected with correlations of the electronic motions in different atoms and can actually be understood in semiclassical terms[52]. Indeed, the instantaneous dipole moment  $\mu$  of a closed shell atom induces on a similar atom a distance  $r$  away a dipole moment, which is proportional to  $\frac{\alpha\mu}{r^3}$  where  $\alpha$  is the atomic polarizability and produces at the location of the first atom a field proportional to  $\frac{\alpha\mu}{r^6}$ . The related term in the interaction energy is thus of the form  $-\frac{\alpha\mu^2}{r^6}$  where  $\mu$  is the mean dipole moment of the first atom. In addition to such a dipole-dipole energy term, the consideration of the instantaneous higher moment of the charge distribution of the atoms yields other attractive terms, which decay more rapidly with increasing interatomic separation. The actual evaluation of the van der Waals energy in a solid is unfortunately subject to considerable uncertainties. However, this is only a minor part of the cohesive energy of an ionic solid in

standard thermodynamic conditions and possible errors in its value are largely compensated in a Born model treatment in the fitting of the parameter entering the overlap repulsive energy. The detailed of the van der Waals energy are described in chapter 4

#### E. Zero point energy:

A great step forward toward an understanding of the specific heat curves at low temperatures was made by Einstein[53] in 1906. For the average energy of an oscillator Einstein made use of a result obtained by Planck in 1900, in connection with the theory of black-body radiation. According to Planck, a harmonic oscillator does not have a continuous energy spectrum as assumed in the classical theory, but can accept only energy values equal to an integer times  $h\nu$ , where  $h$  is Planck's constant. The possible energy levels of a harmonic oscillator are given quantum mechanically by:

$$e_n = (n + \frac{1}{2}) h\nu \quad \text{where } n = 0, 1, 2 \quad (2-10)$$

This has the effect of shifting all energy levels by the constant amount  $h\nu/2$  and instead of Planck's average energy of an oscillator shown in the Fig. 2-3 at a temperature  $T$ , one obtains

$$\langle e \rangle = \frac{h\nu}{2} + \frac{h\nu}{e^{h\nu/KT} - 1} \quad (2-11)$$

The first term is called the zero-point energy of the oscillator because  $\langle e \rangle = -\frac{h\nu}{2}$  for  $T=0$ . Now in the Debye theory of the specific heat of solids, a crystal is represented formally by a system of harmonic oscillators with a frequency spectrum given by:

$$F(\nu) d\nu = 4V \left( -\frac{2}{c_t^3} + -\frac{1}{c_l^3} \right) \nu^2 d\nu \quad (2-12)$$

where  $V$  is the volume of the crystal and  $c_t$  and  $c_l$  are, respectively the velocities of propagation of transverse and of longitudinal elastic waves. Making use of the definition of the Debye frequency  $\nu_D$ . One may write

$$F(\nu) d\nu = \left( -\frac{9N}{\nu_D^3} \right) \nu^2 d\nu \quad (2-13)$$

where  $N$  stands for the total number of atoms or ions in the crystal. Hence, at absolute zero, the contribution of the zero-point energy is

$$\frac{1}{2} \int_0^{\nu_D} F(\nu) h\nu d\nu = 9/8 N h \nu_D \quad (2-14)$$

per ion pair, this corresponds to  $9h\nu_D/4$ . With a Debye frequency of the order of  $10^{12}$ – $10^{13} \text{ sec}^{-1}$  this gives about 0.1 ev. As a correction to the lattice energy the zero-point energy, this contributes about 1 percent. The zero-point energy is very important for light elements (high Debye frequency).

## 2.2 Pressure derivative of bulk modulus:

In order to evaluate the pressure derivative of bulk modulus let us first consider the definition of bulk modulus. The bulk modulus  $B$  defined as:

$$B = -V \frac{dp}{dv} \quad (2-15)$$

Neglecting thermal effects, from the first law of thermodynamics one may write,

$$dU = -pdV \quad (2-16)$$

$$\text{or} \quad \frac{dp}{dv} = - \frac{d^2U}{dv^2} \quad (2-17)$$

$$\text{Therefore } B = V \frac{d^2U}{dv^2} \quad (2-18)$$

It is well known to all  $V = 2NR^3$  as volume per molecule is  $\frac{1}{4}a^3$  and  $a = 2R$ . Where  $N$  is the total number of molecules and  $R$  is the nearest neighbour distance. Thus one may write

$$\frac{dU}{dv} = \left( \frac{dU}{dR} \right) \left( \frac{dR}{dv} \right) \quad (2-19)$$

$$\begin{aligned} \frac{d^2U}{dv^2} &= \frac{d}{dv} \left( \left( \frac{dU}{dR} \right) \left( \frac{dR}{dv} \right) \right) \\ &= \frac{dU}{dR} \cdot \frac{d^2R}{dv^2} + \left( \frac{d^2U}{dR^2} \right) \left( \frac{dR}{dv} \right)^2 \end{aligned} \quad (2-20)$$

At the equilibrium separation  $R=R_0$  and  $\left( \frac{dU}{dR} \right) = 0$  so that

$$B = \frac{1}{18 R_0^3} U(R) \quad R = R_0 \quad (2-21)$$

$$\begin{aligned} \text{using } \left( \frac{dR}{dv} \right)^2 &= \frac{1}{36N^2R^4} \\ \left( \frac{dB}{dp} \right)_T &= 1 - \left( \frac{+R_0^3}{27V} \right) \frac{U(R_0)}{U(R_0)} \\ &= 1 - \frac{18R_0 \cdot R_0^3}{27 \cdot 2 \cdot R_0^3} \cdot \frac{U(R_0)}{U(R_0)} \end{aligned} \quad (2-22)$$

where  $\tau = 1/B$ , is the compressibility and is defined as the reciprocal of the bulk modulus. Thus equation (2-22) may be written as:

$$\left( \frac{dB}{dp} \right)_{\tau} = 1 - \frac{R_0^3 (U(R_0))}{3R_0^3 (U(R_0))} \quad (2-23)$$

### 2.3 The energy from the Born-Haber cycle:

The theoretical value of the lattice energy can be compared with the experimental value determined by a Born-Haber cycle analysis. In this method, one considers all the steps involved in transforming one mole of Ti, Si, Ge and Sn respectively and one mole of molecular oxygen gas into one mole of rutile. The energy associated with each step of the cycle can be determined from thermochemical data. The formula for the energy is:

$$U = 4H - L - D + 2A - I_4 \quad (2-24)$$

where  $H$  is the heat of formation of rutile,  $L$  is the heat of vaporization of Ti, Si, Ge and Sn respectively,  $D$  is the dissociation energy of  $O_2$  gas,  $A$  is the affinity of the oxygen atom for two electrons and  $I$  is the sum of the first four ionization potential of the Si, Ti, Ge and Sn atom respectively.

## CHAPTER 3

## REPULSIVE INTERACTIONS

## 3.1. Origin of Repulsive interaction:

A qualitative picture of the origin of the repulsive force may be given as follows:

When  $M^+$  and  $X^-$  ions approach each other closely enough so that the orbitals of the electrons in the ions begin to overlap each other, then the electrons begin to repel each other by virtue of the repulsive electrostatic Coulomb force. Of course, the closer together the ions are, the greater the repulsive force, which is in qualitative agreement with experimental observation. Without paying attention to the physical origin of the forces between the atoms, let us assume that the potential energy of atom M due to the presence of atom X is given by an expression of the type:

$$U(r) = -\frac{\alpha}{r^n} + \frac{\beta}{r^m} \quad (3-1)$$

where  $r$  is the distance between the nuclei of the two atoms;  $\alpha, \beta, m$  and  $n$  are constants characteristic for the MX molecule. The zero of energy is chosen such that for infinite separation,  $U=0$ . The first term, which is negative, corresponds to the energy associated with the force of attraction, the second (positive) term corresponds to the forces of repulsion. In fact, the force between



that two atoms as a function of  $r$  is given by

$$F(r) = -\frac{dU}{dr} = -\frac{n\alpha}{r^{n+1}} + \frac{m\beta}{r^{m+1}} \quad (3-2)$$

The energy and the force between two atoms  $M^+$  and  $X^-$  which form a chemical compound are represented in Fig. 3-1(a), Fig. 3-1(b).

The stable configuration for the system corresponds to the minimum  $U(r)$  curve, which occurs for a particular separation,  $r=r_0$ . The corresponding energy  $U(r_0)$  is negative; thus the positive quantity  $D = -U(r_0)$  is the dissociation energy of the molecule i.e. the energy required to separate the two atoms.

Dissociation may occur, for example, at high temperatures or as a result of other process in which the molecule can absorb sufficient energy. The dissociation energies are of the order of one or a few electron volts.

Assuming that the energy curve exhibits a minimum, one may express the equilibrium distance  $r_0$  and the corresponding binding energy  $U(r_0)$  in terms of the constants  $\alpha, \beta, m$ , and  $n$  by making use of the condition

$$\left( -\frac{dU}{dr} \right)_{r=r_0} = 0 \quad \text{i.e.} \quad r_0^{m-n} = \left( \frac{m}{n} \right) \left( \frac{\beta}{\alpha} \right) \quad (3-3)$$

According to (3-2) this condition is equivalent to the requirement that the attractive and repulsive forces

balance i.e.  $F(r) = 0$ . substituting from (3-3) into (3-

1) one obtains for the energy in the equilibrium state

$$U(r) = - \frac{\alpha}{r_0^n} + \frac{\beta}{r_0^m} = - \left( \frac{\alpha}{r_0^n} \right) \left( 1 - \frac{n}{m} \right) \quad (3-4)$$

It is noted that although attractive and repulsive forces are equal in equilibrium, the attractive and repulsive energies are not equal since  $n \neq m$ . In fact if  $m \gg n$ , total binding energy is essentially determined by the energy of attraction  $- \frac{\alpha}{r_0^n}$

As one may expect already by looking at fig. 2-3(a), a minimum in the energy curve is possible only if  $m > n$ ; thus the formation of a chemical bond requires that repulsive forces be of short range than the attractive ones. This may be shown by employing the condition that  $\left( -\frac{d^2U}{dr^2} \right)_{r=r_0} = 0$  if must have a minimum at  $r_0$ . In fact, this condition leads to

$$-n(n+1) \frac{\alpha}{r_0^{n+2}} + \frac{m(m+1)}{r_0^{m+2}} > 0 \quad (3-5)$$

which upon substitution of  $r$  from (3-3) immediately gives

$$m > n \quad (3-6)$$

### 3.2 Different empirical forms:

#### i) Born-Lande potential (1918):

Many years ago Born and Lande[1] used an inverse power repulsive term in the potential function for alkali halide crystals. For gaseous ionic molecule Born-Lande proposed a potential function in which the repulsive energy is expressed as:

$$\phi(r) = br^{-n} \quad (3-7)$$

where  $b$  and  $n$  are constants. This repulsive energy was much used in the potential energy during the twenties for investigating ionic crystals. Krebs[54] applied equation (3-7) to LiH and NaH and later paper[55] discussed the nature of alkali hydrides in the gaseous state. Rice[56] has determined the value of  $n$  from the lattice energy data and has used it to calculate the binding energy of gaseous alkali hydrides. The above equation has also been employed by Mulliken[57] in discussing the nature of the binding in LiH.

Investigation of interionic forces that have been carried out on the basis of quantum mechanical calculations of forces between ions showed that an inverse power repulsive term was not satisfactory. The calculated values of  $\alpha_0$  (rotational constant and vibrational constants  $\omega_e x_e$ ) are too high and the ionic binding energy  $D_e$  are too low. Thus it is found that BL potential is not satisfactory for alkali hydrides. However, it is interesting that for a particular constant ( $\alpha_0$ ,  $\omega_e x_e$ , or  $D_1$ ) the percentage error is in the same direction, for all the molecules.

#### ii) Born-Mayer potential (1932):

In most applications of the Born model since 1930,

the repulsive energy of the closed shell ions has been assumed to vary exponentially with their distances, in keeping with quantum mechanical results (Heitler and London[50] , 1927). The repulsive energy, as a function of the nearest-neighbour distance  $r$ , is expressed by Born and Mayer[2] (1932) in the form:

$$\phi(r) = a e^{-r/\rho} \quad (3-8)$$

where  $a$  and  $\rho$  are the repulsive parameter. The BL model is the most successful of the previous models. However, in other respects a representation of the repulsive term as good an exponential function (Born and Mayer). One argument that has been frequently advanced in support of the exponential function is that such a term is predicted by quantum mechanical calculations. Theoretical treatment of the repulsive forces between closed shell anion and point cations have tended to support the assignment of an exponential term. However, several of the theoretical results are in serious disagreement with the experimental data. Thus the available evidence suggests that present quantum mechanical treatments can not be applied to the representation of the binding energy in diatomic ionic crystals. Finally, as Dobbs and Jones[58] remark "The exponential form for the repulsive potential makes calculation of the lattice properties rather complicated and in any case is

perhaps, not valid in the region near the minimum of the total potential which is of course the essential part in considering the properties of the lattices."

iii) Wasastjerna potential (1935):

Wasastjerna[33,34] , in 1935 investigated an extended form of the repulsive potential for Na, Rb and Cs halide crystal. This is as follows:

$$\phi(r) = c r^7 e^{-\beta r} \quad (3-9)$$

where  $c$  and  $\beta$  are constants.

With the repulsive potential the Wasastjerna potential gives rise to negative  $\alpha_e$  (rotational constants). The vibrational constants  $\omega_e \times e$  very high and the ionic binding energy  $D_1$  are excellent agreement with the observed ones. It is the remarkable phenomenon that it is able to reproduce one of the constant ( $D_1$ ) very successful, but fails completely for the other two.

iv) Hellmann potential (1936):

Some 25 years ago, Hellmann[31,32] introduced the following repulsive potential in the potential energy to represent the interaction between the valence electron and the core in an alkali atom:

$$\phi(r) = -\frac{T}{r} \cdot C^{-\lambda r} \quad (3-10)$$

where  $T$  and  $\lambda$  are constants. Since then it has been used for the electron-core interaction by a number of

workers[59-63]. However, as far as we have been able to find, this potential has never been used before as the interaction potential. It has been found that such a potential yields satisfactory results for representing the shape of interatomic potential energy curves of alkali hydrides at least in the neighbourhood of the equilibrium internuclear distance.

v) HM potential:

M.L.Huggins and J.E.Mayer[64] in 1937 proposed a form of repulsive potential which is as follows:

$$W = M \left( \frac{b_+}{r} + \frac{b_-}{r} \right) e^{-r/\rho} + \frac{1}{2} M \left( \frac{b_+^2}{r^2} + \frac{b_-^2}{r^2} + \frac{b_+ b_-}{r^3} \right) e^{-r/\rho} \quad (3-11)$$

where  $b_+$  and  $b_-$  are the characteristic parameters and the parameter  $\rho$  can be determined by a simultaneous fit for the salts of the family. It should be simultaneously emphasized that the fit of the repulsive parameters to crystal data is effectively used in the Born model to correct, in an appropriate way, the approximations made in the assumed expression of the lattice energy. The mean deviation of the values of  $n$  in the individual salts yielded by equation  $n = \left( \frac{\rho}{r} \right)^{-1}$  from their mean value amounts to 6% as for the original Born-Mayer calculation, but the root-mean square deviation is as large and 10% as large discrepancies between the average and the individual value of  $n$  are apparent in a

few salts. This implies that the Huggins-Mayer form of the Born repulsive energy does not provide a good fit of the compressibility for all the salts.

vi) Verwey potential (1946):

Verwey[65] in 1946 proposed a harder core potential function in which the repulsive energy is expressed as:

$$\phi(r) = \mu r^{-12} \quad (3-12)$$

where  $\mu$  is the repulsive parameter. The Verwey potential have been used by workers (Guccione, Tosi and Asdente[66] 1959, Tharmalingham[67] in 1963, 1964, Boswarva and Lidiard[68] in 1967) in the calculations of activation energies and defect energies.

vii) Dick-Overhauser potential (1958):

Regardless of the attractive force between atoms it known that the atoms remain a finite distance apart at equilibrium. Thus a repulsive force must set in suddenly at short distances and balance the attractive force at the equilibrium distance between atoms. This repulsive force arises in part from the application of the Pauling exclusion principle, since the exclusion principle opposes the overlapping of the saturation electron clouds of the different atoms.

The simplest mathematical form for a potential which

yields a sudden repulsion at short distances is expressed within the Born-Mayer model[2] as  $\phi = a e^{-r/\rho}$ . The form of the potential is not obtained from first principles but, nevertheless, represents the repulsive interaction satisfactorily between two ions, as for example, between two helium atoms or two neon atoms. However, as a general model the potential is quite unsuitable for the whole alkali halide series.

The electronic shells in the ions of alkali halides are closed shells and thus can be thought of as being similar to helium atoms except for the increased electronic and nuclear charges. It can reasonably be expected that the results obtained from a study of the interaction of two atoms (helium) can be applied to the more general case of alkali halides. By evaluating the helium-helium interaction integrals, Dick and Overhauser[69] have shown that the total repulsion in this system can be represented by:

$$\phi = e \cdot Q_{ex} / 2r \quad (3-13)$$

where  $Q_{ex}$  is the exchange charge. The nature of the exchange charge can be inferred from a considerable method of Lowdin's technique of symmetrical orthogonalization[70], which takes into account the lack of orthogonality of the ionic electronic wave function due



to overlap. When the value of  $Q_{ex} = 4 e^2 S_{MX}^2$  as determined by Hefemeister and Zahrt[71] is substituted in (3-13) becomes

$$\phi_{rep} = 2 \cdot S_{MX}^2 e^2 / r \quad (3-14)$$

It may be noticed that the overlap integral  $S_{MX}$  in equation (3-14) is a complex function of  $r$ . Rather than being a single exponential it is the sum of number of exponentials, each with complex multiplicative terms. The Born-Mayer form for  $\phi_{rep}$  is thus an oversimplification of the actual results.

viii) Varshni-Shukla potential (1961)

Varshni and Shukla[72] in 1961 proposed a more complicated form of potential for the repulsion between closed shell ions,

$$\phi_{rep} = \lambda_1 e^{-k_1 r^2} \quad (3-15)$$

Where  $\lambda_1$  and  $k_1$  are the repulsive parameters. Recently it has been found that the potential is reasonably satisfactory for the alkali halides. The rotational constants  $\alpha_e$  for LiH and NaH negative, which is contrary to observation. Except for LiH, the vibrational constants  $\omega_e$  are 20% lower than the observed ones. The ionic binding energy  $D_1$  is satisfactory. But the potential is very much unsatisfactory in reproducing other molecular constants. For the above model, one has:

$$\lim_{r \rightarrow 0} U(r) = -\infty \quad (3-16)$$

ix) Benson-Dempsey potential (1962):

Jai Shanker et.al.[30] in 1981 used Benson-Dempsey[73] repulsive potential for analysis of interionic potential in alkaline earth fluoride crystals. The repulsive energy by taking into account the interaction between nearest and next nearest neighbour cation-cation, cation-anion and anion-anion can be written as follows:

$$\phi(r) = 8 \rho_{+-} b e^{(r_+ + r_- - r)/\rho_{+-}} + 6 \rho_{++} b e^{(2r_+ - k_1 r)/\rho_{++}} + 2 \rho_{--} b e^{(2r_- - k_2 r)/\rho_{--}} \quad (3-17)$$

where  $\rho_{ij}$  are the co-efficients introduced by Pauling[74] in order to provide appropriate weightage for the various pair interactions.  $b$  and  $\rho_{ij}$  are the strength and hardness parameters.  $r_+$  and  $r_-$  are the radii of cation and anion respectively;  $k_1 = 1.1547$  and  $k_2 = 1.6330$ . Values of  $\rho_{ij}$  are derived using the correlation between repulsive energy and overlap integrals for the pair of neighbouring ions[74]

$$b_{ij} e^{-r_{ij}/\rho_{ij}} = 2 \gamma e^2 S_{ij}^2 / r_{ij} \quad (3-18)$$

where  $\gamma$  is a dimensionless proportionally constants introduced by Dick and Overhauser[69].  $S_{ij}$  for various ion pairs in  $\text{CaF}_2$  and  $\text{BaF}_2$  crystals have been reported by Ra[75]. Values of  $\rho_{ij}$  based on these overlap integrals. The repulsive strength parameter  $b$  can be calculated from the crystal equilibrium condition. The cohe-

sive energy obtained by Benson and Dempsey[73] are in slightly better agreement with experiment.

x) HF potential (1965):

The Hefemeister and Flygar[76] form of SR overlap repulsive energy extended to the next nearest neighbour ions with  $b$  and  $\beta_{ab}$  as the hardness and range parameters can be written as:

$$\phi(r) = \sum_{ab} \rho_{ab} b e^{r_a + r_b - r_{ab}} / \rho_{ab} \quad (3-19)$$

where  $a, b = 1, 2, \dots$  and  $\rho_{ab}$  are the Pauling coefficients defined as:

$$\beta_{ab} = 1 + \frac{Z_1}{n_1} + \frac{Z_m}{n_m} \quad (3-20)$$

where  $Z_1$  and  $Z_m$  are the valencies and  $n_1$  and  $n_m$  the number of outermost electrons of the 1th and mth ions.  $r_1$  and  $r_m$  are the ionic radii.

R.K. Singh and P. Khare[77] analysed the anharmonic properties of silver thallium and copper halides by means of this interionic potential model incorporating the effects of the long-range coulomb and three body interactions and the short-range vdW attractive and overlap repulsion. The results by using HF potential agree fairly well with the available experimental data and show a consistent trend through out.

xi) Modified Varshni-Shukla potential:

Patel, Gohel and Trivedi et.al.[5,78] adopted a slightly different potential function for the repulsion to that proposed by Varshni and Shukla[72]. Specifically, this potential function can be expressed as:

$$\phi(r) = \frac{1}{2} e^{-k_2 r^{3/2}} \quad (3-22)$$

where  $\lambda_2$  and  $k_2$  are the repulsive parameters. The rotational constants  $\alpha_0$  are too high. The average percentage error of vibrational constant  $\omega_e x_e$  is the lowest amongst the potential. The binding  $D_e$  are about 10% lower than the observed ones. For  $\omega_e x_e$ , (3-22) improves upon (3-10) but for average percentage error by (3-22) is nearly twice of that by (3-10). For  $D_e$  also, the results by (3-22) are uniformly less satisfactory than those by (3-10).

xii) HZ form of overlap repulsion potential:

R.K. Singh and S.P. Sanyal[79] used an overlap repulsion potential for analysing the cohesive and thermodynamic properties of alkaline earth oxides by extending HF and HZ potentials to include the three-body interaction effects. The extended HZ [71] potential can be written as:

$$\phi(r) = N_b \sum_{ij} \frac{\beta_{ij}}{r_{ij}} e^{(r_1 + r_2 - r_{ij})/\rho_{ij}} \quad (3-23)$$

where  $i$  and  $j$  denotes respectively either ion 1 or 2;  $\beta_{ij}$  are the Pauling co-efficients defined as:

$$\beta_{ij} = 1 + \frac{Z_i}{n_i} + \frac{Z_j}{n_j} \quad (3-24)$$

with  $Z_i$  ( $Z_j$ ) and  $n_i$  ( $n_j$ ) as the ionic charge parameters ( $\pm 2$ ) and the numbers of electrons ( $= 8$ ) in the outermost shells of cations and anions;  $r_i$  and  $r_j$  are the ionic radii whose values have been taken from Pauling[74]. The cohesive energies calculated from the present extended HZ form of potential are in better agreement with experimental data than those obtained by previous investigators. It is also seen that the results obtained with HZ potential are much better than those of the HF potential. The extended HZ potential has yielded results much closer to the experimental results on cohesive energy, its overall superiority has been obtained by performing calculations of various thermophysical properties of AEO crystals.

xiii) GT potential (1968):

The appropriateness of the Born-theory of ionic crystals is being successfully for alkali hydride crystals for which a little work is available in literature. A new form of overlap repulsion energy term[80] for alkali hydride earlier suggested by Gohel and Trivedi[45] for alkali halides of the form.

$$\phi(r) = P/r e^{-K r^2} \quad (3-24a)$$

where  $P$  and  $K$  are the repulsive parameters and  $r$  is the

interionic distance. This form (3-24a) has been suggested to study the lattice properties of hydrides.

The crystal energy may be expressed as the sum of coulombian attraction energy, the overlap repulsive energy, the point energy and the van der Waals interaction energy terms. The compressibility predicted by [80] and is superior to those predicted by Das and Sexena [35]. The co-efficient of thermal expansion is in good agreement with the experimental value.

xiv) Prakash-Behari logarithmic potential (1969):

Prakash and Behari [81] suggested a logarithmic form repulsive energy in ionic crystals that has subsequently been adopted by Mishra et. al. [72] (1971) and by Sharma and Jain [83] in 1973, to study the properties of these crystals. The new potential is given by

$$\phi(r) = a \log (b + br^{-9}) \quad (3-25)$$

where  $a$  and  $b$  are the repulsive parameters. It has been found that depends sensitively on the form of the potential for the repulsive energy used within the frame work of the Born model. It should be remarked that the logarithmic potentials yield almost identical values of the cohesive energies and that these are consistently higher in magnitude than those based on experimental thermodynamic data. In contrast, the va-

lues of  $\delta$  derived from these two forms of potential Verway and log.differ significantly each other.

xv) Redington potential (1970):

Redington[14] in 1970 proposed a form of repulsive potential

which can be represented by:

$$\phi(r) = a_1 e^{-\beta r} + a_2 e^{-\beta r/2} + a_3 e^{-\beta r/3} \quad (3-26)$$

where  $a_1$ ,  $a_2$  and  $a_3$  are some constants and  $\beta$  is the repulsive parametrs.

xvi) Katiyar potential (1970):

For the analysis of inter~~onic~~ potential in rutile structure  $MX_2$  crystals corresponding to MRIM, Katiyar[84] presented a SR repulsive energy given by

$$\phi(r) = 4 \psi_1(R_1) + 8 \psi_2(R_2) + 16 \psi_3(R_3) + 2 \psi_4(R_4) \quad (3-27)$$

where  $R_1$ ,  $R_2$ ,  $R_3$  and  $R_4$  are the four different cation-anion, and anion-anion distances in rutile structure defined by Striefler and Barsch,[36]

$$\text{where } \psi_1(R_1) = B_{+-} b e^{(r_+ + r_- - K_1 R)/\rho_{+-}} \quad (3-28)$$

$$\psi_2(R_2) = B_{+-} b e^{(r_+ + r_- - k_2 R)/\rho_{+-}} \quad (3-29)$$

$$\psi_3(R_3) = B_{--} e^{(2r_- - k_3 R)/\rho_{--}} \quad (3-30)$$

$$\psi_4(R_4) = B_{--} e^{(2r_- - k_4 R)/\rho_{--}} \quad (3-31)$$

where  $b$  and  $\rho$  are the strength and range parmaters, respectively,  $k$  ( $i = 1 - - - - 4$ ) are the dimensionless

factors defined by Striefler and Barsch[36], (1973),  $B$  are the Pauling co-efficients (Singh and Tiwary[85], 1980) introduced to provide appropriate weighting for different ion-pair interactions and  $r_+$  and  $r_-$  are the crystalline radii of ~~cations~~ cations and anions.

xvii) RMS potential (1974):

The repulsive energy contribution to the lattice energy per ion pair in an NaCl-type crystal has been proposed by [86] as follow

$$\phi(r) = 6 B_u e^{-\alpha r} + 6 B_1 e^{-\sqrt{2}\alpha r} + 8 B_u e^{-\sqrt{3}\alpha r} + 3 B_1 e^{-2\alpha r} + 24 B_u e^{-\sqrt{5}\alpha r} \quad (3-32)$$

where interactions upto fifth neighbours are included.

The parameters  $\alpha$ ,  $B_u$ ,  $B_1$  are determined crystal by crystal data at atmospheric pressure and at temperature in the range 300 - 700 K via the Hildebrand equation of state.

One can make a comparison of the potential with the Fumi and Tosi [87] potential by performing calculations for NaCl, KCl & KBr. The comparison shows that the FT potential and RMS potential as reported gives quite comparable values for the total repulsive energy contribution to the lattice energies per ion pair a function of the nearest neighbour distance around the equilibrium value in standard thermodynamical condi-



tions, but that the RMS potential gives much smaller values than FT potential for the repulsive energy contribution due to the nearest and next nearest neighbours.

xviii) Thakur potential (1976).

For many of the previous model it is found that

$$\lim_{r \rightarrow 0} U(r) = \infty \quad (3-33)$$

and thus the potential energy curves will approach infinity in the negative energy region. The exponential repulsion terms suffer from the fundamental physical draw back that they gave a constant finite value at  $r \rightarrow 0$ . The forms of the pair potential for an LiF crystal as predicted by the models BL [1], BM [2], VS[72], & PGT[5] are shown in figure 3-1, where it is seen that, after the usual minimum at equilibrium ionic separation  $r_0$ , the curves have a minimum in the region  $r < r_0$  and tend to infinity as  $r \rightarrow 0$ . The height of the potential barrier for the BL model is about  $10^5$  kJ/mol; very much greater than for the other model.

The potential energy curves in fig. 3-1 as predicted by these models are not satisfactory. Since there must be a finite probability for penetration of ions in each direction through the potential barrier under these condition a crystal would not remain stable and could

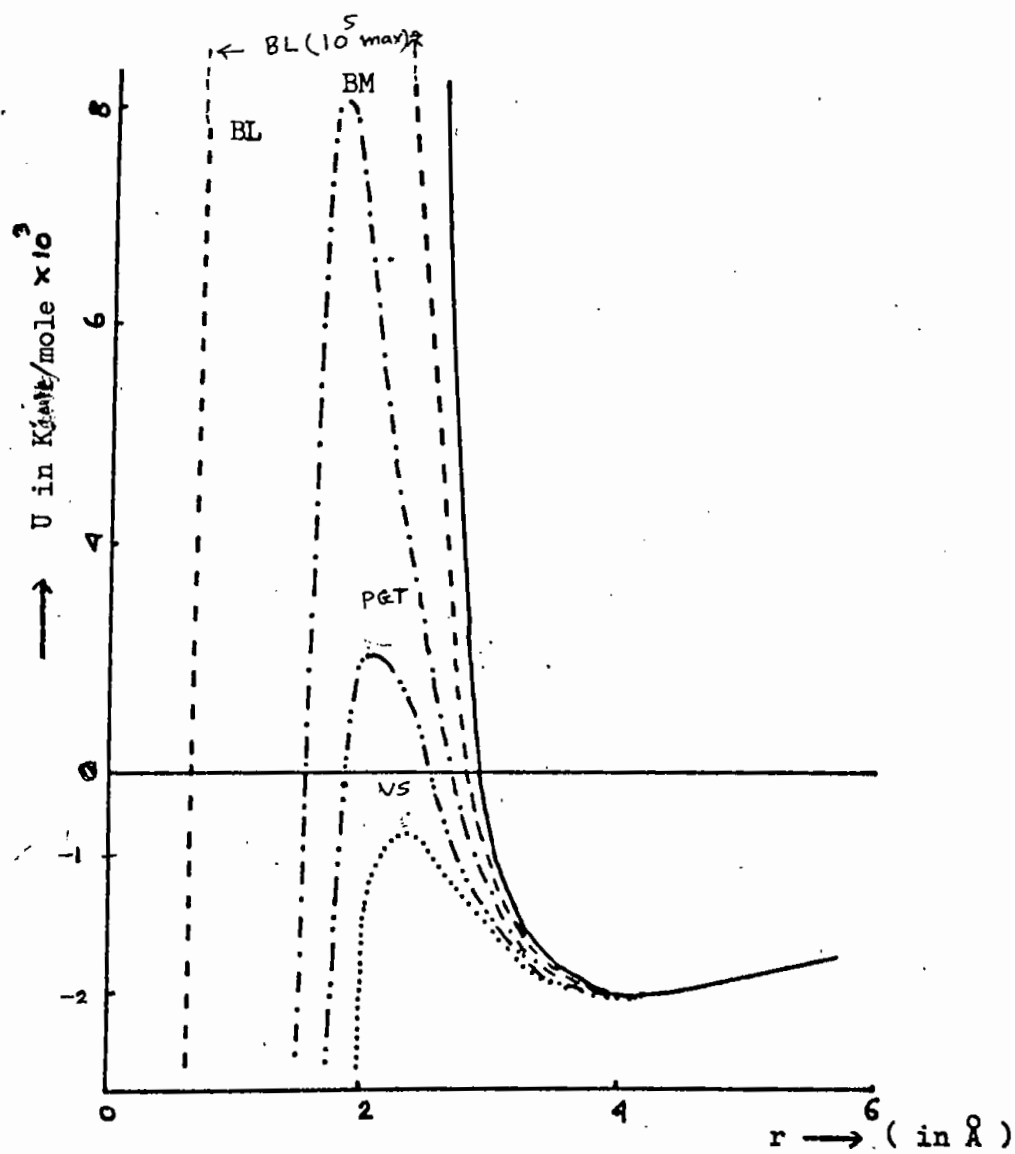


Fig. : 3-1 : Potential energy curves.

either collapse or contain heavier nuclei formed by fusion following such tunneling. There is no evidence to show that diatomic ionic crystals have these characteristics.

The force  $F(r) = - \frac{dU(r)}{dr}$  between an ion pair, as given by the models BL, BM, VS & PGT, is plotted as a function of the ionic separation  $r$  in fig. 3 - 2. Again the curves are not satisfactory since they all give  $F(r)$  zero for two values of  $r$  indicating a stable crystal for two values of ionic radius, together with the possibilities of crystals collapse and the formation of the heavier nuclei by the application of an external force equal to the height of the force curve.

For predicting the form of the potential energy curve then, from the above discussion the BL model[1] is the most successful to the previous models. However in other respects an inverse power function is not as good a representation of the repulsive term as exponential function. One argument that has been frequently advanced in support of the exponential function is that such a term is predicted by quantum mechanical calculations. Theoretical treatments of the repulsive force between closed shell anions and point cations and between inert-gas atoms have tended to support the assign-

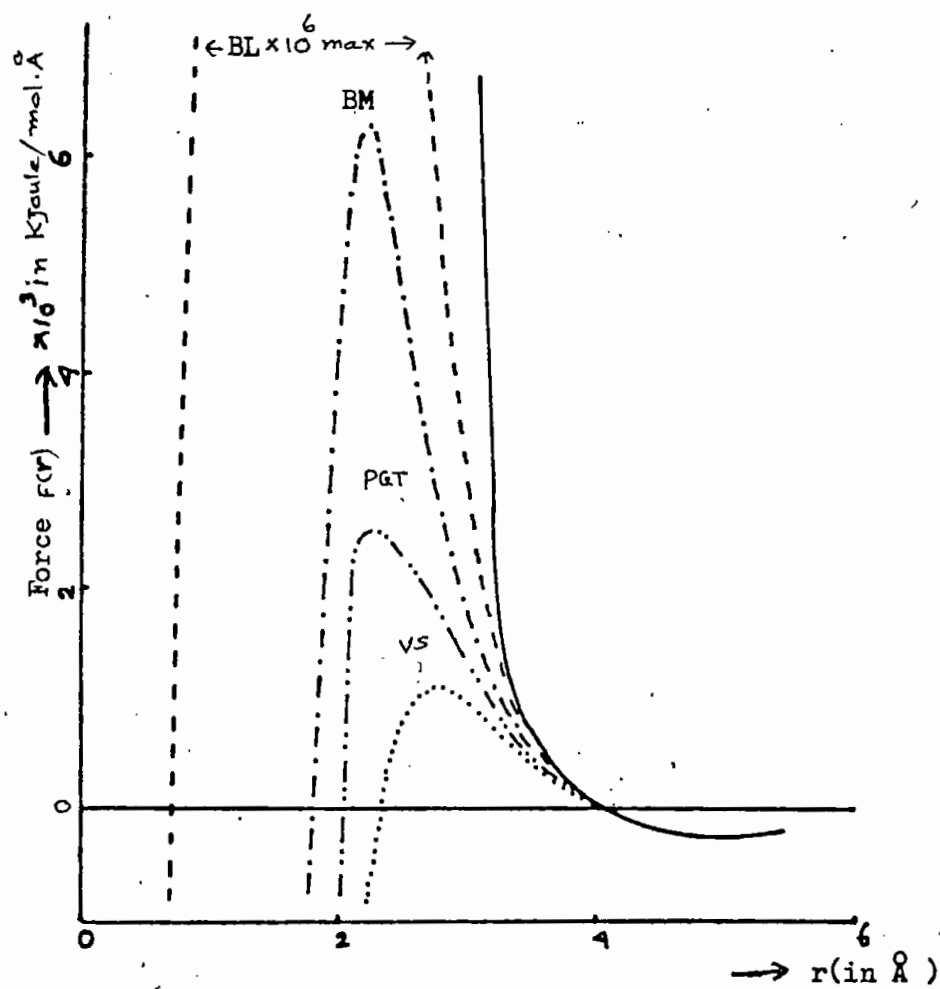


Fig. - 3-2 : Force curves (interionic force)

nment of an exponential form. However, several of the theoretical result are in serious disagreement with the experimental data. Thus the available evidence suggest that present quantum mechanical treatments cannot be applied to the representation of the binding in diatomic ionic crystals. Dobbs and Jones[58] remarks "The exponential form for the repulsive potential makes calculations of the lattice properties rather complicated and, if any case, is perhaps, not valid in the region near the minimum of the total potential which is of course the essential part in considering the properties of the lattices."

Until a complete mechanical treatment of ions in close contact is available, the overall effect of the short-range forces can only be represented by an empirical term in any model of the potential energy. However, existing models above are not entirely satisfactory and it would seem worthwhile to consider an alternative form for the repulsive potential term. It is accepted that this form will not only be adequate representation within the region  $r > r_x$ , where,  $r_x$  is the interionic distance at which the electronic shells come into contact. In accordance with Pauling principle the short-range repulsion should become infinity when the closed shell electron clouds of the anion and cation overlap

and taking account of this, the following logarithmic form[88] for the repulsive potential is proposed:

$$\phi(r) = P \log (1 + p' r^{-n}) \quad (3-34)$$

where  $P$  and  $p'$  and  $n$  are the constants. With inclusion of the terms for the other interactions, the final form for the potential energy of the ion pair is then

$$U(r) = -\frac{Ae^2}{r} - \frac{C}{r^6} - \frac{D}{r^8} - \frac{Ke^2}{r^{10}} + P \log (1 + p' r^{-n}) + \quad (3-35)$$

The last two terms of this equation may be combined to give

$$P \log (1 + p' r^{-n}) = P \log (a + p' r^{-n}) \quad (3-36)$$

where  $\epsilon = P \log a$  now represents the zero point energy and  $P = ap'$ . The model proposed by Thakur[88] is investigated for a parameter value of  $n = 6$ . The form of the present potential function is satisfactory since unlike the previous curves it has a single turning point at  $(U(r_0), r_0)$  and tends to infinity in the +ve energy domain outside region  $0 < r < r_x$ .

The previous proposed models for the potential energy function in an ionic crystal are not entirely satisfactory. In order to overcome these difficulties this new repulsive interaction has been proposed in which the interionic potential energy tends to infinity in the positive energy domain. It has been found that the new model gives a better representation of the

experimental data for the cohesive energy, the Gruneisen and Anderson - Gruneisen parameters and reststrahlen frequency than previous models, and is comparable in its predictions of the atomization energy.

The form for the potential proposed is an improvement on previous models and although far from perfect, it may help in obtaining a better understanding of the nature of the ionic bond.

xix) SKM potential (1977):

The main feature of the existing potential models which have been suggested so far is the direct functional dependence of potential energy on the interionic distance at equilibrium.

Actually the force of repulsion depends directly on the depth of overlapping of wave functions of the outer most orbits and thus it will be appropriate to assign such a form of the repulsive energy term which is function of interorbital distance.

Introducing the concept of interorbital distance instead of interionic distance for ionic crystals a new form of overlap repulsion energy was proposed by M.N.Sharma et.al[39](1977). The form of overlap repulsion[39] is as follows:

$$\phi(r) = f(\delta_1) \quad (3-37)$$

where  $f(\delta_1)$  is a function of interorbital distance.

Assuming  $\phi(R)$  to be function of  $\delta_1$ , the potential energy per unit in an ionic crystal may be expressed as

$$U(r) = -\frac{e^2}{r} + \phi(R) - \frac{C}{r^6} - \frac{D}{r^8} \quad (3-38)$$

where the notations have their usual meaning. To determine the form of the repulsive potential the values of  $\delta_1$  were determined by the following method.

For NaCl-type crystal each metal ion is surrounded by six nearest neighbour halogen ions, four of which can be taken in the same plane with the central metal ion. The distance between the centres of the two opposite halogen ions can be determined as  $2r_-\sqrt{2}$ , half of which will be equal to the distance between centres of metal and halogen ion. Thus

$$\begin{aligned} &= (r_-\sqrt{2} - (r_+ - r_-)) \\ &= (0.414 r_- - r_+) \end{aligned} \quad (3-39)$$

similarly for CsCl type crystals

$$= (0.732r_- - r_+) \quad (3-40)$$

$$\text{Thus one can obtain as : } \phi(r) = A \delta_1^n \quad (3-41)$$

where A and n are potential parameters.

This model is more suitable for predicting the behaviour of alkali halide crystals regarding infrared absorption frequency as compared to previous values by other workers. Though its performance is poorer for



fluorides among other crystals, the model shows a marked improvement in the case of fluorides as compared to the results obtained with other model. Thus the overall performances of the properties of the crystals shows a marked improvement to the previous models. The uniform behaviour of the crystal properties may be observed which was one the short-comings of the previous models.

xx) Mohammed potential (1979):

S. Noor Mohammad[42] proposed a general form for repulsive potential of the given below:

$$\phi(r) = S e^{-\eta r^m/r^n} \quad (3-42)$$

where  $S, \eta, m$  and  $n$  are the parameters of the potential. With this form for  $\phi(r)$  the total potential energy can be written:

$$U(r) = - \frac{Z_M Z_X e^2}{r} + S e^{-\eta r^m/r^n} - 0.5 e^{\frac{2(\alpha_M + \alpha_X)}{r^4}} - \frac{C}{r^6} - \frac{2 e^2}{r^2} M \alpha_X \quad (3-43)$$

In equation (3-43)  $\alpha_M$  and  $\alpha_X$  are the polarizabilities and  $Z_M$  and  $Z_X$  are the atomic weights of the  $M^+$  and  $X^-$  and  $C$  is the van der Waals constants, given by

$$C = 1.5 \frac{\alpha_M \alpha_X I_M E}{I_M + E} \quad (3-44)$$

$I_M$  is the second ionization potential of the ions and  $E$  is the electron affinity of the negative ion.

It is possible to derive this potential from a

series of empirical consideration. In order to derive the improved model we assume that the total potential energy of a system is  $E = E_1 + E_2 + E_3$ , where  $E_1$  is the combination of the exchange and Coulomb energies and  $E_1 + E_2$  arises from the polarization of charges of the ions of the system. Other contributions to  $E$  are assumed negligible. The electronic energy  $E$  depends largely on the charge density in the bond region. To determine it we then be used the charge density model of Anderson and Parr can be used. We then write

$$\nabla^2 E_1 = F_1(r) \approx 4 \pi Z_{\alpha'} \rho_{\beta'}(\alpha') = 4 \pi Z_{\beta'} \quad (3-45)$$

where  $Z_{\alpha'}$  is the atomic number of nucleus  $\alpha'$  and  $\rho_{\beta'}(\alpha')$  is the first-order electron density at nucleus due to the part of the total electron density which perfectly follows nucleus during vibration. Each first order density function  $F_1(r)$  in equation (3-45) determines a potential  $E_1(r)$  and conversely. The simplest possible assumption about  $\rho_{\beta'}(\alpha')$  may be that it is exponentially decaying and with this assumption we take  $F_1(r)$  as

$$F_1(r) = S e^{-\eta r^m / r^{n+2}} (n^2 m^2 r^{2m} - nm(m - 2n + 1)r^m + n(n - 1)) \quad (3-46)$$

in which  $\eta$ ,  $S$ ,  $m$  and  $n$  are the parameters of the function  $F_1(r)$ ; with this function we get from equation (3-45)

$$E_1(r) = -e^2/r + S e^{-\eta r^m / r^n} \quad (3-47)$$

In order to determine  $E_2$  and  $E_3$  (considering only term

which are zeroth order in overlap ) we write the interaction potential  $V$  as a multiple expansion. Using the relation due to Buckingham, one can write

$$V = \frac{1}{r} q_1 q_2 + \frac{1}{r^3} (q_1 \mu_2 - q_2 \mu_1) + \frac{1}{r^5} (q_1 \theta_2 + \frac{1}{3} q_1 \theta_1 - \dots) + \dots \quad (3-48)$$

Index 1 refers to  $M^+$  and index 2 to  $X^-$ . The quantities  $q_i, \mu_i, \theta_i$  are respectively, the monopole, dipole and quadrupole operators associated with species  $i$  ( $i = 1, 2$ ).

With this  $V$ ,  $E_2$  and  $E_3$  can be approximated as

$$E_2(r) + E_3(r) \approx -0.5 \frac{e^2 (\alpha_M \alpha_X)}{r^4} - \frac{C}{r^6} - 2 \frac{e^2 \alpha_M \alpha_X}{r^7} \quad (3-49)$$

Sum of  $E_1$ ,  $E_2$  and  $E_3$  given the potential  $U(r)$  as in equation (3-43).

Comparison to other potentials:

The average percentage errors for quantities for all the system of alkali halide series it can be stated that the new potential with variable  $m$  predicts consistently better results than the other. It has been observed that with  $m = 1.4$  and  $n = 1.75$  the proposed can also given satisfactory results. The calculated values of the spectroscopic constants are quite poor. However these values using thus new potential with variable  $m$  are better than using Rittner's potential[3]. Thus the proposed potential with variable  $m$  is more flexible and much better than the Rittner

potential[3].

Defect of the potential:

The main defect of the potential is that it is a semiempirical one and uses either the free ion polarizabilities ( $\alpha_M, \alpha_X$ ) or the crystal polarizabilities as input. Since one can use in principle only the effective polarizabilities ( $\alpha_M^{\text{eff}}, \alpha_X^{\text{eff}}$ ) viz., the polarizabilities of the ions as part of the alkali halide molecules, the use of any of these two should lead to inaccurate results. The crystal polarizabilities can not be used since they differ greatly from the effective polarizabilities. The free-ion polarizabilities can not be used because the polarizability of a positive ion  $M^+$  is increased in the coulomb field of an anion, while the polarizability of a negative ion  $X^-$ , is decreased in the coulomb field of a cation.

xxi) Islam potential (1980):

The simple Born-Mayer potential compared to other form has been fairly successful in predicting some of the properties of the ionic compounds with NaCl structure. But for bivalent metal oxides, sulphides, selenides and tellurides having NaCl structure and other ionic compounds with different structures the results seem to be less satisfactory. Similar conclusions can

also be made for other available potential, some of which are suitable for one of the crystals and not for other and vice-versa.

The available repulsive terms in their simple form thus do not describe the interaction energy properly at all distances and involving cation and anion which differ considerably in size from each other. Moreover, the lattice energy generally is larger for compounds containing atoms of higher valency than for compounds containing atoms of lower valency. It is stated that this is not fully understood by the difference in coulomb interactions and by the repulsion of simple exponential type. Thus a potential is needed which will not too be difficult to handle and at the same time it gives a simple dependence on the charge and the relative sizes of the ions and be able to account for the difference in structure type.

In view of the above considerations a modified short-range repulsive potential has been suggested by Islam[B9] in 1980 which is as follows:

$$\phi(r) = I e^{-S r^{\sigma}} \quad (3-50)$$

Where  $\sigma = Z + \frac{d}{2r_0}$  ;  $r$  and  $d$  are equilibrium ionic separation and the difference of the ionic radii,  $Z$  is largest common factor of the valencies of the cation

and anion.  $I$  and  $S$  are two parameters of the potential.

This specific form of the potential has been tested by calculating the crystals energy and the Anderson-Gruneisen parameters of the alkali halides, alkaline earth chalcogenides and titanium dioxide (rutile). The interaction potential includes the Coulomb, the two-body overlap confined to nearest neighbour and the van der Waals interactions which approximate the dipole-dipole and dipole-quadrupole attractions.

The lattice energy calculated using the Born-Mayer form showed significant deviation (average 7%), compared with either the present [89] (4.1%) or the Thakur's form [88] (4.7%). The overall prediction becomes much better with the present potential than obtained using Thakur's form. Thus the chief merit of the suggested potential lies in the fact that it leads to a good connection between the observed and the calculated results not only for simple NaCl type crystals but also for a wide variety of ionic crystals.

xxii) Harrison potential (1981):

Harrison [26] has presented a quantum mechanical treatment of the short-range repulsive energy can be written as:

$$\phi(r) = \frac{nh^2}{2m} \bar{\mu}^3 r e^{-k\bar{\mu}r} \quad (3-51)$$

where  $r$  is interionic distance,  $n$  is adjustable parameter,  $h$  planck's constant divided  $2\pi$ ,  $m$  the electron mass,  $k$  a numerical factor taken as  $5/3$  by Harrison, equal for the kinetic energy term.  $\bar{\mu}$  is an average of the quantities  $\mu_1$  and  $\mu_2$  for cations and anions respectively, such that  $\mu$  is related to the valence  $p$  state energy  $\epsilon_p$  as given below:

$$\epsilon_p = - \frac{h^2 \mu^2}{2m} \quad (3-52)$$

On the basis of (3-34) one can write the total overlap repulsion energy  $\phi(r)$  extended up to second neighbour ions as follows:

$$\begin{aligned} \phi(r) = & -\frac{6nh^2}{2m} \left( \bar{\mu}^3 r e^{-k\bar{\mu}r} + \sqrt{2} \mu_1^3 r e^{-k\sqrt{2}\mu_1 r} \right. \\ & \left. + \sqrt{2} \mu_2^3 r e^{-k\sqrt{2}\mu_2 r} \right) \end{aligned} \quad (3-53)$$

where  $r$  is the nearest neighbour distance and  $r$  is the second neighbour distance in the NaCl structure solids. The Harrison repulsive potential is represented by a quantum mechanical analytical potential form derived from the tight binding theory. According to J.Shanker and G.D. Jain[25], we have used the Born-Mayer potential for mixed crystals by taking the repulsive hardness parameter corresponding to overlap integrals. The results using Harrison's potential for mixed obtained in the study are in better agreement with experimental data obtain the corresponding values obtained from the

Born-Mayer potential for mixed crystals[25].

xxiii) Narayan-Ramaseshan potential (1982):

In the compressible ion model[90,91] a radius is associated with an ion in the direction of each of its nearest and next nearest neighbour. The ions are then pictured to be in the form of a polyhedron, whose faces are perpendicular to the interionic bonds at distances from the ions centre equal to the corresponding radii. For each bond the sum of the radii of ions is taken to be equal to the bond length and so the whole crystal is made up of space filling polyhedra. The compression energy at the face  $i$  of an ions of polyhedral shape is assumed to be of the form[90,91]:

$$\phi(r) = B/2\pi \iint e^{-r'(s)/\sigma} ds \quad (3-54)$$

where  $r'(s)$  is the distance from the centre of the cell to an area element  $ds$  on the face and the integral is over the face area.  $B$  and  $\sigma$  are the repulsion parameters for the ions under consideration. The cell face can be approximated to a circle of equal area (Narayan and Ramaseshan) and one can then write the compression energy of the  $i$ th face as:

$$\phi(r)_i = B\sigma [(r_i + \sigma) e^{-r_i/\sigma} - (l_i + \sigma) e^{-l_i/\sigma}] \quad (3-55)$$

where  $r_i$  is the distance to the  $i$ th face from the ion centre and  $l_i$  is the distance to the circumference of the corresponding circular cell face. The  $l_i$ 's depend



on the interionic distance  $r$  as well as the crystal structure. The above theory of repulsion has been rather successful in explaining the structure of the alkali halides and is a natural choice for the others studies.

In calculations on the alkaline earth chalcogenides, the repulsive energy was computed using the simplified formula  $l_i = \frac{r_i}{1 - 2/n + k(r_i/r_{av} - 1)}$ . The actual procedure of the optimising the repulsion parameters  $B$  and  $\phi$  is explained elsewhere (Narayan and Ramaseshan[46,90], 1976, 1979)

The free energy per molecule of the crystal is given by

$$U_L = - \frac{AB^2}{r} - \frac{C}{r^6} - \frac{D}{r^8} + \phi_{rep} + pv \quad (3-56)$$

where  $r$  is the nearest neighbour distance,  $p$  the pressure and volume per molecule. The Madelung constants  $A$  is known for structure of interest. The van der Waals coefficients  $C$  and  $D$  be calculated in terms of the polarizabilities of the ions and the effective numbers of participating electrons. However, it has been shown that the polarizabilities of the chalcogen ions can not be considered to be constants but must be taken to vary in the form.

(3-57)

The above theory of repulsion has been rather successful in explaining the structures of the alkali ha-

lides[45]. Detailed formula are given by Narayan & Ramaseshan for NaCl, CsCl and ZnS structures. However, the labour involved in deriving exact formula for the different  $l_i$  can become quite excessive when one deals with other lower symmetry structures and this would defeat the very purpose of the present approach which seeks to develop a simple semiempirical theory of repulsion. Instead an alternative simplified approach is presented here where  $l_i$  is computed in terms of only the co-ordination number and ionic radii.

If there are  $n$  faces symmetrically disposed at equal distance from the ion centre, the solid angle subtended by each face at the centre is  $\phi = \frac{4\pi}{n}$ . If the  $n$  faces are at different distances  $r_i$  from the centre, a weighted average distance  $r_{av}$  may be defined as

$$r_{av} = 1/n \sum_i r_i \quad \text{---} \quad (3-58)$$

If  $r_i < r_{av}$  the solid angle subtended by such a face will be greater than  $\frac{4\pi}{n}$  while the reverse will be true when  $r_i > r_{av}$ . Motivated by this one can approximately write,

$$\phi_i = 4 \left( \frac{1}{n} + \frac{K}{2} \left( 1 - \left( \frac{r_i}{r_{av}} \right) \right) \right) \quad (3-59)$$

where we  $\phi_i$  is written in a form which ensures that  $\sum_i \phi_i = 4\pi$ .  $K$  is a suitable constants which has to be determined.

It can be easily shown that equation (3-59) leads to the following relation for  $l_i$

$$l_1 = \frac{r_1}{1 - 2/n + K (r_1/r_{av})^{-1}} \quad (3-60)$$

The constants  $K=0.85$  has been found by a least squares fit to the known exact values of the  $l_1$ 's in the NaCl, CsCl, and ZnS structures.

The main advantage of the relation (3-60) is that only input required for calculation of  $l$  are the number of nearest neighbour and the corresponding radii.

Using the repulsive parameters of the chalcogen ions, one can determine the repulsion parameters for the other divalent cations. However, considering the low compressibility of the cations compared to anions, one can assume the cations to be hard spheres to a radius which can be fitted to reproduce the experimental interionic distance of the corresponding chalcogenides.

The compressible ion theory of repulsion has been applied to the alkaline earth chalcogenides using a simplified formulation of the polyhedral cell approach. The theory correctly shows that most of the crystals should occur in the NaCl structure. The repulsion parameters of the chalcogenide ions have been used to derive hard sphere radii for few divalent ions. Also the theory has been extended to the rutile and perovskite where the interionic distances and compressibilities are satisfac-

ctorily predicted. These results indicate that the theory, which is based on a purely ionic picture, is quite valid for divalent ions in crystals. However there is a mild discrepancy in the matter of relative stability of different crystals structure. The approach appears to over-estimate the stability of the NaCl structure and underestimate the binding energies of the competing ZnO and CsCl structures. The presence of the covalency might possibly explain the discrepancy.

xxiv) Satyanarayana potential (1984):

An empirical expression for the repulsion energy has been proposed for computing the lattice energies of alkaline earth chalcogenides and alkali halides in view of the short-comings of earlier forms[92] which is given by:

$$\phi(r) = Mb (e^{r/p} - 1)^{-1} \quad (3-61)$$

where M is the number of nearest neighbour, and b and p are repulsion parameters to be determined under static equilibrium conditions from crystal data. The defensibility of the present form equation (3-61) is discussed in details below. Expanding equation (3-61) in a power series one obtains,

$$\begin{aligned} \phi(r) &= M b e^{-r/p} (1 + e^{-r/p} + e^{-2r/p} + \dots) \\ &= M b e^{-r/p} \left( \sum_{n=0}^{\infty} e^{-nr/p} \right) \end{aligned} \quad (3-62)$$

Generally  $p$  is of the order of  $1/10$  of  $r$ , and hence  $r/p$  will be of the order of 10. Therefore the sum of the infinite series is a rapidly converging one, and hence, to a good approximation, the series sum can be truncated at the second term. In this approximation the expression for the repulsion energy can be written as:

$$\begin{aligned}\phi(r) &= M b e^{-r/p} (1 + e^{-r/p}) = M b e^{-r/p} + M b e^{-2r/p} \\ &= \phi_{r_1} + \phi_{r_2}\end{aligned}\quad (3-63)$$

This results in a two term expression for the repulsion energy, the first term being simple BM form. For NaCl-type crystal structure the formula for repulsion energy is

$$\phi(r) = M b e^{-r/p} + 15 A e^{-2r/p} \quad (3-64)$$

and for CsCl - type crystal structure it is

$$\phi(r) = M b e^{-r/p} + 28 A e^{-2r/p} \quad (3-65)$$

where  $A$ 's are the structure-independent constants accounting for the short-range three body interactions.

xxv) Yadav potential (1985):

Yadav[93] proposed a new repulsion term in the ionic interaction potential. The form of the potential is as follows:

$$\phi(r) = A r^{-n} e^{-r/\lambda} \quad (3-66)$$

where  $A$ ,  $n$  and  $\lambda$  are constants. He has utilized this to determine the cohesive energy of several alkali halide crystals. In going through this work some discrepancies

are found in the evaluation of the potential parameters which leads the theoretical results meaningless.

The total potential energy of the alkali halide crystals is given by:

$$U(r) = \frac{e^2 z_1 z_2 \alpha}{r} + A r^{-n} e^{-r/\lambda} \quad (3-67)$$

There are three unknown parameters namely,  $A$ ,  $n$  and  $\lambda$  which can not be obtained by solving then above equation. Varshni[94] and Varshni and Shukla[95] have used experimental vibrational energy of the crystals in computing the unknown parameters. Yadav[93] on the other hand, has introduced an arbitrary condition

$$\frac{d\phi(r)}{dv} = A r^{-3} \quad (3-68)$$

$$\text{But } \frac{d\phi(r)}{dv} = \frac{r}{-3v} \cdot \frac{d\phi(r)}{dr} \quad (3-69)$$

and the explicit form of above equation (3-66) with the help of (3-68) and (3-69)

$$\frac{d\phi(r)}{dr} = \frac{r}{-3r} \left( -\frac{e^2 z_1 z_2 \alpha}{r^2} + \frac{A}{\lambda} r^{-(n+1)} e^{-r/\lambda} \left( n + \frac{r}{\lambda} \right) \right) \quad (3-72)$$

Equation (3-66) and (3-58) are identical and a comparison of these equations shows that while the explicit form of  $\frac{d\phi(r)}{dr}$  constants all the three parameters,  $A$ ,  $n$  and  $\lambda$ , Yadav suppresses  $\lambda$  and  $n$ . He could have chosen  $\frac{d\phi(r)}{dr} = A r^{-m}$ , with  $m = 1, 2, 3, 4$  or any other interger. The equation (3-66) thus constitutes a serious restriction on the form of potential function and is not warranted by any stability condition about the

lattice. Moreover since the equation is not written at the equilibrium, it should be true for any value of  $r$ . On the other hand if the equation (3-67) were written for the equilibrium value, the right hand side of the equation should be zero. This point has been missed by Yadav[93] and in order to evaluate the model parameter he has used  $\frac{d\phi(r)}{dr} \bigg|_{r=r_0} = A r_0^{-3}$  and not zero. To prove, this is trivial but given here in order to clarify this point.

Write  $\frac{d\phi(r)}{dr} \bigg|_{r=r_0} = A r_0^{-3}$   
 Then  $\frac{d\phi}{dr} \bigg|_{r=r_0} = \frac{d\phi}{dv} \cdot \frac{dv}{dr} \bigg|_{r=r_0} = A r_0^{-3} \cdot 3Kr_0^2$  or  
 $\frac{d\phi}{dr} \bigg|_{r=r_0} = \frac{3AKr_0}{r}$   
 thus  $\frac{d^2\phi}{dr^2} \bigg|_{r=r_0} = -\frac{3AK}{r_0^2}$  and now equating  $\phi = \frac{9K}{\beta} \frac{r_0}{r}$   
 from equation (3-69) for Yadav, we have the result of Yadav[93]. Thus shows the Yadav has used  $\phi'(r) = 0$  and  $\frac{3AK}{r_0}$  at the same time to determine the model parameters which makes his theoretical results invalid.

xxvi) Potential of Buckingham type:-

In our study we would also use a short-range potential of the familiar Buckingham type

$$\phi(r) = Ae^{-r/p} - C/r^6 \quad (3-73)$$

where the constant have their usual meanings. James and Catlow [159] while studying the interionic potential derived the various interactions utilizing Shell model.

A major problem in deriving such potentials for oxide crystals is the lack of experimental data. This problem has been overcome by using the following assumptions:

i) The  $O^{2-}-O^{2-}$  interaction is taken to be the same for all crystals and the potential derived by James and Catlow is used. At equilibrium oxygen-oxygen separations this interaction is very small.

ii) Cation-cation interactions are assumed to be purely Coulombic. Since cations are generally smaller than the oxygen ion and  $O^{2-}-O^{2-}$  interaction already very small at equilibrium lattice spacings this assumption seems to be reasonable.

iii) The cation-anion interaction is considered to be of the Born-Mayer form

$$\phi = A e^{-r/p} \quad (3-74)$$

i.e. the attractive  $r^{-6}$  term is ignored. The small contribution of such terms to the short-range potential at the lattice interatomic spacing will be incorporated by small modifications of the Born-Mayer parameters.



XXVii) A new proposed form:

Many of the repulsive potentials proposed thus far suffer from some fundamental drawbacks. As  $r \rightarrow 0$ , the repulsive forms consisting of exponential term give finite values. As a result the potential energy predicted by previous models are not satisfactory and hence there must be a finite probability for ions in each direction through the potential barrier, under these conditions a crystal would not remain stable and could either collapse or contain heavier nuclei formed by fusion following such tunneling. Evidence shows that the crystals do not have these characteristics.

In fig. 3-2 the force  $f(r) = -\frac{dU(r)}{dr}$   $= 0$  for two values of  $r$ , which indicates that the crystal is stable for two values of ionic radius. Thus  $U(r)$  and hence  $\phi(r)$  is not satisfactory due to this possibilities in addition to collapse and to formation of heavier nuclei by the application of an external force equal to the height of the force curve. The electronic shells of the ions in question will have overlapped long before the interionic separation has been reduced to  $(1-2) \text{ \AA}$  the ions  $M^+(M^+)$ ,  $X^-(X^-)$  can not exist in the region and an interionic potential as such cannot be defined in such a distance.

Taking this point in consideration, we are thus encouraged to propose the modified form of the existing potential due to Islam[89] as follows:

$$\phi(r) = G/(r^n) \exp [-g (r^{\Sigma})]$$

where  $\Sigma = z+d/zr$ ,  $G$  and  $g$  are two parameters of the potential.

This form is in conformity with the Pauling principle according to which the short-range repulsion should become infinite when the closed-shell electron clouds of the anion and cation overlap.

The crystal properties were calculated using various integral values of the parameter,  $n=3$  yields better result. This specific form of the potential with the said value will be applied for calculating the crystal energy and pressure derivative of bulk modulus,  $\frac{dB}{dp}$  for rutile-type oxide crystals.

## CHAPTER 4

## VAN DER WAALS INTERACTIONS

## 4.1 Origin of van der Waals interaction:

Let us consider two atoms that are gradually brought closer to each other. As long as they remain more than an atomic diameter distance from each other the electronic charge of each atom will tend to shield its own nucleus so that in the zeroth approximation, there will be no net force between the atoms. If we consider more carefully, what happens, however we can see that there should be small residual force. This arises from the fact that the electrons move around in orbits. As a result, the potential produced by any given atom will undergo small fluctuations. This fluctuation will produce small electric fields that polarize the other atoms and create a dipole moment which we denote by  $M$ , since the force on  $M$  is,

$\vec{F} = (\vec{M} \cdot \vec{\nabla}) \vec{E}$ , where  $\vec{E}$  is the electric field and since  $\vec{M} = \vec{P}\vec{E}$ , where  $\vec{P}$  is the polarizability, one obtains,

$$\vec{F} = \vec{P} (\vec{E} \cdot \vec{\nabla}) \vec{E} \quad (4-1)$$

This small residual force is called the van der Waals force [96]. A notable feature of the van der Waals force is that they act between electrically neutral systems and between system having no electric moment, for exam-

ple, between helium atoms, charge distribution is spherically symmetric so that these atoms have no dipole, quadrupole or higher electric moment. A second important property of these forces is that they are independent of temperature[97]. If the charge distribution on the atoms were rigid, the interaction between atoms would be zero, because the electrostatic potential of a spherically symmetric distribution of electronic charge is cancelled outside a neutral atom by the electrostatic potential of the charge on the nucleus. Then the inert gas atoms could show no cohesion and could not condense, contrary to experiment. It is true that the time-average electric moments are all zero. But the electrons are in motion around the nucleus even in lowest electronic state, and at any instant of time is likely to be a non-vanishing electric dipole moment from this motion[98]. An instantaneous dipole moment of magnitude  $P_1$  on one atom produces an electric field  $E$  of magnitude  $2 P_1 / R^3$  at the center of the second atom distance  $R$  from the first atom. This field will induce an instantaneous dipole moment  $\vec{P}_2 = \alpha \vec{E} = 2\alpha P_1 / R^3$  on the second atom. Here  $\alpha$  is the electronic polarizability defined as the dipole moment per unit electric field.


van der Waals forces have two outstanding charac-

teristics:


(1) They are much weaker than the forces in chemical bonds.

(2) In many cases, they are additive and can not be saturated. That is, the van der Waals force between two atoms A and B, is not very much affected if energy of say, three neon atoms,  $Ne_a$ ,  $Ne_b$  and  $Ne_c$  in a given configuration can be calculated by adding the energy that would be obtained if only  $Ne_a$  and  $Ne_b$  were present, plus the energy of  $Ne_b$  and  $Ne_c$  by themselves, plus behaviour of chemical forces. For instance if there are no other hydrogen atoms in the vicinity, the interaction, of two hydrogen atoms,  $H_a$  and  $H_b$ , is not at all the same as the interaction that occurs when  $H_b$  is already chemically bonded to another[99] hydrogen atom  $H_c$ .

The van der Waals force is not precisely a two body force since the moment induced in an atom by a second will interact with a third but in the case of neutral atoms it may be regarded as a two-body force for large separation, when power laws mentioned are valid. In the two-body approximation, it is also central force and it is certainly of short range, so that in general the effect of any but the nearest-neighbours are negligible[100].

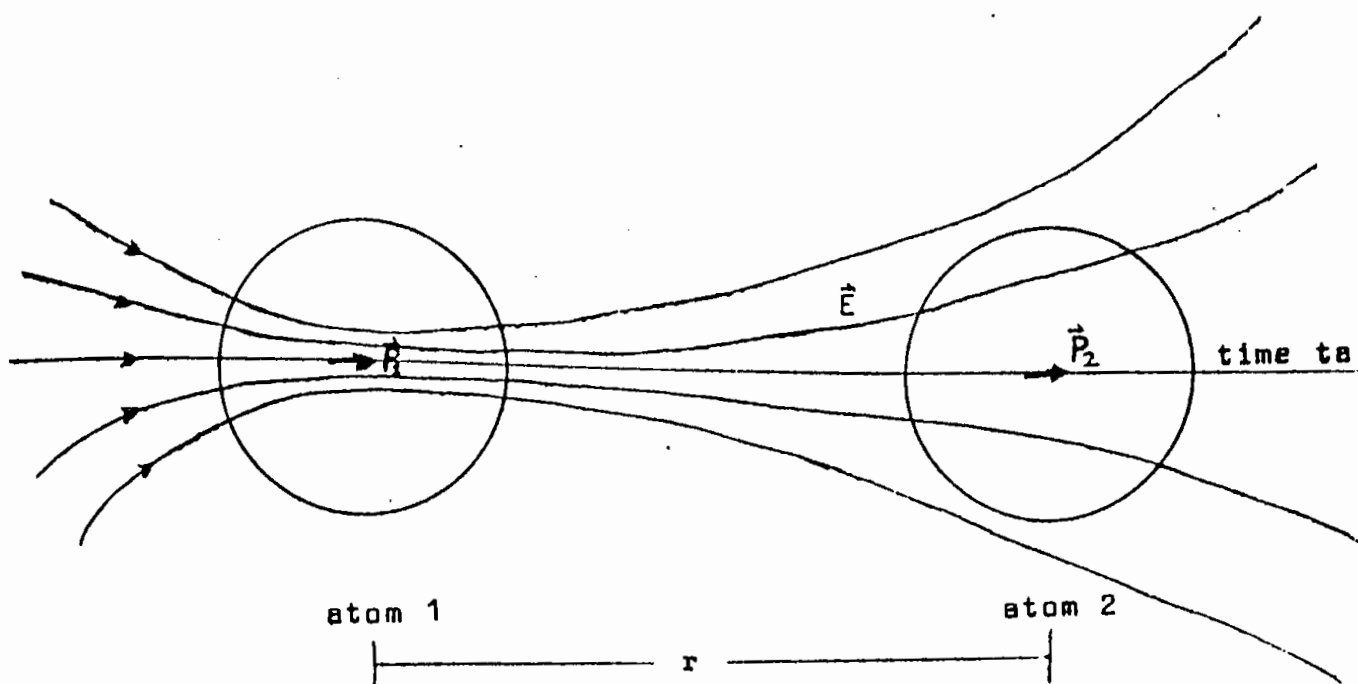

(a) Origin of the van der Waals interaction.

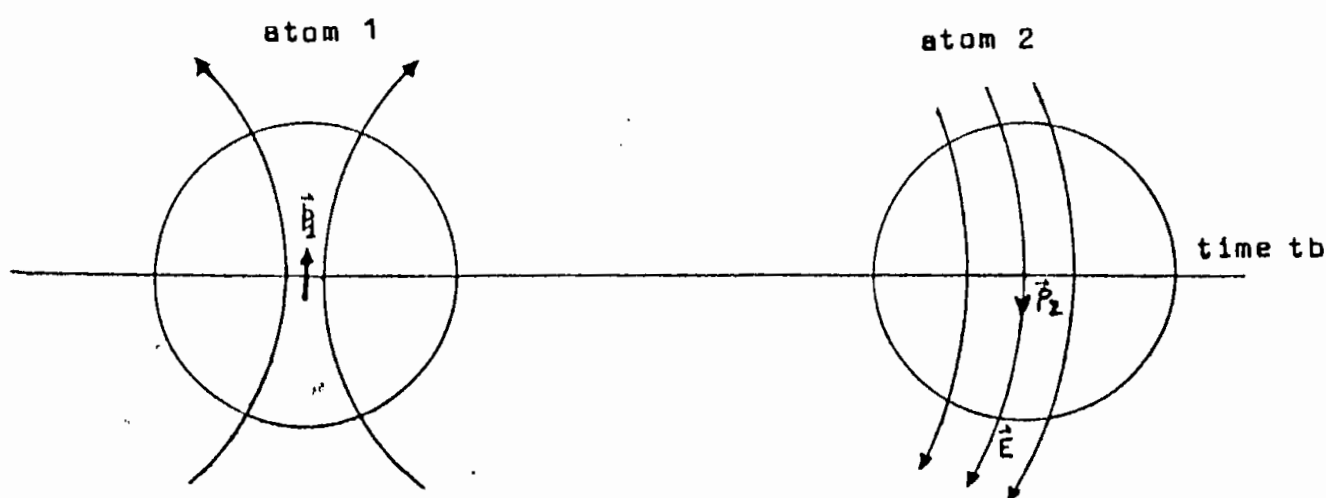

(b) At one instant of time, there is dipole moment  $P_1$  on atom 1. This produces an electric field  $E$  which acquires an induced dipole moment  $P_2$ .

Fig. 4-1 : van der Waals interaction between the two inert gas atoms.

The van der Waals potential are short range attractive between closed shell atoms or ions, having an origin connected with correlations of the electronic motions in different atoms. In the case of rare gas solid like  $\text{Ne}^5$ , the van der Waals forces are the sources of binding where their contributions to the binding energy of ionic crystals is small. However, the consideration for producing better agreement with experimental values of cohesive energies and also for studying various other properties of ionic crystals, for example, the studies on phase transformation, lattice dynamical behaviour and evaluation of defect energies require the reliable knowledge of van der Waals potential. The contributions to the van der Waals energy mainly arise from the dipole-dipole (d-d) and the dipole-quadrupole (d-q) interaction. Other higher order terms such as quadrupole-quadrupole (q-q) interaction decay more rapidly with increasing interionic separation and therefore can be neglected.

Several explanations for van der Waals forces have been proposed. In 1921 Keesom pointed out that if two molecules bear permanent electric dipole moment  $m_1$  and  $m_2$  and if they undergo thermal motion, they will on the average assume orientations leading to attractive for-

ce. If  $R$  is the vector joining the two dipoles the potential energy of a pair of dipoles is

$$\vec{V} = -\frac{1}{|R|^3} (\vec{m}_1 \cdot \vec{m}_2 - 3 \frac{(\vec{m}_1 \cdot \vec{R})(\vec{m}_2 \cdot \vec{R})}{|R|^2}) \quad (4-2)$$

Since the thermal motions are subject to the Boltzmann distribution, so that an arrangement whose energy is  $V$  has the probability  $e^{-V/KT}$ , orientations with low energy are favoured on average the quantity  $Ve^{-V/KT}$  over all orientation and assuming that  $KT \gg V$ , it is found that the average potential energy so a pair of dipoles whose separation is  $R$  is approximately

$$V = -\frac{2|m_1^2||m_2^2|}{3 KTR^6} \quad (4-3)$$

This force evidently decreases in importance as the temperature increases. It is known as the dipole orientation force, or the Keesom force. The (d-d) energy is proportional to  $-\frac{C}{r^6}$  i.e.  $U_{dd} = -\frac{C}{r^6}$  and the (d-q) energy is proportional to  $-\frac{D}{r^8}$  i.e.  $U_{dq} = -\frac{D}{r^8}$

The Van der Waals energy is mainly represented by the relation.

$$U_{vdW} = U_{dd} + U_{dq} = -\frac{C}{r^6} - \frac{D}{r^8} \quad (4-4)$$

where  $C$  and  $D$  are known as the van der Waals co-efficients and  $R$  is the interionic separation. The co-efficients  $C$  and  $D$  are linear combinations of the van der Waals co-efficients ( $c_{ij}$ ,  $d_{ij}$ ) for interactions of the various ion pairs weighted by appropriate lattice sums. In the particular case of an ionic crystal formed



by two Bravais lattice of ions one has,

$$C = c_{+-} S_{\mathbf{r}}^6(\mathbf{r}_{-}) + \frac{1}{2} (c_{++} + c_{--}) S_{\mathbf{r}}^6(0) \quad (4-5)$$

$$D = d_{+-} S_{\mathbf{r}}^8(\mathbf{r}_{-}) + 1/2 (d_{++} + d_{--}) S_{\mathbf{r}}^8(0) \quad (4-6)$$

where  $\mathbf{r}$  is position vector of the negative ion in the unit cell, the positive ion is being at the origin and the sum[102].

#### 4.2 Derivation of van der Waals co-efficients:

In this section we will consider the derivation of the van der Waals co-efficients  $c_{ij}$  and  $d_{ij}$ . The following three methods will be discussed in details for obtaining  $c_{ij}$  and  $d_{ij}$

i) London-Margenau[103,104](LM) formulation based on the perturbation treatment.

ii) Slater-Kirkwood[105] (SK) treatment based on variational theory.

fii) Kirkwood-Muller[106,107] (KM) formulation. The expression for the dipole-dipole(d-d) and dipole-quadrupole(d-q) co-efficients obtained from these theories are given below:

LM theory:

$$c_{ij} = \frac{3}{2} \alpha_i \alpha_j \frac{E_i E_j}{E_i + E_j} \quad (4-7)$$

$$d_{ij} = q/4 \frac{c_{ij}}{e^2} \left( \frac{\alpha_i \cdot E_i}{N_i} - \frac{\alpha_j \cdot E_j}{N_j} \right) \quad (4-8)$$

SK theory:

$$c_{ij} = \frac{3}{2} \frac{e\hbar}{m^2} \frac{\alpha_i \alpha_j}{(\alpha_i/N_i)^{\frac{1}{2}} + (\alpha_j/N_j)^{\frac{1}{2}}} \quad (4-9)$$

$$d_{ij} = \frac{27}{8m} \frac{\hbar^2 \alpha_i \alpha_j}{(\alpha_i/N_i)^{\frac{1}{2}} + (\alpha_j/N_j)^{\frac{1}{2}}} \quad (4-10)$$

$$\text{MK theory: } \frac{\alpha_i \alpha_j}{(\alpha_i/N_i) + 20/3(\alpha_i \alpha_j / N_i N_j)^{\frac{1}{2}} + (\alpha_j/N_j)}$$

$$c_{ij} = - \frac{6mc}{N_0} \alpha_i \alpha_j \left( \frac{\alpha_i}{\alpha_i + \chi_j/\alpha_j} \right) \quad (4-11)$$

$$d_{ij} = \frac{9 m_0}{e^2 N_0} C_{ij} \left( \chi_i/N_i + \chi_j/N_j \right) \quad (4-12)$$

where  $e$  and  $m$  are the charge and mass of an electron,  $\hbar$  is the Planck's constant divided by  $2\pi$ ,  $c$  is the velocity of light.  $E_i$  and  $N_i$  are respectively the polarizability, molar susceptibility, characteristic excitation energy and effective number of electrons in ion  $i$ . Equation (4-7) to (4-12) have been used by various workers to calculate  $c_{ij}$  and  $d_{ij}$  in alkali halide and other ionic crystals. These calculations require the knowledge of excitation energies, effective number of electrons and electronic polarizabilities of ions. There are considerable variations in the values of these quantities used in different calculations. A critical discussion along this line is presented in the following section. As far as the soundness of mathematical formulation is concerned, the KM[122,123] equation (3-11) and (4-12) has the great advantage that it does not suffer from uncertainties regarding the off-diagonal term  $Q_{kl}$  defined by Pitzer. On the other hand, the LM and SK theories neglect the contribution of these off-diagonal terms which are not without sig-

nificance. The KM formulae have been derived in such a manner that off-diagonal terms eliminated with the use of expressions for molar susceptibilities and electron polarizabilities.

#### 4.2.1 Dipole-dipole term, $c_{ij}$

(a) London formula:

The ground state wave function of the closed shell atom can be written by Slater determinant for  $N$  electrons:

$$\Psi = (N)^{-\frac{1}{2}} \det (q_1, q_2 \dots q_N) \quad (4-13)$$

To define the polarizability one can write the perturbing potential as:

$$V = F \sum_{p=1}^N Z_p \quad (4-14)$$

where  $F$  is the electric field along the  $Z$ -axis. The variational wave function  $\Psi'$  is taken to be

$$\Psi' = \Psi + \sum_{\lambda=1}^N a_{\lambda} \phi_{\lambda} \quad (4-15)$$

$$\phi_{\lambda} = (N)^{\frac{1}{2}} \det (q_1, q_2 \dots \phi_N) \quad (4-16)$$

$$= Z_{\lambda} \phi_{\lambda} f_{\lambda} \quad (4-17)$$

where  $f_{\lambda}$  is either unity or a function such as  $(1 + C_1 r + C_2 r^2)$ . The following three quantities need to be defined

as

$$h_{\lambda} = (\Psi | \sum_p Z_p | \phi_{\lambda}) \quad (4-18)$$

$$\phi_{\lambda\mu} = (\phi_{\lambda} | H | \phi_{\mu}) \quad (4-19)$$

$$q_{\lambda\mu} = (\phi_{\lambda}^* | \phi_{\mu}) \quad (4-20)$$

Here  $H$  is the complete Hamiltonian for the unperturbed

system and the usual quantum mechanical integrals over all space are indicated.

The energy change up on imposing the field is

$$h' = 2 F \sum_{\lambda} a_{\lambda} h_{\lambda} + \sum_{\lambda} \sum_{\mu} a_{\lambda} a_{\mu} \phi_{\lambda\mu} \quad (4-21)$$

which is to be minimized with respect to each  $a_{\lambda}$  i.e.

$$-\frac{dh'}{da_{\lambda}} = 0 = 2 F h_{\lambda} + 2 \sum_{\mu} a_{\mu} \phi_{\lambda\mu} \quad (4-22)$$

From the determinant theory, the solution is:  $a_{\lambda} = -\frac{h_{\lambda}}{F} \quad (4-23)$

$$\begin{aligned} \text{and the minimized energy is: } h' &= -F^2 \left( 2 \sum_{\lambda} A_{\lambda} h_{\lambda} - \sum_{\lambda} \sum_{\mu} A_{\lambda} A_{\mu} \phi_{\lambda\mu} \right) \\ &= -F^2 \sum_{\lambda} A_{\lambda} h_{\lambda} \end{aligned} \quad (4-24)$$

The expression for polarizability is:

$$\alpha = - \frac{2 h'}{F^2} = 2 \sum_{\lambda} A_{\lambda} h_{\lambda} \quad (4-25)$$

It is assumed that the  $q_{\lambda}$  are orthogonal to all  $\phi_{\lambda}$ .

This assumption is not necessarily true although the  $f_{\lambda}$  can be selected to make it true. Then

$$q_{\lambda\mu} = 0 \text{ if } \lambda \neq \mu \quad (4-26)$$

The calculation of  $Q$  is more complex. If  $f$  is unity and Hartree wave function are used  $Q_{\lambda\lambda} = 1/2$ . This value was taken as an approximation by previous workers [103,108]. The off diagonal  $Q_{\lambda\mu}$  term which have been neglected previously are not without significance.  $A_{\lambda}$  is given by:

$$A_{\lambda} = \frac{h_{\lambda}}{\sum_{\mu} Q_{\lambda\mu} h_{\mu}^2} \quad (4-27)$$

$$\text{So that } \alpha = \frac{2 \sum_{\lambda} h_{\lambda}^2}{\sum_{\lambda} Q_{\lambda\lambda}} = \frac{2 N h^2}{\sum_{\lambda} Q_{\lambda\lambda}} \quad (4-28)$$

Using the above approximations we can get the following

expression for the dipole,

$$U_{d-d} = - \frac{6}{R^6} \left( \sum_K \frac{(h_K^A)^2}{\sum_l Q_{kl}^A} \right) \left( \frac{(h_P^B)^2}{Q_{pq}^B} \right) \cdot \left( \frac{Q_{kl}^A}{Q_{kk}^A} \right) \cdot \frac{(Q_{pq}^B / Q_{pp}^B)}{\left( \frac{Q_{kl}^A}{Q_{kk}^A} \right) + \left( \frac{Q_{pq}^B}{Q_{pp}^B} \right)} \cdot E_A = \sum_l \frac{Q_{kl}^A}{Q_{kk}^A} \quad (4-29)$$

$$\frac{(Q_{pq}^B / Q_{pp}^B)}{\left( \frac{Q_{kl}^A}{Q_{kk}^A} \right) + \left( \frac{Q_{pq}^B}{Q_{pp}^B} \right)} \cdot E_A = \sum_l \frac{Q_{kl}^A}{Q_{kk}^A} \quad (4-30)$$

the equation (4-29) takes the following form

$$U_{d-d} = - \frac{3 \alpha_A \alpha_B}{2 n^6} \frac{E_A \cdot E_B}{E_A + E_B} \quad (4-31)$$

This formula was first derived by London. The main assumptions in deriving (4-17) are that

(b) (i) all  $\phi$  are orthogonal to  $\psi_\lambda$

(ii)  $f_\lambda = 1$  and (iii) off-diagonal terms  $\phi_{\lambda\mu}$  do not contribute to polarizability and dipole-dipole energy.

The assumption lead to the following results:

$$q_{\lambda\lambda} = h_\lambda = \langle \phi_\lambda^* | z_\lambda^2 | \phi_\lambda \rangle \quad (4-32)$$

so that we have;

$$\alpha_A = 2 \sum_\lambda \frac{h_\lambda^A}{E_A} = \frac{2 N h^4}{E_A} \quad (4-33)$$

From equation (4-30) and (4-33) we get,

$$E_A^{-1} = \frac{h^A}{\sum_l Q_{kl}^A} = \left( \frac{\alpha_A}{2n \sum_l Q_{kl}^A} \right) \quad (4-34)$$

Inserting (4-34) in (4-31) and assuming that off-diagonal terms do not contribute i.e.  $\sum Q = \frac{1}{2}$ , we get,

$$U_{d-d} = - \frac{3}{2} \frac{\alpha_A \alpha_B}{R^6} \left( \alpha_A / N_A^{\frac{1}{2}} + \alpha_B / N_B^{\frac{1}{2}} \right) \quad (4-35)$$

which is the SK formula for the van der Waals dipole-dipole interaction.

(c) KM formula

Another useful equation for the dipole-dipole energy is that obtained by Kirkwood[106] and Muller[107]. This

contains the diamagnetic susceptibility as well as the polarizability per atom of a spherically symmetric system is given by:

$$\alpha = - (2 m c^2)^{-1} \sum_k (z_k^2)^2 \quad (4-36)$$

In view of electronic arrangement we can for a sub-shell of equivalent electrons

$$\alpha_A = - \frac{N h^4}{2 m c^2} \quad (4-37)$$

Equations (4-36) and (4-37) imply that the assumption that the same number of electrons contribute to polarizability as to susceptibility. Such an assumption has been found to be fairly satisfactory. Thus we have,

$$E_A^{-1} = - (4 m c^2)^{-1} \left( \frac{\alpha_A}{\alpha_A} \right) \quad (4-38)$$

Then the dipole-dipole energy then becomes

$$U_{dd} = - \frac{6 m c^2}{N_0 R^6} \chi_A \chi_B \left[ \left( \frac{\chi_A}{\alpha_A} + \frac{\chi_B}{\alpha_B} \right) \right]^{-1} \quad (4-39)$$

In equation (4-39),  $N_0$  is the Avogadro's number and  $\chi$  is now the molar susceptibility in  $\text{cm}^3$ . The most remarkable feature in deriving (4-39) is that  $\sum Q$  has been eliminated. Thus the Kirkwood-Muller formula (4-39) has the great advantage that it does not suffer from the uncertainties regarding the off-diagonal term  $Q_{kl}$ .

#### 4.2.2 Dipole-quadrupole term $d_{ij}$

To derive the SK theory of the type:

$$d_{ij} = - \frac{27}{8m} h^2 \frac{\alpha_i \alpha_j \left( \left( \alpha_i / N_i \right)^{\frac{1}{2}} + \left( \alpha_j / N_j \right)^{\frac{1}{2}} \right)^2}{\left( \alpha_i / N_i \right) + 20/3 \left( \alpha_i / N_i \right) \left( \alpha_j / N_j \right) + \left( \alpha_j / N_j \right)} \quad \text{let a system have the ground state wave-function with energy } E_0$$

for the unperturbed Hamiltonian  $H$  i.e.

$$H_0 \psi_0 = E_0 \psi_0 \quad (4-40)$$

Let the perturbed Hamiltonian be  $H$  whose

$$H = H_0 + V \quad (4-41)$$

We assumed that the perturbed wave-function closely approximated be a function of the form,

$$\psi = \psi_0 (1 + V) \quad (4-42)$$

where  $V$  is small compared to unity. From the variational theorem in quantum mechanics, the excess energy of the system arising from the perturbation approximation closely reduces of the value.

$$E = \langle H \rangle - E_0 \quad (4-43)$$

$$= V_{00} + 2(VV)_{00} + \frac{\hbar^2}{2} \sum_{\text{co-ords}} \frac{1}{m_i} \left( \left( \frac{dv}{dx_i} \right)^2 \right)_{00}$$

where the summation goes over all the electrons and over the three co-ordinates for each electron.

Using the above formula, the polarizability of an atom can be derived to be

$$\alpha = 4me^2/9h^2 N(r^2_{00}) \quad (4-44)$$

From the multiple expansion of the charge distribution in two atoms we get the dipole-quadrupole interaction potential of the two atoms to be

$$V = 3/2 e^2/r^4 \sum_{ij} (r_{1i}^2 z_{2j} - z_{1i} r_{2j}^2 + (2x_{1i} x_{2j} + 2y_{1i} y_{2j} - 3 z_{1i} z_{2j} (z_{1i} - z_{2j})) \quad (4-45)$$

where the subscripts 1,2 refer to electrons in the first and second atom and  $i,j$  goes from 1 to  $N,N$  the

respective numbers of electrons participating in the interaction.

We use the first approximation in Hasse's[109] method and express  $v$  as

$$V = v = ((r_{11}^2 Z_{2j} - Z_{11} r_{2j}^2 + 2x_{11} x_{2j} + 2y_{11} y_{2j} - 3 z_{11} z_{2j}) (Z_{11} - Z_{2j})) \quad (4-46)$$

where  $\lambda$  is an undetermined multiplier.

It is determined the matrix elements in (4-43) that,

$$V_{00} = 0 \quad (4-47)$$

$$V_{00} = 0 \quad (4-48)$$

$$\text{Also } (vV)_{00} = -\frac{2e^2}{3a^4} N_1 N_2 ((r_1^4)_{00} (r_2^2)_{00} + (r_1^2)_{00} (r_2^4)_{00}) \quad (4-49)$$

From equation (4-46) we have

$$\frac{dv}{dx_{1k}} = \lambda \sum_j (2x_{1k} Z_{2j} + 2x_{2j}(Z_{1k} - Z_{2j})) \quad (4-50)$$

$$\text{i.e. } \left( \frac{dv}{dx_{1k}} \right)_{00}^2 = \lambda^2 N_2^2 (8/9 (r_1^2)_{00} (r_2^2)_{00} + 4/15 (r_2^4)_{00}) \quad (4-51)$$

Thus we obtain for the  $k$ th electron of the first atom

$$\sum_{\text{co-ords}} \left( \frac{dv}{dx_{1k}} \right)_{00}^2 = \lambda^2 N_2^2 (40/9 (r_1^2)_{00} (r_2^2)_{00} + 4/3 (r_2^4)_{00}) \quad (4-52)$$

Finally summing over all the electrons of the first atom and adding a symmetrical term for the second atom we have

$$\left( \frac{dv}{dx_1} \right)_{00}^2 = \lambda^2 N_1 N_2 (4/3 (r_1^4)_{00} + 80/9 (r_1^2)_{00} (r_2^2)_{00} + 4/3 (r_2^4)_{00}) \quad (4-53)$$

Substituting (4-54), (4-48), (4-49) and (4-43) we have the perturbation energy to be

$$E = -\frac{4e^2}{3a^4} N_1 N_2 ((r_1^4)_{00} (r_2^2)_{00} + (r_1^2)_{00} (r_2^4)_{00})$$



$$+ \frac{h}{2m} N_1 N_2 (4/3 (r_1^4)_{00} + 80/9 (r_1^2)_{00} (r_2^2)_{00} + 4/3 (r_2^4)_{00})^2 \quad (4-54)$$

The result (4-54) contains the undetermined multiplier  $\lambda$ . To eliminate it we minimize (4-54) with respect to  $\lambda$ . we then get the dipole-quadrupole interaction energy as:

$$\Delta E_{dq} = - \frac{d}{r^8} = - \frac{2 m e^4}{9 \hbar^2 r^8} N_1 N_2 \frac{((r_1^4)_{00} (r_2^2)_{00} + (r_1^2)_{00} (r_2^4)_{00})^2}{(4/3 (r_1^4)_{00} + 80/9 (r_1^2)_{00} (r_2^2)_{00} + 4/3 (r_2^4)_{00})} \quad (4-55)$$

From equation (4-44) we can express  $r^2$  in terms of the polarizability

$$\text{as: } (r^2)_{00} = \left( \frac{9 \hbar^2}{4 m e^2} \right)^{1/2} \left( \frac{\alpha}{N} \right)^{1/2} \quad (4-56)$$

We also make the approximation that

$$(r^4)_{00} = (r^2)_{00}^2 \quad (4-57)$$

which is reasonably valid whenever the electrons are distributed in a shell around the nucleus with a strong speaking of the electron density at some radius.

Substituting (4-56) and (4-57) in (4-55) we thus obtain the following formula for the dipole-quadrupole interaction co-efficient.

$$d_{12} = \frac{27 \hbar^2}{8 m} \alpha_1 \alpha_2 \frac{((\alpha_1 / N_1)^{1/2} + (\alpha_2 / N_2)^{1/2})^2}{(\alpha_1 / N_2) + 20/3 (\alpha_1 \alpha_2 / N_1 N_2) + (\alpha_2 / N_1)} \quad (4-58)$$

#### 4.3.1 Origin Of polarizability :

In order to understand the origin of polarizability of an atom let us first define dipole moment and local electric field.

The dipole moment of the pair of charge  $\pm q$  is  $\vec{P} =$

$q\vec{r}_1 - q\vec{r}_2 = q\vec{R}$ , and is directed from the negative charge toward the positive charge. The local electric field at an atom is the sum of the electric field  $E_0$  from external sources and of the field of the dipoles within the specimen, we write,

$$E_{\text{local}} = E_0 + E_1 + E_2 + E_3 \quad (4-59)$$

The contribution of the local field are as given in figure 4-2.


The polarizability of an atom is defined in terms of the local electric field at the atom:

$$P = E_{\text{local}} \quad (4-60)$$


where  $P$  is the dipole moment. The polarizability is an atomic properties, but the dielectric constants will depend on the manner in which the atoms are assembled to form crystal. The polarizability has the dimension of (Length)<sup>3</sup>. The total polarizability may be separated into three parts:

- i) Electronic,
- ii) Ionic and (iii) Dipolar,

The electronic polarizability arises from the displacement of the electronic shell relative to a nucleus. The ionic contribution comes from the displacement of a charged ion with respect to other ions. The dipolar polarizability arises from molecules with a permanent electronic dipole moment that can change orientation in


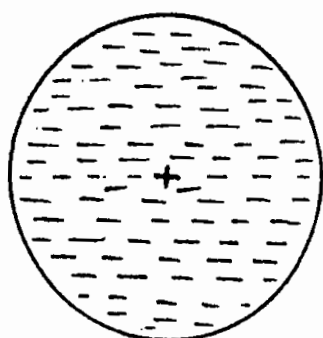


Unpolarized atom


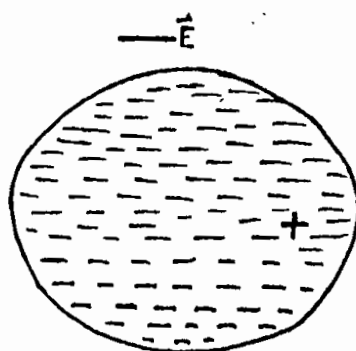


Polarized atom


Fig. 4-2 : Polarized and unpolarized atoms.

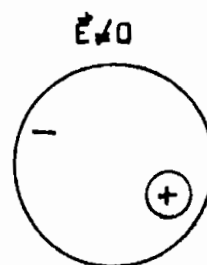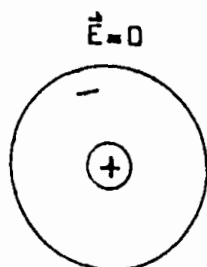

(a) Electronic

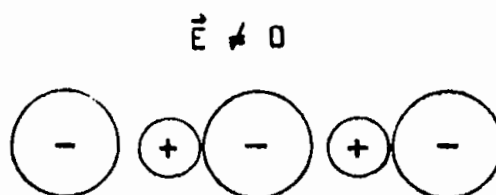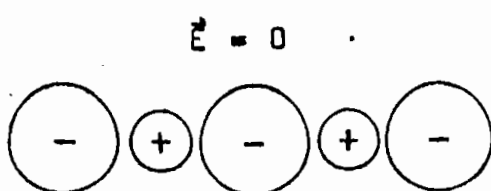

(b) Ionic

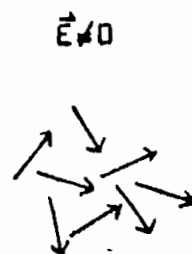

(c) Dipolar

Fig. 4-3 : Different polarizabilities.

an applied electric field. The contributions to the polarizability are as given in figure 4-2.

Let us now calculate the polarizability of an ionic crystal. The polarizability of molecules plays an important role in several of the theories of long range intermolecular forces. Accordingly we devote this section to a discussion of the calculation of polarizability. First the general quantum mechanical theory is presented and this theory is applied to the calculation of the polarizability of molecule. Then the principle of additivity of polarizability is discussed and finally the use of screening constants to calculate polarizability and other molecular properties is considered.

#### 4.3.2. Polarizability versus ion-environment:

The polarizability of an ion is sensitive to its environment. For example, the best spectroscopic value for polarizability of the lithium ion is  $0.0283 \text{ \AA}^3$  and the most recent theoretical estimation for the polarizability of the free fluoride ion are 1.56 and  $1.40 \text{ \AA}^3$ . The sum of these lies between 1.59 and  $1.43 \text{ \AA}^3$  whereas the experimental polarizability per ion pair in crystalline LiF is  $0.915 \text{ \AA}^3$ .

The existence of such effects was demonstrated in principle over 40 years ago by Spangenberg[110] who showed that the polarizability per ion-pair in crystalline alkali halides cannot be accurately described as sums of constant polarizabilities for the component ions. This is illustrated by the fact that the difference in polarizability between NaF and NaBr is  $3.24 \text{ \AA}^3$  whereas the corresponding difference in the rubidium salts is  $3.43 \text{ \AA}^3$ .

Fajans and Joos[111] proposed on the basis of quite general arguments that the polarizability of a positive ion is increased in the Coulomb field of an anion, while the polarizability of a negative ion should be decreased in the Coulomb field of a cation. In an extensive review of the information available at the time, they applied these ideas to correlate not only the polarizability of ionic component in crystals and in solution but also those of molecules composed of groups differing substantially in electronegativity. The application of these concepts to a great variety of substances has been pursued subsequently by Fajans and his collaborators in a long series of publications[112,113]. Fajans and Joos also proposed a formalism for estimating the polarizability of the free ions, both positive and negative, on the basis of two quali-

tative rules:

(1)  $\alpha^+/\alpha^0 > \alpha^0/\alpha^-$  where the subscripts positive, 0, negative refer to monoatomic cation, noble gas and anion in an isoelectronic series and (2)  $(\alpha^+/\alpha^0)_n < (\alpha^+/\alpha^0)_{n+1}$  where n is the principal quantum number of the balance shell in an isoelectronic pair. These rules together with experimental values for the polarizabilities  $\alpha_n^0$ , independent estimates of  $\alpha^+$  for the lighter cations and plausible assumptions about the trends in the inequalities in rules (1) and (2), led to estimates for the polarizabilities of the ions. These estimates were influenced also by the estimated polarizabilities[111] of the heavier anions in aqueous solution; with minor modifications, they are current to day[114]. They appear to have had a significance influence on the selection of parameters for Pauling's semi empirical calculation[115] of the polarizabilities of the free alkali halide ions.

Despite the evidence summarized above that ionic polarizabilities vary with environment, many workers have based their estimates of polarization energies and London energies in ionic system on the "Constants" or additive ionic polarizabilities assigned by Tessman, Kahn and Shockley[116]. These values were chosen to minimize the mean square deviations from

additivity in the polarizabilities of ionic crystals, but with due to consideration of independent estimates of the polarizabilities of the lighter free alkali ions, especially  $\text{Li}^+$ . Clearly the use of these additive polarizabilities must be regarded as only a first approximation. More realistic estimates of the secondary interactions in ionic systems could be made if reliable values were available for ionic polarizabilities in different environments. Indeed the values deduced by TKS for the polarizabilities of the oxide ion,  $\text{O}^{2-}$  in a number of crystals ranged from 0.9 to  $3.2 \text{ \AA}^3$ , illustrated again the existence of a substantial environmental effect.

At the level of approximation represented by the lightly successful Born-Mayer model[2] of ionic crystals, it is neutral to represent the polarizability of an ionic crystal as the sum of anionic and cationic component polarizabilities. From the point of view of the quantum mechanical description of the system, however, this procedure can not be strictly justified. The nature and validity of the quantum mechanical approximations involved in this additivity concepts have been discussed by Ruffa[117]. Making use of a well established description of the polarizabilities of an



atom or ion as proportional to a weighted mean square excitation energy, Ruffa extended his analysis to carry out what amounts to a semi-quantitative of the hypothesis of Fajans & Joos. On the basis of a somewhat intuitive estimates of the effects of the lattice interactions on the mean-square excitation energy, he confirmed their contention that the polarizability of a cation is increased by lattice interactions, whereas the polarizability of an anion is decreased even more. As Ruffa himself admits, however, some of the parameter that entered his theory could be estimated only roughly and his estimates of the magnitude of the changes in polarizability may have been too large. In addition, he based his estimates of the mean square excitation energies of the unperturbed ions on Pauling's estimates of the free ion-polarizabilities. As will be shown below, subsequent work has made available more reliable estimates for the polarizabilities of the lighter ions in the free states and has raised doubts about the accuracy of Pauling's estimates for the polarizabilities of the heavier ones.

The effect of lattice interaction on the polarizabilities of the component ions in the chlorides and fluorides of lithium, sodium & potassium has also been analyzed by Mitskevich[118] on basis of variation theo-

ry. His treatment leads to the same qualitative conclusions that the polarizabilities of the ions is increased in the crystal and that of the negative ions is decreased relative to the values that characterize the free ions.

Pentrashev, Abarenkov and Krostofel[119] have presented a model which allows for the modification of the Hartreefock distribution by the Madelung potential. The expected dilution of the cation and construction of the anion were demonstrated. The corresponding perturbations of the polarizabilities have been investigated by Ledovskaya[120]. Qualitative similar results have been obtained by Paschalis and Weis[121] using the model of an ion embedded in a hollow sphere, a sphere which carries an electric charge of the same magnitude but opposite in sign to that of the ion considered.

Wilson and Curtis have treated the variation of anion polarizabilities in the alkali halides using the model of a compressible conducting sphere. They assume that the relative decrease of the polarizability experienced by the anion is proportional to the compressive force acting upon the anion. This force was approximated by the Coulomb force. Applying their model to the alkali halides having the sodium chloride structure,

they found free anion polarizabilities that were essentially equal to the cube of the anion radii. The refractive index data did not seem to require significant enhancement of the cation polarizabilities.

Pirenne and Kartheuser[122] have obtained a set of free ion polarizabilities that is based on the presumption that crystal polarizabilities are enhanced by a dipole-dipole interaction. Some theoretical support for this position, which contradicts Fajans principle, is given by Heinrich.

An alternative approach to this problem was made earlier by Burns and Wikner[124], who calculated the polarizabilities of the fluoride ion from the approximate wave functions proposed by Yamashita[125] for the free ion and for the fluoride ion in the crystal of LiF. They obtained a polarizability of  $1.31 \text{ \AA}^3$  for the free ion but a smaller polarizability of  $1.11 \text{ \AA}^3$  for the contracted wave function, of the fluoride ion in the crystal. The model which we present below is related conceptually to the results of these calculations.

A model for the polarizability of anion in crystals:

This model can be based on the following arguments. The major contribution to the polarizabilities

of a closed shell atom or ion is made by the electrons of its highest occupied sub-shell. In the halides ions these electrons are relatively weakly bound and might therefore be expected to respond to a polarizing field rather as if they were the electrons of a conduction sphere. Classically the polarizabilities of a conducting sphere is the cube of its radius. In applying this concepts to a halide ion, it is not clear how the radius should be chosen. We shall defer consideration of that question until a later section; for the moment, we simply assume that the polarizability of an anion responds to its environment as if it were proportional to a radius cubed i.e. to a volume.

We would not expect this model to apply as well to the polarizabilities of cations and of the noble gases since the ionization potentials of these systems are much lighter than those of the halide ions. That one should not expect a proportionality between polarizability and volume in general is shown by the form of the of these well known quantum theory expressions for one electron polarizability as the square of a sum of terms of the form,

$$\langle \psi_i | r_i^2 | \psi_i \rangle \text{ and } |\langle \psi_i | r_i | \psi \rangle|^2 \quad (4-61)$$

where  $r_i$  is the radius from the nucleus to the  $i$ th electron  $\psi_i$  is the corresponding one electron wave fun-

ction. In a condensed phase we assume that an increment  $dF$  of the compressive force results in a proportionate decrease of the polarizability, similar to the decrease in effective volume. Thus we write for the  $i$ th ion

$$d\alpha_i = -K_i \alpha_i F_i \quad (4-62)$$

where  $K_i$  is the constant analogous to a compressibility. Integration yields

$$(\ln \alpha_i = \ln \alpha_i^0 - K_i F_i) \quad (4-63)$$

where  $\alpha_i^0$  is the polarizability of the free ion.

Let us approximate the lattice free energy  $U$  of a crystal as a sum of the coulomb term and a repulsive potential, we ignore for the moment the K.E. and entropy terms and the London potentials. The use of a more elaborate model will be discussed in a later section. Thus we write

$$U = - \frac{\alpha e^2}{r} + \phi(r) \quad (4-64)$$

where  $\alpha$  is the Madelung constant. At the equilibrium nearest neighbour distance,  $r_e$

$$\left( -\frac{dU}{dr} \right) = \alpha e^2/r_e^2 + \phi'(r_e) = 0 \quad (4-65)$$

Here the attractive and repulsive forces acting on the ions are in balance and we may write for the compressive force  $F(r_e)$

$$F(r_e) = -\phi'(r_e) = \alpha e^2/r_e^2 \quad (4-66)$$

Then equation for correlating ionic polarizabilities between different crystals with the same structure

because

$$\ln \alpha_i = \ln \alpha_i^0 - K_i \kappa_e^2 / r_e^2 \quad (4-67)$$

$$\text{or } \log \alpha_i = \log \alpha_i^0 - b / r_e^2 \quad (4-68)$$

we have ignored the difference between the compressive forces acting on ions of differing "size".

#### Model - 1

It was assumed that the polarizabilities of  $\text{Li}^+$  and of  $\text{Na}^+$  remain constant at their well-known vacuum values of 0.0283 and 0.148  $\text{\AA}^3$ , respectively. In each of the lithium and sodium salts the polarizability of the halide ion was obtained by subtracting the polarizability of the cation, assumed to be constant, from the polarizability per ion pair of the salt. These anion polarizabilities were extrapolated by means of equ. (4-68) to the values of  $r_e^{-2}$  for the corresponding potassium salts and the polarizability of the potassium ion was obtained for each salt by difference. The values obtained for  $\alpha(\text{K}^+)$  ranged from 0.75 to 0.84  $\text{\AA}^3$  with no obvious trend with  $r_e^{-2}$ ; it was therefore assumed that  $\alpha(\text{K}^+)$  was approximately independent of  $r_e^{-2}$ . The average value was 0.787  $\text{\AA}^3$  with an average deviation of 0.024  $\text{\AA}^3$ ; this value was used to  $\alpha(\bar{X})$  at the values of  $r_e^{-2}$  obtaining in the potassium salts. These from the lithium and sodium salts to extrapolate to  $r_e^{-2}$  for the rubidium salts. The values of  $\alpha(\text{Rb}^+)$ , obtained as before ranged

from 1.31 to 1.36, and again showed no systematic trend with  $r_2^{-2}$ ; the values obtained from fluoride and iodide salts were almost identical. The average value of  $\alpha(R_b^+)$ ,  $1.328 \text{ \AA}^3$  with an average deviation of  $0.015 \text{ \AA}^3$  was then used as before to obtain  $\alpha(Cs^+)$  in CsF. Here the value obtained was  $2.31 \text{ \AA}^3$ .

Model - II: Variable cation polarizability.

It is very likely that the polarizabilities of the alkali cations are larger in ionic crystals than in free space. The magnitude of the increase is far from certain, however, since the increase resulting from electrostatic effects is opposed by the repulsive interactions with neighbouring ions.

The approximation proposed by Ruffa for the polarizability of a cation in a crystal can be written in the form

$$\alpha_o^+ / \alpha_c^+ = (1 - 2.434 \alpha_o^{1/2} / n^{1/2} \cdot r_e)^2 \quad (4-69)$$

where  $\alpha_o^+$  is the free-ion polarizability,  $n$  is the total number of electrons in the ion, and  $r_e$  is the nearest neighbour anion-cation distance. This expression has been used to calculate cation polarizabilities in the alkali halides on the basis of the spectroscopic estimates of the free-ion polarizabilities rather than the Pauling estimates used by Ruffa. The resulting values

for  $K^+$ ,  $Rb^+$  and  $Cs^+$  though smaller than Ruffa's, appeared still to be much too large on the basis of the values obtained by difference for the polarizabilities of the anions in the crystals. Thus for example in the fluorides, the resulting value of  $\alpha(F^-)$  increased as expected from LiF to NaF but then declined through the salts of  $K^+$  and  $Rb^+$  to unreasonably low value of  $0.23 \text{ \AA}^3$ , in CsF. It therefore appeared likely that overestimates also the polarizabilities of  $Li^+$  and  $Na^+$  in their salts.

In the "bootstrap" procedure, it has been assumed that the functional form provides a reasonable approximation for interpolation or extrapolation with respect to  $r$ , but it has been used for this purpose in the following empirical form, in which  $C$  is a constant characteristic of the  $i$ th cation

$$\left( \frac{\alpha_0}{\alpha_c} \right)^{1/2} = 1 - \frac{C_i}{r_i} \quad (4-70)$$

For the range of values of  $C_i$  which has been found useful to describe the experimental data is very closely approximated by

$$\alpha_c^+ = \alpha_0^+ e^{2C_i/r_i} \quad (4-71)$$

Sum rule analysis of free ion polarizabilities:

First an analysis of the polarizability of a system of non interacting free ions will be made. Considering one of the isolated ions for the moment, its static electronic polarizability may be obtained direc-



tly from the quadratic Stark effect since at ordinary temperature the ground state of the ion is the only one having an appreciable probability of being occupied. If the electric field is in the  $x$  direction, second order perturbation theory yields for the polarizability, the results.

$$\alpha = 2e \sum_{r'} \frac{|\langle r' | x | r \rangle|^2}{E_{r'} - E_r} \quad (4-72)$$

where  $X = \sum_i x_i$ , the  $x_i$  being the  $x$  co-ordinates of the individual electrons and  $E_{r'} = E_{Y'} - E_Y$ . There is no first order contribution since for free ions  $\langle r | x | r \rangle = 0$ . Evaluation of the expression (4-72) is complicated by the fact that it requires a knowledge of the energies and wave functions of all the states of the system, which is generally not available. Consequently, it is necessary to know the wave functions as well as the specific energies of all the quantum states.

Such a means is available in this case in the form of a sum rule which was discovered independently by Thomas and from a consideration of the dispersion formula for optical frequencies from the standing point of the corresponding principle. It follows directly from the commutation relations

$$[q_i, p_j] = i\hbar \delta_{ij} \quad (4-73)$$

for the electronic co-ordinates and momenta and may be written in the following manner:

$$(8\pi^2 m / \hbar^2) \sum_r E_r \left| \langle r | x | r' \rangle \right|^2 = n \quad (4-74)$$

where  $n$  is the number of electron in the ions. Identical relations hold for

$$Y = \sum_i y_i \quad \text{and} \quad Z = \sum_i z_i$$

The use of (4-40) enables one to express (3-38) as

$$\alpha = (2e^2 / E_1^2) \sum_r E_r \left| \langle r | x | r' \rangle \right|^2 = e^2 \hbar^2 n / 4 \pi^2 m E_1^2 \quad (4-75)$$

where  $E_1$  is a parameter whose magnitude is determined by the equality of the right hand sides of (4-72) and (4-75). Because the sum rule is identical for all three co-ordinates, the polarizability is independent of the direction of the field. Moreover, it may be seen that the expression for  $\alpha$  has been reduced to a dependence upon only one unknown parameter i.e.  $\alpha \propto 1/E_1^2$ . The quantity  $E_1$  may be loosely referred to as being a mean excitation energy although this designation is not a precise one since the values of such quantities are dependent upon the sums from which they are obtained.

This fact may be illustrated by obtaining an expression for the polarizability in another way. The sum rule (4-75) may be simplified by taking advantage of the matrix sum rule,

$$\sum_r \left| \langle Y | x | r \rangle \right|^2 = \langle Y | x^2 | Y \rangle - \left| \langle Y | x | Y \rangle \right|^2 \quad (4-76)$$

to yield the following:

$$\begin{aligned} (8\pi^2 m / \hbar^2) E_1^2 \langle r | x^2 | r \rangle &= n \\ (8\pi^2 m / \hbar^2) E_1^2 \langle r | y^2 | r \rangle &= n \end{aligned} \quad (4-77)$$

$$(8\pi m/h^2) \vec{E}_2^z \langle r|z^2|r\rangle = n$$

where advantage has been made of the fact that  $\langle r|x|r\rangle = \langle r|y|r\rangle = \langle r|z|r\rangle = 0$ , and where  $\vec{E}_2^x$ ,  $\vec{E}_2^y$ ,  $\vec{E}_2^z$  are parameters whose magnitudes are determined by the equality of the left hand sides of (4-74) and (4-77).

Equations (4-77) may be simplified further by the use of the principle of spectroscopic stability. According to this principle, sums of the form  $\sum_{m,m'} |\langle nm|A_q|n'm'\rangle|^2$ , where  $m$  is a space quantization index, are independent of the axis of the quantization so that

$$\sum_{m,m'} |\langle nm|A_q|n'm'\rangle|^2 = \sum_{m,m'} |\langle nm|A_y|n'm'\rangle|^2 = \sum_{m,m'} |\langle nm|A_z|n'm'\rangle|^2$$

In this case, the result is

$$\sum_{r \neq r'} |\langle r|x|r'\rangle|^2 = \sum_{r \neq r'} |\langle r|y|r'\rangle|^2 = \sum_{r \neq r'} |\langle r|z|r'\rangle|^2$$

Consequently, equations (4-77) reduce to

$$(8\pi m/h^2) \vec{E}_2 \langle r|\{ \begin{smallmatrix} x^2 \\ y^2 \\ z^2 \end{smallmatrix} \}|r\rangle = n \quad (4-78)$$

where the  $\vec{E}_2^i$  have been replaced by  $\vec{E}_2$ . In a similar manner, one may define as  $\vec{E}_3$  given by

$$\vec{E}_3 = 2e^2 \langle r|x|r\rangle \quad (4-79)$$

So that we have as a second expression for

$$\alpha = 2e^2 n c / \vec{E}_2 \cdot \vec{E}_3 \quad (4-80)$$

where  $c = \frac{h^2}{8\pi^2 m}$ . The result is again independent of direction in agreement with (4-75). The quantities  $\vec{E}_1$ ,  $\vec{E}_2$  and  $\vec{E}_3$  which may be called the mean excitation energies of the first, second and third kinds respec-

tively, satisfy the relationship,

$$\vec{E}_1 = \vec{E}_2 \cdot \vec{E}_3 \quad (4-81)$$

Although they are not equal, one might generally expect them to be of the same order of magnitude. A specific comparison of these quantities is made by the relation

$$\frac{\alpha_1}{\alpha_2} = \left( \frac{R_1^4 n_2}{R_2^4 n_1} \right) \left( \frac{\bar{E}_2^2(1) / \bar{E}_1^2(1)}{\bar{E}_2^2(2) / \bar{E}_1^2(2)} \right) \quad (4-82)$$

A system of non-interacting free ions is electric dilute so that the effective and applied fields acting on a given ion are the same. Under these conditions, the polarizability of the system, is the sum of the ionic polarizabilities, and is equal to the total polarization divided by the applied field. If

$$X = \sum_{i=1}^N x_i = \sum_{i=1}^M x_i$$

where  $N$  is the number of electrons in the system and  $M$  is the number of ions, then

$$\begin{aligned} \alpha_s &= \sum_{i=1}^M \alpha_i = 2e^2 \sum_{i=1}^M \frac{|\langle r | x_i | r' \rangle|^2}{E_{r,r'}} \\ &= 2e^2 \sum_{i=1}^M \frac{\langle r | x_i^2 | r \rangle}{\bar{E}_{3i}} = (2e^2 / \bar{E}_{3s}) \sum_{i=1}^M \langle r | x_i^2 | r \rangle \\ &= 2e^2 C \sum_{i=1}^M (n_i / \bar{E}_{3i}^2) \end{aligned} \quad (4-83)$$

where  $\bar{E}_{3s}$  is the mean excitation energy of the third kind for the system. It is evident that

$$\bar{E}_{3s} = 2e^2 \frac{\sum_{i=1}^M \langle r | x_i^2 | r \rangle}{\sum_{i=1}^M \alpha_i} = \frac{\sum_{i=1}^M \alpha_i \bar{E}_{3i}}{\sum_{i=1}^M \alpha_i} \quad (4-84)$$

Because there is some ambiguity in the value of the mean excitation energy, it is dangerous to attempt to determine polarizabilities by estimating  $E$ 's. However, the value of (4-75) and (4-82) to our approach to the

determination of the polarizabilities of ions in crystal lies in calculating  $E$ 's directly from theoretically determined free ion values. Then given a crystalline environment in which the ions maintain their individuality to good approximation and the crystalline interaction is known to the extent that the change in the  $E$ 's from their free ions values may be estimated, values for the ionic polarizabilities may be obtained. The electronic polarizabilities of ions alkaline earth chalcogenides were obtained by Tessman et.al.[116] by performing an analysis of the crystal refraction data on the basis of the Lorentz-Lorentz relation employing the additivity rule. The electronic polarizabilities of ions in alkaline earth chalcogenides crystals obtained by Tessman et.al. may by Boswarva[68] differ from free state values (Fajans and Joos), (Pauling), being larger for cations and smaller for anions.

When the ions are transported from free state to a crystal, their polarizabilities are changed. According to Ruffa[117] one can write

$$-\frac{\alpha_c^+}{\alpha_f^+} = -\frac{E_{f+}^2}{E_{c+}^2} \quad (4-85)$$

where  $E_{c+} = E_{f+} - eV_M$ .  $\alpha_{f+}$  and  $\alpha_{c+}$  are respectively the free state and crystalline state polarizabilities of a cation.  $V_M$  is the Madelung potential,  $E_{f+}$  is the energy

parameter defined as

$$E_f^2 = \frac{e^2 \hbar^2 n}{m \alpha_{f+}} \quad (4-86)$$

where  $e$  and  $m$  are the electronic charge and mass respectively.  $n$  is the number of electrons in the ion.  $\hbar$  is the Planck's constants divided by  $2\pi$ . An equation similar to (4-85) cannot, however, be used for anions because of the excitation levels to the anion polarizabilities in the crystal which has no counterpart in free state. In addition, quantum states above the first ionization continuum contribute substantially to the free anion polarizabilities. Ruffa therefore obtained a different expression for anion polarizabilities which is as follows

$$\frac{\alpha_c^-}{\alpha_f^-} = \frac{E_{f-}^2}{E_{c-}^2} \quad (4-87)$$

where  $\alpha_{c-}$  and  $\alpha_{f-}$  are the crystalline and free state polarizabilities of anion,  $E_{f-}$  is the energy parameter analogous to  $E_{f+}$ . Crystalline state parameter  $E_{c-}$  is

$$E_{c-} = \frac{1}{4}((\Delta - e^2/R) + 3(E_{f-} + \Delta - E))$$

$$\text{where } \Delta = 2e(V_M - V_R) + E - I + Q \quad (4-88)$$

where  $R$  is the interionic separation,  $e V_R$  is the repulsive energy,  $E$  the electron affinity of anion,  $I$  the ionization potential of cation and  $Q$  is the energy of interaction between the free atoms and the crystal environment.

### 4.3.3 Methods for the calculation of polarizabilities:

#### Variational procedure of screening constant method:

The polarizability of a molecule can be approximated by Hyllerrss[126] and Hasse[109]. Let us consider an unperturbed molecule containing  $n$  electrons and nuclei for which the quantum mechanical Hamiltonian operator is  $H_0$ . The energy of the molecule in its ground state is designated by  $E_0$ . Associated with this energy is a wave function  $\psi_0$ , which satisfies the Schrodinger equation and a normalization condition:

$$H_0 \psi_0 = E_0 \psi_0 \quad (4-89)$$

$$\int \psi_0^* \psi_0 dr^n = 1 \quad (4-90)$$

when the molecule is subjected to an external disturbing influence there is a contribution to the Hamiltonian  $H_1$ , due to the perturbation effect. The total Hamiltonian for the perturbed molecule is then,

$$H = H_0 + H_1 \quad (4-91)$$

Corresponding to this Hamiltonian there is a wave function and an energy  $E$ . The perturbed wave function can be written approximately as:

$$\psi = (1 + AH) \psi_0 \quad (4-92)$$

in which  $A$  is the variational parameter. This parameter is evaluated by requiring that the approximate value of the energy:

$$E = \frac{\int \psi H \psi dr^n}{\int \psi \psi dr^n} \quad (4-93)$$

be a minimum. Substitution of the Hamiltonian given in equation (4-91) and of  $\psi$  given equation in (4-93) into this expression for the energy gives,

$$E = \frac{\int \psi_0 (H_0 + H_1) + A (H_1 H_0 + H_0 H_1 + 2 H_1^2 + A^2 (H_1 H_0 H_1 + H_1^3)) \psi_0 dr^n}{\int \psi_0 (1 + 2 A H_1 + A^2 H_1^2) \psi_0 dr^n} \quad (4-94)$$

When use is made of the properties of the unperturbed wave functions, the expression assumes the form:

$$E - E_0 = \frac{W_1 + (Q_1 + 2W_2) A + (Q_2 + W_3) A^2}{1 + 2W_1 A + W_2 A^2} \quad (4-95)$$

in which

$$W_1 = \int \psi_0 H_1 \psi_0 dr^n \quad (4-96)$$

$$W_2 = \int \psi_0 H_1^2 \psi_0 dr^n \quad (4-97)$$

$$W_3 = \int \psi_0 H_1^3 \psi_0 dr^n \quad (4-98)$$

$$Q_1 = \int \psi_0 (H_0 - E_0) H_1 \psi_0 dr^n \quad (4-99)$$

$$Q_2 = \int \psi_0 H_1 (H_0 - E_0) H_1 \psi_0 dr^n \quad (4-100)$$

When the constant  $A$  is varied so as to minimize the value of  $E$ , equation (4-95) gives the shift in the energy level due to the perturbing effect. Let us now apply this result to the special case of a molecule in an electric field. In order to study the polarizability of a neutral molecule, the perturbation is taken to be uniform electric field of intensity  $E$  in the  $x$  direction. The perturbing potential is then

$$H_1 = -e E_x \left[ -\sum_{i=1}^n x_i + \sum_{\alpha=1}^Z Z_{\alpha} x_{\alpha} \right] \quad (4-101)$$

Here  $e$  is the absolute value of the charge on an electron. The  $x_i$  and  $x_{\alpha}$  are the  $x$  co-ordinates of the electrons and nuclei, respectively, and the  $Z_{\alpha}$  are the



atomic number of the nuclei. Now the x-component of the permanent dipole moment of the undisturbed molecule is given by

$$\begin{aligned} \mu_x &= \int \psi_0 \left[ -e \left\{ \sum_{i=1}^n x_i - \sum_{\alpha=1}^Z Z_\alpha x_\alpha \right\} \right] \psi_0 d\tau^n \\ &= -e \left[ \sum_{i=1}^n \bar{x}_i - \sum_{\alpha=1}^Z Z_\alpha x_\alpha \right] \end{aligned} \quad (4-102)$$

in which a bar indicates a quantum mechanical averaging with respect to the unperturbed wave function. Since all electrons are equivalent, we can drop the subscript on  $\bar{x}_i$  and call it  $\bar{x}$ , the average x co-ordinate of an electron. Thus it may be seen that when the integral  $W_1$  defined above is evaluated for the perturbation in equation (4-101), the result may be written as:  $W_1 = -\mu_x E_x$ . The expression given in equation (4-95) or the energy shift is then,

$$E - E_0 = \frac{-\mu_x E_x + A(Q_1 + 2W_2 - 2\mu_x^2 E_x^2) + A^2(Q_2 + W_3 + W_2 \mu_x E_x)}{1 - 2A\mu_x E_x + A^2 W_2} \quad (4-103)$$

This expression for the energy shift is of the same form as equation  $E - E_0$ . Hence the evaluation of the integral  $Q_i$  and  $W_i$  enables us to calculate the coefficient of  $E_x^2$ , which is simply related to the polarizability. First we notice from the definitions of the  $W_i$  that both the  $W_3$  and  $W_2 \mu_x E_x$  are proportional to  $E_x^3$ .

Hence these terms do not contribute to the polarizability and need not be considered further here. The integral  $Q_1$  may be shown to be zero, and the other integrals in equation (4-103) may be shown to have the

following values:

$$W = \mu_x^2 E_x^2 + e^2 E_x^2 n \sqrt{(x - \bar{x})^2 + (n-1) (\overline{x_1 - \bar{x}}) (\overline{x_2 - \bar{x}})} \quad (4-104)$$

$$Q = \frac{1}{2} a_0^4 \frac{2}{x} \quad (4-105)$$

in which  $n$  is the number of the electrons in the molecule and  $a_0 = \left( \frac{\hbar^2}{me^2} \right) = 0.5292 \text{ \AA}$  is the Bohr radius. The term  $(\overline{x_1 - \bar{x}})^2$  is the mean square deviation of an electron from its average position in the  $x$  direction. The term  $(\overline{x_1 - \bar{x}}) (\overline{x_2 - \bar{x}})$  gives the average correlation between the instantaneous  $x$  co-ordinates of two different electrons. This correlation would be zero for a molecular wave function. However, for polyatomic molecules this correlation is appreciably large if the wave function is either of a chemical bond using atomic orbitals or else the wave function is of the correlated molecular orbital type.

The variational parameter  $A$  may be determined by setting  $\left( \frac{\partial E}{\partial A} \right)$  equal to zero and solving for  $A$ . In the limit of low electric field strength, it may easily be shown that  $A$  varies as  $E$  and the form,

$$A = \frac{\mu_x^2 E_x^2 - W_2}{Q_2} \quad (4.106)$$

with the result that

$$E - E_0 = \mu_x E_x - \frac{(\mu_x^2 E_x^2 - W_2)^2}{Q_2} \quad (4-107)$$

Comparison of this result with equation (4-104) and the use of the expression given in equations (4-107),

and (4-105) for  $Q_2$  and  $W_2$  yields the following formula for xx component of the polarizability.

$$\alpha_{xx} = -\frac{4n}{a_0} ((x_1 - \bar{x}) + (n-1)(x_1 - \bar{x})(x_2 - \bar{x})^2 \quad (4-108)$$

This result, which is valid for molecules is a generalization of the expression for the polarizability of atoms which was obtained by Kirkwood (106).

The polarizability of an atom is isotropic. If the wave function for an atom is approximated by an atomic orbital wave function, the second term in equation (4-108) vanishes. Further more, in an atom  $\bar{x} = 0$  and  $\bar{x}_1^2 = \bar{y}_1^2 = \bar{z}_1^2 = 1/3 \bar{r}_1^2$ . Thus equation (4-108) becomes,

$$\alpha = 4/9a_0 \sum_i n_i (\bar{r}_i^2)^2 \quad (4.109)$$

When  $n$  is the principle quantum number of an electron and  $\bar{r}_i^k$  is given by the relation

$$\bar{r}_i^k = \frac{\int_0^\infty r^{k+2} |R_i|^2 dr}{\int_0^\infty r^2 |R_i|^2 dr} = \left( -\frac{n_i}{2(z-s_i)} \right)^k \left( \frac{k}{j=1} (2n_i^* + j) \right) a_0^k \quad (4-110)$$

where  $n_i^*$  is the effective quantum number and  $(z - s_i)$  is the effective nuclear charge for various electrons in an atom.

Estimation of screening constants:

The polarizability can be estimated easily and quite accurately by means of "Screening constants" using the formulas (4-109) and (4-110). The basis for this treatment is the fact that an electron in an atom does not "feel" the presence of the nucleus completely, in as

much as the electron is screened from nucleus by the other electrons. Hence, although the charge on the nucleus is  $Ze$ , and electron in the atom acts as though it is moving in the field of a nucleus of  $(Z-S)e$ . The quantity  $S$  is called the screening constant. From the knowledge of one property of an atom it is possible to determine a set of screening constants.

We assume that each electron in the atom may be represented by a wave function of the form,

$$\begin{aligned}\psi_{n,l,m} &= R_{n^*}(r) Y_l^m(\theta, \phi) \\ R_{n^*}(r) &= r^{n^*-1} e^{-(Z-S)r/n^*}\end{aligned}\quad (4-111)$$

Hence the  $(Y_l^m)$  are the normalized spherical harmonics defined by the equation

$$Y_l^m(\theta, \phi) = i^{|m|-m} \frac{\sqrt{(2l+1)(l-|m|)!}}{\sqrt{4\pi(l+|m|)!}} P_l^m(\cos\theta) e^{im\phi}$$

where  $a_0$  is the units of the Bohr radius,  $a_0 = 0.5292 \text{ \AA}$ .

At large distance this function behaves like a hydrogen like wave function of principle quantum number  $n$  in a field of nuclear charge  $(Z-S)$ . The effective quantum number  $n^*$  and the effective nuclear charge  $(Z-S)$  for various electrons in an atom are given by the following empirical rules:

(i) If the principle quantum number of an electron is  $n$  the value of  $n^*$  is obtained from this table:

---

$n$	1	2	3	4	5	6
$n^*$	1	2	3	3.7	4	4.2

(ii) For determining  $(z-s)$ , the electron are divided into the following groups, each having a different shielding constant:

---

1s	2s	3s	3d	4s	4d	5s	5d
	2p	3p		4p		5p	

---

That is the s and p for a given  $n$  are grouped together, but the d and the f each considered separately. The groups are considered to be arranged from inside out in the order given, above, with 1s as the inner most.

(iii) The screening constant  $S$  is found for any group of electrons from the following contributions.

(a) Nothing from any shell outside the one being considered.

(b) An amount 0.35 from each other electron in the group considered (except in the 1s group where 0.30 is used instead).

(c) If the shell considered is an s or p shell, an amount of 0.85 is contributed from each electron, with total quantum number less by one; and an amount 1.00 from each electron still further in.

(d) If the shell is a d or f shell each electron in the groups closer contributes 1.00 to the screening constant.

## CHAPTER 5

## CALCULATIONS AND RESULTS

## 5.1 Derivation of repulsive constants:

In order to take account different interactions existing in rutile structure (oxide crystals), the crystal energy can be expressed in equation (2-1) of chapter 2. When two ions combine to form a stable molecule two equilibrium conditions have been established. These are presented in chapter 1. At equilibrium position, the equilibrium distance  $r_0$  is called the bond length.

It may be observed that the bond between two atoms obey Hooke's law by taking the analogy of a spring. Thus the expression for restoring force may be written as:

$$F = -K_e (r - r_0) = -K_e x \quad (5-1)$$

where  $K_e$  and  $r$  are the force constant and the inter nuclear distance respectively. Therefore the energy of a crystal is given by:

$$U(x) = U_{x=0} + K_e x^2 \quad (5-2)$$

In this case, the energy curve is parabolic. The crystal formed by the analogy of Harmonic motion is called the simple harmonic oscillation and the frequency of the oscillation is given by

$$\gamma_0 = \frac{1}{2n} \sqrt{\frac{K}{m}} \quad (5-3)$$

where  $\gamma$  is the reduced mass of the system and the energy is given by

$$U_n = (n + \frac{1}{2}) h \sqrt{\frac{K}{m}} \quad (5-4)$$

where  $n = 0, 1, 2, \dots$  etc.

For  $n = 0$ , equation (5-4) can be expressed as:

$$U_0 = \frac{1}{2} h \sqrt{\frac{K}{m}} = \frac{1}{2} h \omega = \frac{1}{2} h \gamma_0 \quad (5-5)$$

The expression (5-5) is called the zero point energy.

The vibration of molecule results in only small distortion of the bond from its equilibrium length. If  $x$  is the displacement of the bond from its equilibrium length, a Maclaurin series expansion about  $x = 0$  gives

$$U(x) = U_{x=0} + \left( \frac{dU}{dx} \right)_{x=0} + \frac{1}{2} \left( \frac{d^2U}{dx^2} \right)_{x=0} x^2 + \dots \quad (5-6)$$

At  $x = 0$ , the potential energy is a minimum and therefore,

$$\left( \frac{dU}{dx} \right)_{x=0} = 0$$

If only the next higher term in the expansion is retained, the expression valid near the equilibrium position and have the form:

$$U(x) = U_{x=0} + \frac{1}{2} \left( \frac{d^2U}{dx^2} \right)_{x=0} x^2 \quad (5-7)$$

Comparing this expression with equation (5-4) gives :

$$\left( \frac{d^2U}{dx^2} \right)_{x=0} = K_e \quad \text{or} \quad \left( \frac{d^2U}{dr^2} \right)_{r=r_0} = K_e$$

Thus the force constant is then the value of  $\frac{d^2U}{dr^2}$  near

equilibrium distance  $r = r_0$

Now the total energy expression (5-1) of a crystal is again written as:

$$U = - \frac{\alpha_M Z^2 e^2}{r} - \frac{C}{r^6} - \frac{D}{r^8} + \phi_r \quad (5-8)$$

Here zero point is neglected because it has very small contribution to the total energy.

Now equation (5-8) can be also be written as

$$U = - \frac{\alpha_M Z^2 e^2}{r} - \frac{C}{r^6} - \frac{D}{r^8} + \phi \quad (5-9)$$

$$\frac{dU}{dr} = - \frac{\alpha_M Z^2 e^2}{r^2} + \frac{6C}{r^7} + \frac{8D}{r^9} + \phi' \quad (5-10)$$

$$\frac{d^2U}{dr^2} = - \frac{2\alpha_M Z^2 e^2}{r^3} - \frac{42C}{r^8} - \frac{72D}{r^{10}} + \phi'' \quad (5-11)$$

From equation (5-10), we have,

$$r \frac{dU}{dr} = a + r \phi' \quad (5-12)$$

$$\text{where } a = \frac{\alpha_M Z^2 e^2}{r} + \frac{6C}{r^6} + \frac{8D}{r^8} \quad (5-13)$$

$$\text{and } r^2 \left( \frac{d^2U}{dr^2} \right) = b + r^2 \phi'' \quad (5-14)$$

$$\text{where } b = - \frac{2\alpha_M Z^2 e^2}{r} - \frac{42C}{r^6} - \frac{72D}{r^8}$$

$$\text{but } r_0 \left( - \frac{dU}{dr} \right)_{r=r_0} = 3TV_m \beta / K$$

$$\text{and } r_0^2 \left( - \frac{d^2U}{dr^2} \right)_{r=r_0} = - \frac{9V_m}{K}$$

Therefore (5-12) and (5-14) reduces to



$$a + r \phi' = -\frac{3TV_m \beta}{K} \quad (5-15)$$

$$\text{or } r \phi' = -\frac{3TV_m \beta}{K} - a = M$$

$$\phi' = M/r \text{ where } M = -\frac{3TV_m \beta}{K} - a \quad (5-16)$$

$$\text{and } b + r^2 \phi'' = -\frac{9V_m}{K} \quad (5-17)$$

$$\text{or } r^2 \phi'' = -\frac{9V_m}{K} - b$$

$$\text{or } r^2 \phi'' = -\frac{9V_m}{K} - b = X$$

$$\text{or } \phi'' = -\frac{X}{r^2} \text{ where } X = -\frac{9V_m}{K} - b \quad (5-18)$$

$$\frac{\phi''}{\phi'} = -\frac{X}{r^2} \cdot \frac{r}{M} = -\frac{X}{rM} \quad (5-19)$$

After solving equation (5-19) the repulsive parameters can easily be found out for different repulsive potential.

A. BL potential (1918)

The form of the repulsive potential

$$\phi = A r^{-n} \quad (5-20)$$

$$\phi' = n A r \quad (5-21)$$

$$\phi'' = + n (n+1) A r \quad (5-22)$$

$$\frac{\phi''}{\phi'} = -\frac{n(n+1) A r^{-(n+2)}}{n A r^{-(n+1)}} = -\frac{X}{rM} \quad (5-23)$$

$$\text{or } \frac{n+1}{r} = -\frac{X}{rM} \text{ or, } n+1 = -\frac{X}{M}$$

$$n = -\left(-\frac{X}{M} + 1\right) = -\frac{X}{M} - 1 \quad (5-24)$$

From equation (5-15) one can write

$$a + r \phi' = \frac{3TV_m \beta}{K}$$

$$r \phi' = \frac{3TV_m \beta}{K} - a = M \quad (5-25)$$

Substituting (5-21) in equation (5-25) it may easily write that,

$$r (-n A r^{-(n+1)}) = M$$

$$A = - \frac{M}{nr} r^{(n+1)} = - \frac{M}{n} r^n$$

$$= - \frac{M}{n} r^n \quad (5-26)$$

B. BM potential:

The form of repulsive potential as:

$$\phi = B e^{-r/\rho} \quad (5-27)$$

$$\phi' = - \frac{B}{\rho} e^{-r/\rho} \quad (5-28)$$

$$\phi'' = \frac{B}{\rho^2} e^{-r/\rho} \quad (5-29)$$

substituting equation (5-28) and (5-29) in (5-19) one can obtain,

$$- \frac{\frac{B}{\rho^2} e^{-r/\rho}}{\frac{B}{\rho} e^{-r/\rho}} = \frac{X}{rE}$$

$$\text{or } 1/ = - \frac{X}{rE}$$

$$= - \frac{Mr}{X} = - \frac{M}{X} r \quad (5-30)$$

From equation (5-15) may easily write that

$$a + r \left( - \frac{B}{\rho} e^{-r/\rho} \right) = - \frac{3TV_m \beta}{K}$$

$$\text{or, } r \frac{B}{\rho} e^{-r/\rho} = - M$$

$$\text{or, } B = - \frac{M}{r} \rho e^{-r/\rho}$$

$$B = - \frac{M}{r} \rho e^{+r/\rho} \quad (5-31)$$

C. Verwey potential:

The form of the repulsive potential as:

$$\phi = \mu r^{-12} \quad (5-32)$$

$$\phi' = - 12 \mu r^{-13} \quad (5-33)$$

$$\phi'' = - 13 \times 12 \mu r^{-14} \quad (5-34)$$

Substituting equations (5-33), (5-34) in (5-19) it can be written as:

$$- \frac{156 \mu r^{-14}}{12 \mu r^{-13}} = - \frac{X}{rM}$$

$$\text{or } 13 r^{-1} = - \frac{X}{rM}$$

$$\text{or } 12 = - \frac{X}{M} - 1 \quad (5-35)$$

From equation (5-15) one may write,

$$a + r (- 12 \mu r^{-13}) = - \frac{3TV_m \beta}{K}$$

$$\text{or, } r(- 12 \mu r^{-13}) = M$$

$$\text{or, } 12 \mu r^{-12} = - M$$

$$\text{or, } \mu = - \frac{M}{12} r^{12} \quad (5-36)$$

## D. VS potential:

The form of the repulsive potential as:

$$\phi = \lambda_1 e^{-K_1 r^2} \quad (5-37)$$

$$\phi' = - \lambda_1 K_1 2r e^{-K_1 r^2} \quad (5-38)$$

$$\phi'' = - 2 \lambda_1 K_1 e^{-K_1 r^2} + 4r \lambda_1 K_1^2 e^{-K_1 r^2} \quad (5-39)$$

Substituting equation (5-38) and (5-39) in equation (5-

19) one may obtain:

$$K_1 = - \left( \frac{X}{M} - 1 \right) / 2r^2 \quad (5-40)$$

From equation (5-15) it can be written as:

$$r(-\lambda_1 K_1 2r e^{-K_1 r^2}) = M$$

$$\text{or, } \lambda_1 = - \frac{M}{2r^2 K_1} e^{K_1 r^2} \quad (5-41)$$

## E. GT potential:

The form of the repulsive potential as:

$$\phi = \frac{p}{r} e^{-Kr^2} \quad (5-42)$$

$$\begin{aligned} \phi' &= - \frac{pK}{r} 2r e^{-Kr^2} - \frac{pe^{-Kr^2}}{r^2} \\ &= - 2 \frac{pK}{r} e^{-Kr^2} - \frac{pe^{-Kr^2}}{r^2} \\ &= - 2pK e^{-Kr^2} - \frac{pe^{-Kr^2}}{r^2} \end{aligned} \quad (5-43)$$

$$= - \frac{(2Kr^2 + 1)}{r^2} p e^{-Kr^2} \quad (5-44)$$

$$\begin{aligned} \phi'' &= -2pk. - K.2r. e^{-Kr^2} + \frac{p.K.2r e^{-Kr^2}}{r^2} \\ &\quad + \frac{2p e^{-Kr^2}}{r^3} \\ &= 2pe^{-Kr^2} (2k^2 r + \frac{-K}{r} \cdot \frac{1}{r^3}) \\ &= 2pe^{-Kr^2} (\frac{2K^2 r^4 + Kr^2 + 1}{r^3}) \end{aligned} \quad (5-45)$$

Substituting equations (5-44) and (5-45) in (5-19) one may write as:

$$\begin{aligned} &2pe^{-Kr^2} (\frac{2K^2 r^4 + Kr^2 + 1}{r^3}) \\ &\quad - \frac{pe^{-Kr^2} (2Kr^2 + 1/r^2)}{2K^2 r^4 + Kr^2 + 1} = -\frac{X}{rM} \\ \text{or, } &\frac{2K^2 r^4 + Kr^2 + 1}{r^3} \times \frac{r^2}{2Kr^2 + 1} = -\frac{X}{2rM} \\ \text{or, } &\frac{2K^2 r^4 + Kr^2 + 1}{2Kr^2 + 1} = -\frac{X}{2M} \end{aligned} \quad (5-46)$$

$$\text{Let } -\frac{X}{2M} = a.$$

Then equation (5-46) becomes,

$$\frac{2K^2 r^4 + Kr^2 + 1}{2Kr^2 + 1} = a$$

$$\text{Therefore, } 2K^2 r^4 + Kr^2 + 1 = 2Kr^2 + a$$

$$\text{or, } 2r^4 k^2 + r^2 k + 1 - 2r^2 ka - a = 0$$

$$\text{or, } 2r^4 k^2 + r^2(1-2a)K + (1-a) = 0 \quad (5-47)$$

This is the quadratic equation in K.

Therefore the solution of equation (5-47) is

$$K = \frac{-1 + 2a \pm \sqrt{-7 + 4a + 4a^2}}{4r^2} \quad (5-48)$$

From equation (5-15) one may obtain,

$$P = \frac{Mre \quad Kr^2}{(2kr^2 + 1)} \quad (5-49)$$

F. Islam potential:

The form of the potential is

$$\phi = I e^{-\lambda r^\sigma} \quad (5-50)$$

$$\text{Let } m = \lambda r^\sigma, \quad \sigma = Z + \frac{1}{Z} \frac{4r}{r_0}$$

$$\phi = I e^{-m} \quad (5-51)$$

$$\phi' = -\sigma \frac{m}{r} \phi \quad (5-52)$$

$$\phi'' = -\sigma \frac{m}{r} \phi - \sigma(\sigma - 1) \frac{m}{r^2} \phi \quad (5-53)$$

$$\frac{\sigma \frac{m}{r} \phi' - \sigma(\sigma - 1) \frac{m}{r^2} \phi}{-\sigma m/r \phi} = \frac{X}{rM}$$

$$\frac{-\sigma m/r \cdot -\sigma m/r \cdot \phi - \sigma(\sigma - 1) \frac{m}{r^2} \phi}{-\sigma m/r \phi} = \frac{X}{rM}$$

$$\text{or, } \frac{\sigma^2 m^2/r^2 \phi - \sigma(\sigma - 1) \frac{m}{r^2} \phi}{-\sigma m/r \phi} = \frac{X}{rM}$$

$$\text{or, } \frac{\sigma m/r^2 \phi (\sigma m/r - (\sigma - 1)/r)}{\sigma m/r \phi} = \frac{X}{rM}$$

$$\text{or, } \frac{\sigma m}{r} - \frac{(\sigma - 1)}{r} = -\frac{X}{rM}$$

$$\text{or, } (\sigma m - \sigma + 1) = -X/M$$

$$\text{or, } \omega(m-1) + 1 = -x/M$$

$$\text{or, } \omega(m-1) = -\frac{x}{M} - 1 = -\left(\frac{x}{M} + 1\right)$$

$$\text{or, } m-1 = -\frac{1}{\omega} \left(\frac{x}{M} + 1\right)$$

$$\text{or, } m = -\frac{1}{\omega} \left(\frac{x}{M} + 1\right) + 1 \quad (5-54)$$

$$\text{But } m = \lambda r^\omega$$

$$\therefore \lambda = -\frac{m}{r^\omega} \quad (5-55)$$

Now from equation (5-15) one may obtain,

$$a + r \left( -\omega - \frac{m}{r} \right) \phi = -\frac{3IV_m \beta}{K}$$

$$a - m\omega I e^{-m} = -\frac{3IV_m \beta}{K}$$

$$Im\omega e^{-m} = a - \frac{3IV_m \beta}{K} = -M$$

$$I = -\frac{M}{m\omega} e^m = -\frac{M}{m\omega} e^m \quad (5-56)$$

6. Proposed new potential:

The form of the potential is

$$\phi(r) = \frac{G}{r^3} e^{-\omega r} \quad (5-57)$$

$$\text{Where } \omega = Z + \frac{1}{Z} - \frac{4r}{r_0}, \quad n=3$$

$$\text{Let } m = \omega r$$

$$\phi' = - (3 + \omega m) \frac{\phi}{r} \quad (5-58)$$

$$\phi'' = (12 + 3\sigma_m - \sigma(\sigma - 4)m + \sigma^2 m^2) \frac{\phi}{r^2} \quad (5-59)$$

$$\begin{aligned} \text{and } \phi &= (-60 + 12\sigma m + 3\sigma(\sigma - 5)m - 3\sigma^2 m^2 \\ &\quad - \sigma(\sigma - 4)(\sigma - 5)m + 3(\sigma - 4)m^2 + \sigma^2(2\sigma - 5)m^2 \\ &\quad - \sigma^3 m^3) \frac{\phi}{r^3} \end{aligned} \quad (5-60)$$

By solving equation (5-57) and equation (5-58) one obtains.

$$m = \frac{(\sigma^2 - 7 + \sigma a) + (\sigma^2 - 7 + \sigma a)^2 - 4\sigma^2(4 - a)}{2\sigma^2} \quad (5-61)$$

and from equation (5-57) it can be easily written that

$$G = - \frac{H r^3 e^m}{(3 + \sigma m)} \quad (5-62)$$

H. Buckingham potential:

The form of the potential is

$$\phi(r) = A e^{-r/\rho_C} / r^6 \quad (5-63)$$

James and Catlow[159] has given the following values for the parameters appropriate for the nearest neighbour and next nearest neighbour interactions

For  $\text{TiO}_2$

$$A_{+-} = 656.7 \text{ ev}, \quad \rho_{+-} = 0.40431 \text{ \AA}, \quad C_{+-} = 0$$

$$A_{--} = 22764.3 \text{ ev}, \quad \rho_{--} = 0.1490 \text{ \AA}, \quad C_{--} = 27.063 \text{ ev \AA}^{-6}$$

For  $\text{SnO}_2$



$$A_{+-} = 1056.8 \text{ ev}, \rho_{+-} = 0.3683 \text{ \AA}, C_{+-} = 0$$

$$A_{--} = 22764.3 \text{ ev}, \rho_{--} = 0.1490 \text{ \AA}, C_{--} = 28.43 \text{ ev \AA}^6$$

## 5.2 Electronic polarizability and van der Waals constants:

### a) Electronic polarizability:

The electronic polarizability plays a very important role in several of the theories of long range intermolecular forces. Matter is made up of two kinds of charges, free and bound. Free charges can move through considerable distances, whereas bound charges such as the electrons in atoms can shift their average positions only by distances small compared to atomic dimensions, that is, by a small fraction of an angstrom. An electron in an atom maintains a stationary orbit by balancing the force of attraction towards the nucleus with centrifugal force generated by its motion. The internal electronic forces in atoms and molecules are very large compared to the forces produced by external electric fields. In a conductor a fraction of the electrons are free to move from one place to another. These free electrons distribute themselves so as to make the electric potential constant throughout the conductor. Any other distribution of free electron would have a higher energy. In an insulator the electrons are firmly attached to individual atoms, mole-

cules or ions. When such an insulator is placed in an electric field, the electrons are pulled slightly in one direction while the nuclei are pulled in the opposite direction. This relative displacement of charges in matter is referred to as polarization. When two molecules approach one another a mutual polarization takes place. This polarization of the molecules may be an important contribution to the intermolecular potential. The extent to which the polarization takes place can be obtained from a study of the electric susceptibility of the bulk substances. The detailed study of polarizability are discussed in chapter 4.3 of this thesis.

According to Pauling the free state polarizability  $\alpha_f$  of an atom or ion can be expressed in an approximate manner as follows:

$$\alpha_f = kZ \quad (5-64)$$

Where  $Z$  is the nuclear charge and  $k$  is a constant depending upon structure of the ion. Because ions and atoms of the same species have different electrical environments, the polarizability of an ion or atom varies somewhat with the substances. Thus a different set of polarizability obtained for different ion environment. The  $\alpha$ -values of  $\text{Si}^{4+}$ ,  $\text{Ti}^{4+}$ ,  $\text{Sn}^{4+}$  and  $\text{O}^{2-}$  are available in literature are shown in Table -1. TKS values

are shown in column 4 of Table -1. The free ion polarizability values are presented in column 2 of Table-1. It can be observed from Table -1 that polarizability values for some ions in a particular column or set are missing. Thus we estimated a consistent set of  $\alpha$ -values for all the ions under discussion by means of "Screening Constant" method and are shown in Table-1. The basis of this treatment is the fact that an electron in an ion does not "feel" the presence of the nucleus completely, in as much as the electron is screened from the nucleus by the other electrons.

Table - 1 : Electronic Polarizability of ions ( in  $\text{\AA}^3$  ).

Ion	Pauling <sup>a</sup>	FJ <sup>b</sup>	TKS <sup>c</sup>	Present study Set I	Set II	Effective numbers of electron
$\text{Si}^{4+}$	0.017	0.04	-	0.05	0.04	14
$\text{Ti}^{4+}$	0.185	0.24	-	0.63	0.24	19
$\text{Ge}^{4+}$	-	-	1.0	0.80	1.0	21
$\text{Sn}^{4+}$	-	-	3.4	3.64	3.4	29
$\text{O}^{2-}$	3.88	2.75	0.5 to 3.2	2.16	2.75	7

Set II : Reference No. b with missing values from reference No. c.

a. Ref. 131

b. Ref. 127

c. Ref. 132

(b) van der Waals constants.

The van der Waals constants  $C$  and  $D$  are the linear combinations of the van der Waals coefficients  $(c_{ij}, d_{ij})$  for interactions of the various ions pairs weighted by appropriate lattice sums. The detailed study for van der Waals energy, co-efficients are presented in chapter iv. Here the above studies are described very shortly. In this thesis SK treatment based on variational theory is used mainly for deriving  $(c_{ij}, d_{ij})$ . This treatment is most appropriate than others. Because in London and KM formulas have large uncertainties. Thus one expresses the van der Waals energy as in eqn.(4-4). Where the constants have their usual meaning. The calculated value of van der Waals constants are shown in Table 2.

### 5.3 Lattice sums.

The lattice sums for rutile type compounds are obtained by summing  $\sum_j \frac{1}{r_{ij}^6}$  (for S) and  $\sum_j \frac{1}{r_{ij}^8}$  (for T), where  $l_{ij}$  is the number of  $j$  ions distant  $r_{ij}$  from ion  $i$ . The lattice sums for rutile type compounds studied are listed in Table 2.

### 5.4 Effective number of electrons:

The effective number of electrons are the number of outermost electrons of the cation and

the anion. The values of  $c_{ij}$  when fitted in eqn. given below  $c_{ij} = 3/2 \cdot e h / m^2 \cdot \alpha_i \alpha_j / (\alpha_i / N_i)^{1/2} + (\alpha_j / N_j)^{1/2}$  give the effective numbers of electrons  $N_i$  or  $N_j$  which show a smooth trend of variation with atomic number  $Z$ . It has been suggested  $\rightarrow$

$\rightarrow$  by Scott and Scheraga [12] that the plot of  $N_{eff}$  vs  $Z_{eff}$  (Fig.5-1) can be used to predict the values of  $N$  for any atom or ion. Values of  $N_j$  and  $N_i$  for rutile so obtained are given in Table-1.

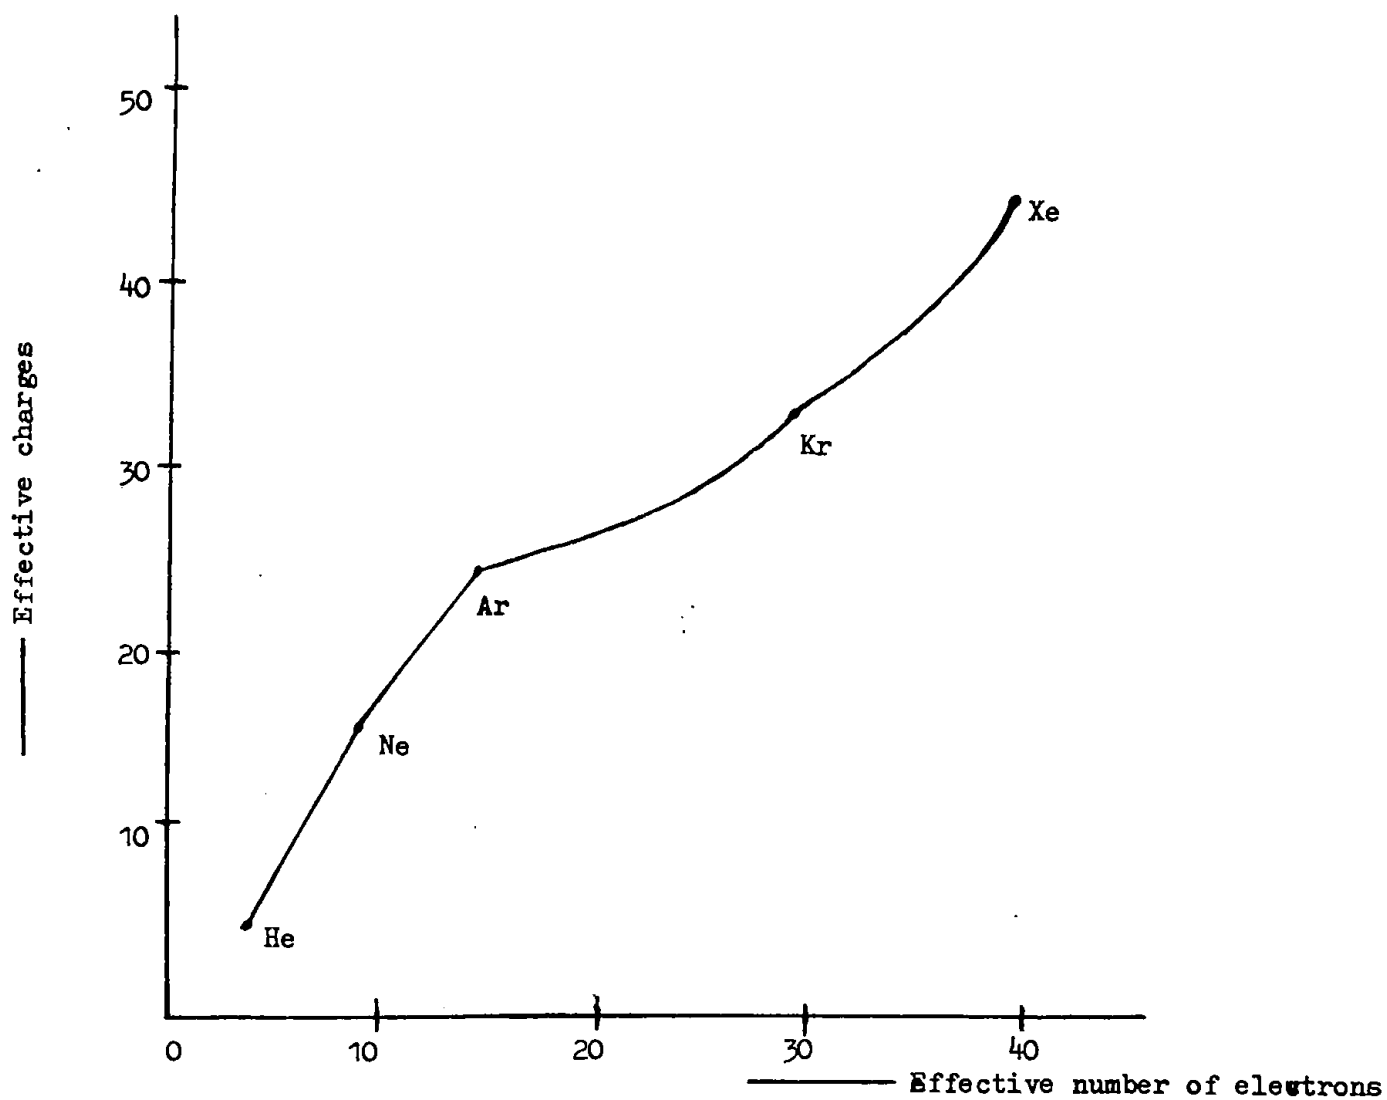


Fig. 5-1 : Plot of effective number of electrons versus effective charges.

Table - 2 : Input data

Crystal	$r_o$ (Å)	K*** ( $10^{-13}$ cm <sup>2</sup> /dy.)	$C^C$ ( $10^{-60}$ erg-cm <sup>6</sup> )	$D^D$ ( $10^{-76}$ erg-cm <sup>8</sup> )	Ionic radii (Å)**		Madelung constant (Rutile type)	
					r+	r-		
SiO <sub>2</sub>	1.757	2.78	172.80	77.64	0.506	1.251	4.77	2.212
			234.53	116.03				
TiO <sub>2</sub>	1.945	4.91	443.08	236.92	0.94	1.005	4.77	2.22
			354.24	198.23				
GeO <sub>2</sub>	1.872	3.86	523.91	283.40	0.59	1.282	4.77	2.185
			743.87	453.51				
SnO <sub>2</sub>	2.052	4.69	1729.66	1045.41	0.79	1.261	4.77	2.115
			1941.75	1283.69				

Different entries for C and D corresponding for different sets of polarizability values.

\*\* Ref. 128

\*\*\* Ref. 129

Contd.....



Contd --- Table - 2 : Input data

Crystal	Lattice sums* of four oxides						vdW - $U_{SR}$ ( Kcal/mol )
	S <sub>+-</sub>	S <sub>++</sub>	S <sub>--</sub>	T <sub>+-</sub>	T <sub>++</sub>	T <sub>--</sub>	
6							
SiO <sub>2</sub>	5.963	0.362	1.382	5.646	0.128	0.671	96.90 133.20
TiO <sub>2</sub>	6.097	0.371	1.412	5.794	0.131	0.688	134.51 108.16
GeO <sub>2</sub>	6.165	0.375	1.425	5.841	0.132	0.694	202.36 291.20
SnO <sub>2</sub>	6.383	0.389	1.487	6.131	0.139	0.729	331.52 433.34

\* Ref. 127

### 5.5 Repulsive parameters and energy:

The repulsive parameters and energies calculated under study, have been shown in table 3 and in table 4. Different repulsive forms have been used for calculating the parameters and energies.

Table - 3 : Values of repulsive parameters.

Crystal	Polariza- bility set	B - L		B - M		Vergey $r^{-12}$ ( $10^{-12}$ erg)	V - S	
		n	$\epsilon_{ar}^{-n}$ ( $10^{-12}$ erg)	( $10^{-8}$ cm)	B ( $10^{-12}$ erg)		$r_1$ ( $10^{-12}$ cm)	$r_1 e^{-K_1 r_1^2}$ ( $10^{-12}$ erg)
SiO <sub>2</sub>	I	4.34	67.42	1142.96	329	24.38	1098.96	46.15
	II	4.45	69.37	1315.96	322	25.72	1202.66	47.86
TiO <sub>2</sub>	I	4.12	68.69	928.96	380	23.61	988.66	46.25
	II	4.04	67.41	829.91	386	22.66	920.98	45.06
GeO <sub>2</sub>	I	4.45	72.61	1381.70	343	26.93	1260.95	50.10
	II	4.67	77.71	1856.75	330	30.24	1527.84	54.41
SnO <sub>2</sub>	I	5.13	74.18	2836.29	335	31.68	1880.46	53.35
	II	5.21	77.47	3217.94	331	33.60	2053.32	55.97

Contd.....

Contd... Table - 3 : Values of repulsive parameters

Crystal	G - T			Islam		Buckingham		M. Islam	
	$P(10^{-20})$	$K_2(10^{16})$	$P/r^2 e^{-K_2 r^2} (10^{-12} \text{ erg})$	$I(10^{-22} \text{ erg})$	$mc = r^-$	$\phi(r) = Ae^{-r/}$	$-C/r^6 (10^{-12} \text{ erg})$	$mc_1 = gr^-$	G
SiO <sub>2</sub>	1046.49	0.80	48.71	868.71	2.96	-	-	1.04	847.14
	1146.58	0.83	50.41	940.85	3.01	-	-	1.10	927.26
TiO <sub>2</sub>	1039.74	0.63	49.03	777.99	2.86	8.25	-	0.91	1030.62
	967.60	0.62	47.86	727.58	2.82	-	-	0.85	959.58
GeO <sub>2</sub>	1280.88	0.73	52.77	1015.47	3.04	-	-	1.11	1187.04
	1555.58	0.76	58.00	1220.17	3.14	-	-	1.24	1439.49
SnO <sub>2</sub>	2108.38	0.69	55.64	1610.95	3.42	6.26	-	1.52	2420.52
	2303.98	0.70	58.31	1755.52	3.46	-	-	1.57	2643.84

Table - 4      Different types of repulsive energies.

Crystal	Polarizability set	Calculated repulsive energy in Kcal/mol							
		B - L	B - M	Verwey	V - S	G - T	Islam	Buckingham	M. Islam
SiO <sub>2</sub>	I	970.80	789.02	351.14	664.57	701.40	643.07	-	794.96
	II	998.97	815.61	370.30	689.12	725.90	667.19	-	816.77
TiO <sub>2</sub>	I	989.26	796.20	339.98	666.19	706.10	643.08	118.97	813.28
	II	970.66	777.86	326.35	648.96	689.55	626.14	-	800.27
GeO <sub>2</sub>	I	1045.64	853.82	387.86	721.47	759.93	701.37	-	857.37
	II	1118.95	921.62	435.48	783.45	822.24	762.31	-	915.77
SnO <sub>2</sub>	I	1068.14	893.74	456.15	768.30	801.22	756.14	90.19	880.10
	II	1115.61	935.81	483.89	805.93	839.63	793.32	-	919.51

## 5.6 Output results:

### 5.6.1

#### Lattice energy:

The lattice energies for rutile-type oxide crystals have been calculated using the expression (5-9) of this chapter.

The results of the calculations using two different sets of electronic polarizability as well as seven different forms (A-G) for the repulsive interactions are presented in Table 5. This 5 also contains experimental values of the lattice energy for comparison.

### 5.6.2

#### Pressure derivative of Bulk moduli:

The potential represented by (5-9) has also been used to calculate the pressure derivative of Bulk moduli,  $\frac{dB}{dp}$ . The results of the calculations obtained for  $\frac{dB}{dp}$  are listed in Table 6 with available experimental values for comparison.

Table - 5 : Lattice energies of four Rutile-type oxides.  
( $\text{SiO}_2$ ,  $\text{TiO}_2$ ,  $\text{GeO}_2$ ,  $\text{SnO}_2$ )

Crystal	Polariza- bility set	- U ( Kcal/mol.) Calculated								-U(Kcal/mol) Experimental
		B - L	B - M	Verwey	V - S	G - T	Islam	Bucking ham	M. Islam	
$\text{SiO}_2$	I	2733.73	2915.51	3353.39	3039.95	3003.22	3061.45	-	2909.56	3166 <sup>a</sup>
	II	2741.85	2925.21	3370.52	3051.70	3014.92	3073.63	-	2924.65	
$\text{TiO}_2$	I	2404.16	2579.22	3053.44	2727.24	2697.33	2750.34	3139.89	2580.14	2858 <sup>a</sup> , 2873 <sup>c</sup>
	II	2396.41	2589.21	3040.72	2718.11	2677.92	2740.94	-	2566.81	2900 <sup>d</sup> , 2930 <sup>e</sup>
$\text{GeO}_2$	I	2542.72	2734.54	3200.50	2866.89	2828.43	2886.99	-	2730.99	3037 <sup>a</sup> , 3050 <sup>d</sup>
	II	2559.25	2756.58	3242.72	2894.75	2855.96	2915.87	-	2762.43	3090 <sup>e</sup>
$\text{SnO}_2$	I	2402.36	2576.76	3014.34	2702.20	2669.28	2714.35	2998.88	2790.34	2783 <sup>a</sup> , 2924 <sup>d</sup>
	II	2406.7	2586.51	3038.44	2716.39	2682.69	2729.00	-	2602.80	2838 <sup>e</sup>

a Ref. 127

c Ref. 129

d Ref. 130

e Ref. 131

Table - 6 : Pressure Derivative of Bulk Modulus

Crystal	Polariza- bility set	dB/dp								Experimental dB/dp
		B - L	B - M	Verwey	V - S	G - T	Islam	Bucking ham	M. Islam	
SiO <sub>2</sub>	I	3.57	2.88	6.47	1.52	1.51	1.70	-	3.07	7.00 <sup>f</sup>
	II	3.54	2.79	6.52	1.43	1.44	1.53	-	2.97	-
TiO <sub>2</sub>	I	3.30	2.46	6.54	1.14	1.28	0.98	-	2.76	6.76 <sup>g</sup>
	II	3.33	2.54	6.51	1.22	1.23	1.14	1.56	2.86	-
SnO <sub>2</sub>	I	3.33	2.42	6.62	1.09	1.23	0.91	-	2.64	6.16 <sup>g</sup>
	II	3.24	2.18	6.71	0.88	1.09	0.44	-	2.36	-
SnO <sub>2</sub>	I	3.49	2.36	6.83	0.93	1.11	0.66	-	2.44	5.13 <sup>g</sup>
	II	3.46	2.24	6.88	0.83	1.06	0.43	1.30	2.30	-

f Ref. 132

g Ref. 133



## CHAPTER 6

## DISCUSSIONS AND CONCLUSIONS

Wackman et.al.[129] discussed the effect of polarizabilities on energy values for  $\text{TiO}_2$  because these are not known exactly. They found that binding energy changes by more than 10%. When one set of values is replaced by those obtained by Ruffa's method[134]. In view of this extreme situation with Ruffa's polarizability values Wackman et.al.[129] considered that these values of ions are incorrect. Thus the part played by polarizability is apparent. The values of  $\text{Si}^{4+}$ ,  $\text{Ti}^{4+}$ ,  $\text{Sn}^{4+}$  and  $\text{O}^{2-}$  available in the literature [111,115,116,129] are shown in Table 1. TKS values [116] of simple additivity in oxide crystal leads to an appreciable spread of the values of polarizability. As suggested by TKS [116] this would result from a departure from the ideal ionic crystal state and an overlapping and distortion of the ionic wave function. TKS [116] values give an approximate measure of various ions in crystals rather than of "free" ions. On the other hand, the polarizability values in column 2 are those for free ions. The experimental work suggests a significant dependence of the values on the environment. The crystalline environment significantly reduces

the polarizability of the anions and increase the polarizability values of the cations.

The value for  $\alpha(\text{Si}^{4+})$  derived by us is consistent with the value of  $0.04 \times 10^{-3} \text{ nm}^3$  obtained by Born and Heisenberg[137], an analysis of the Rydberg Ritz correction for a spectral series. From the indices of refraction of salts in aqueous solution, Fajan and Joos [127] also obtained the same value but Schmidt et.al. [154] reported its value to be  $0.51 \times 10^{-3} \text{ nm}^3$  and  $0.66 \times 10^{-3} \text{ nm}^3$ . The first one refers to the result when the influence of both the environment in the crystal and self consistency is not included. In their study the effect of the crystal environment is incorporated by the Watson-sphere model, while consistency effects are included by a procedure adopted from many body perturbation theory. The polarizability values of both  $\text{Ge}^{4+}$  and  $\text{Sn}^{4+}$  are found to be consistent with the TKS values  $\alpha(\text{O}^{2-})$  is consistent with the crystal have values by Bisarya and Shanker [155].

Table 1 shows different sets of polarizability values, including free ion sets and the choice of values is not necessarily clear-cut. It was thus thought to be of interest to see how sensitive the results were to the specific choice of polarizability

and so a range of polarizability values with reasonable physical justification will be considered. The use of different sets of values affects constants and hence other calculations. There is no direct method which can yield experimental values of vdW energy in ionic crystal. It has been indicated by many authors that the London formulae involved excitation energies of ions which are subject to large uncertainties and these seriously underestimate the actual vdW interactions. Thus the vdW Co-efficients  $c_{ij}$  and  $d_{ij}$  are estimated using SKV approach to obtain an increased vdW bonding effect.

The estimated values (set I) are used to calculate the values of C and D based on variational method. The values of vdW energies calculated by Ladd [127] and by Shaker and Jain [128] vary between 40 to 50 and 50 to 100 Kcal/mol., respectively for the compounds under discussion. The results are much smaller than those obtained from present calculations.

The repulsive energy contributions to the total energy for various crystals <sup>have</sup> been shown in the six columns of Table 4. Eight short-range repulsive interactions are considered. It is observed that the repulsive potential energy increases with the increase

of vdW energy. The contribution of the second neighbour repulsion is small. For this reason we have not included the contribution of the second neighbour interaction in the repulsive energy calculations, except for one case as mentioned earlier.

As shown in table 5 for any particular repulsive potential form the values of the lattice energies are seen to vary from one set of polarizability values to another. However the variation is small. For a particular set of polarizability values, the lattice energy vary appreciably when different repulsive potentials are used. The lattice energy using Born-Landé form with set I polarizability is lower than on the average experimental values by 14.86%, but in case of Born-Mayer, Islam, Modified Islam and Buckingham potential forms the discrepancy is 3.50%-9%. In the case of Verwey, Varshni-Shukla, Gohel-Trivedi forms the corresponding values differ from experimental values by amount of -6.60% 4.25%, and 5.52% respectively.

In the light of the above calculated results it is seen that although the calculated values are not in exact agreement with the experimental values the deviations or discrepancies are not much except Verwey and Buckingham potential. This situation reveals that the

ionic character of these crystals are nearly correct.

Earlier investigations [73,129] assumed the short-range parameters to be equal i.e.  $\rho_{+-} = \rho_{-+} = \rho_{++} = \rho_{--}$ . In an attempt to remedy this deficiency Shanker and Jain [128] used a more general short-range repulsive interaction but could not determine  $\rho_{+-}$  because of the lack of  $\rho_{+-}$  values for tetravalent positive ions. They chose  $\rho_{+-} = 0.0345 \text{ nm}^3$  for all oxide crystals. This model which assumes a full ionic charge including a vdW energy term, and the resulting dB/dp values were found to be not very satisfactory.

Anderson and Anderson [132] within the framework of a simple Born model also calculated dB/dp for  $\text{SiO}_2$  and  $\text{TiO}_2$  by adjusting the potential parameters until they yield the correct value of bulk modulus. Shanker and Jain [144] pointed out that these results clearly demonstrated the fact that even the fitting of the bulk modulus did not improved the agreement between theory and experiment. Contrary to this agreement our simple approach showed that not only lattice energy values but also dB/dp values yield much agreement with experiments than those due to either Shanker and Jain [128] or Anderson and Anderson [132].

Anderson and Anderson [132] suggested that the

directional and bond-bending forces are most likely present in these crystals. Striefler and Barsch [141] used the rigid ion model of Katiyar [84] where central force short-range interaction between first and second nearest neighbours is included and an effective charge takes into account deviations from ionic binding. The six free parameters were determined from a least-square fit of the Raman and inactive frequencies and of the elastic constants to the available experimental data. They concluded that the application of the model to the rutile-type oxides turned out to be much less satisfactory than for fluorides [141]. They then added harmonic angle bending forces for the five O pairs showing a common nearest neighbour cation and a least squares technique fitted the nine free parameters. Their results for  $dB/dp$  are much better than all previous calculations, but as pointed out by Shanker and Jain [144] this improvement of  $dB/dp$  has been achieved at cost of reducing the ionic charges which are about one third of the nominal values, such small ionic charges would reduce the Madelung energy and hence the lattice energy significantly with respect to the experimental energy.

With the same polarizability values the potential

with the B-M repulsion reduces the lattice energies to within 8.59% of the experimental values, where as this is not so for  $dB/dp$ . In the case of B-M repulsion, the pressure derivative of bulk modulus  $dB/dp$  shows a derivative from average experimental values amounting to 59%. But the use of the modified Islam potential the lattice energy agrees within 8.7% compared to the experimental values and the  $dB/dp$  is on the average 56% smaller compared to the experimental value. Although with B-L form, the lattice energy,  $dB/dp$  show a deviation from experimental value by 14.86% and 44.55% respectively. Hence it may be remarked that the present approach with the new modified Islam potential seems to be able to describe reasonably both the lattice energy and  $dB/dp$  values simultaneously. The improvement results mainly from the inclusion of vdW energy calculated with a estimated consistent set of polarizability values obtained in the study and the new modified Islam potential. The resulting values seems to imply that the binding in rutile, while somewhat more ionic than some of the previous studies would indicate, (e.g. Baur, [130] and Kingsbury) [142] whose calculation suggested an appreciable covalent character in the M-O bond because the calculated lattice energies have been found to 25% larger or more positive than the thermodynamic values)

does contain a covalent contribution.

It is worth mentioning here that theoretical models based on rigid ion and shell models, with either axially symmetric or tensor the first and second neighbour forces have been ~~fitted~~ fitted to the measured dispersion relation available fully for  $\text{TiO}_2$  only [150]. It was also shown that both the second neighbour rigid-ion and shell models, when used with central forces are unable to predict the qualitative features and only the shell model with tensor forces for all interaction except the second neighbour O-O interaction was able to give acceptable qualitative agreement with data and that agreement is good for only some models. From this discussion it is apparent that a comprehensive theory which can correlate all physical properties of rutile-type compounds, is still not available. In view of this we conclude that a relatively simple treatment with a newly derived polarizability set is moderately successful in explaining at least some of the properties of the compounds under study.



```

C      CALCULATION OF LATTICE ENERGIES AND PRESSURE DERIVATIVE OF SOL
C      MODULI.
C      PROGRAM      CLLE
C      IMPLICIT     REAL (A-Z)
C      INTEGER      MAXROW, MAXCOL, IROW, JCOL
C      CHARACTER     NULL
C      CHARACTER     COMP*4
C      PARAMETER     (MAXROW=00004, MAXCOL=00024, NN=7.0)

```

```

*      DIMENSION DI1 (MAXROW, MAXCOL)
C      DIMENSION DI2 (MAXROW, MAXCOL)
C      DIMENSION DI1(8, 15), DI2(8, 23)

```

```

*      OPEN(UNIT=22, STATUS="OLD", FILE="CLLE.DAT")
C      OPEN(UNIT=11, STATUS="NEW", FILE="CLLE.OUT")
C      OPEN(UNIT=33, STATUS="NEW", FILE="CLLE.TXT")
C      --Calculation of van der Waals co-efficients (D.D)--
C      READ (22, 998) NULL
C      READ (22, 998) NULL

```

```

*      DO 10000 IROW=1, 4
C      READ (22, 100) COMP, AP, AN, NP, SPN, SPP, SNN, TPP, TNN, TPN, R, VM, BT, K,
C      IF (AP .EQ. 100.0) GOTO 111
C      I=I+1

```

```

C      -----
C      A1=AP*AP*.5
C      A2=(AP/NP)**.5
C      A3=A1/A2
C      CPP=A3*25.20
C      WRITE(11, *) CPP
C      -----

```

```

C      B1=AN*AN*.5
C      B2=(AN/NN)**.5
C      B3=B1/B2
C      CNN=B3*25.20
C      WRITE(11, *) CNN
C      -----

```

```

C      C1=AP*AN
C      C2=(AP/NP)**.5+(AN/NN)**.5
C      C3=C1/C2
C      CPN=C3*25.20
C      WRITE(11, *) "CPN =", CPN, "CNN =", CNN, "CPP =", CPP
C      -----

```

```

C      CV=CPN*SPN+CPP*SPP+CNN*SNN
C      WRITE(11, *) "CV = ", CV
C      calculation of van der Waals co_efficients(D.Q)
C

```

```

C      FR=6.666
C      D1=AP*AN
C      D21=(AP/NP)**.5
C      D22=(AN/NN)**.5
C      D2=(D21+D22)**2
C      D31=(AP/NP)
C      D32=SQRT((AP*AN)/(NP*NN))*6.66
C      D33=(AN/NN)
C      D3=D31+D32+D33
C      D4=D1*D2/D3
C      DPN=D4*41.34
C      WRITE(11, *) "DPN = ", DPN
C      -----

```

```

C      E1=AP*AP
C      E2=(2*(AP/NP)**.5)**2
C      E3=2*(AP/NP)+FR*(AP/NP)
C      E4=E1*E2/E3
C      DPP=E4*41.34
C      WRITE(11, *) DPP

```

```

F1=AN*AN
F2=(2*(AN/NN)**.5)**2
F3=2*(AN/NN)+FR*(AN/NN)
F4=F1*F2/F3
DNN=F4*41.34
WRITE(11,*)DNN
DV =DPN*TPN+DPP*TPP+DNN*TNN
WRITE(11,*)"DV= ",DV,"DPN= ",DPN,"DPP= ",DPP,"DNN= ",DNN
T =14.40
calculation of van der Waals energies
UDD=(-CV/(R**6))*T
UDD0=(-DV/(R**3))*T
UVT=UDD+UDD0
WRITE(11,*)"UVT=",UVT
WRITE(11,*)"UDD=",UDD
WRITE(11,*)"UDD0=",UDD0
Calculation of Repulsive Energies.
TP=300.0
-----BL-----
A=(440.18/R)+(C*CV/R**6)+(8*DV/R**8)
B=-(880.36/R)-(42.*CV/R**6)-(72*DV/R**8)
M=1.36-A
M=(3*TP*VM*BT)/K
WRITE(11,*)M
X=(90*VM/K)-B
N=-(X/M)-1
A1=-(M/N)*(R**N)
URBL=A1*(R**N)*T
WRITE(11,*)"M =",M,"X =",X,"N =",N,"A =",A,"UDD =",UDD,
-----BM-----
ROW=-(M/X)*R
BBM=-(M/R)*ROW*EXP(R/ROW)
URBM=BBM*EXP(-R/ROW)*T
WRITE(11,*)"ROW =",ROW,"BBM =",BBM,"URBM =",URBM
-----VERWEY-----
G1=12
MUE=-(M/G1)*(R**G1)
URV=MUE*(R**G1)*T
WRITE(11,*)"MUE =",MUE,"URV =",URV
-----VS-----
K2=-(X/M-1)
K3=2*(R**2)
K1=K2/K3
LAMDA1=M/(2*(R**2)*K1)
LAMDA2=EXP(K1*(R**2))
LAMDA=-LAMDA1*LAMDA2
URVS1=LAMDA*T
URVS2=EXP(-K1*(R**2))
URVS=URVS1*URVS2
WRITE(11,*)"LAMDA =",LAMDA,"URVS =",URVS,"K1 =",K1
-----GT-----
CONA=-X/(2*M)
EP=SQRT(-7+4*CONA+4*(CONA**2))
PK1=-1+2*CONA+EP
PK2=4*(R**2)
PK=PK1/PK2
P0=EXP(PK*(R**2))
P1=M*R*P0
P2=2*PK*(R**2)+1
P=-(P1/P2)
URGT1=P/R
URGT2=EXP(-PK*(R**2))
URGT=URGT1*URGT2*T
WRITE(11,*)"P =",P,"PK =",PK,"URGT =",URGT
-----ISLAM-----

```

```

MC=1-(1/SIG)-(X/(M*SIG))
I=-M/(MC*SIG)*EXP(MC)
URI=I*EXP(-MC)*T
C WRITE(11,*)"MC =",MC,"I =",I,"URI =",URI
C -----AK-----
Z1=-X/M
MC11=((SIG*SIG)-(7*SIG)+(Z1*SIG))
MC12=SQRT((MC11**2)-(12*(SIG**2)*(4-Z1)))
MC13=2*(SIG*SIG)
MC1=(MC11+MC12)/MC13
GA=M/(3+MC1*SIG)
GB=(R**3)*EXP(MC1)
G=-GA*GB
C URAK1=EXP(-G2*(R**SIG))
C URAK=(G/(R**3))*EXP(-MC1)*T
C WRITE(11,*)"URAK =",URAK,"MC1 =",MC1,"G =",G
C
C Calculation of lattice Energy:-
C
UE=(-440.18/R)*T
UBL=UE+UVT+URBL
UBM=UE+UVT+URBM
UV=UE+UVT+URV
UVS=UE+UVT+URVS
UGT=UE+UVT+URGT
UI=UE+UVT+URI
UAK=UE+UVT+URAK
C WRITE(11,*)"UE = ",UE
C WRITE(11,*)"UBL= ",UBL
C WRITE(11,*)"UBM= ",UBM
C WRITE(11,*)"UV = ",UV
C WRITE(11,*)"UVS= ",UVS
C WRITE(11,*)"UGT= ",UGT
C WRITE(11,*)"UI = ",UI
C WRITE(11,*)"UAK= ",UAK
C
C Calculation of pressure derivative of bulk moduli:-
C
C -----BL-----
U21=-(880.36/(R**3))-(42*CV/(R**8))-(72*DV/(R**10))
U22=N*(N+1)*A1*(R**-(N+2))
U2=U21+U22
U31=(2641.08/(R**4))+(336*CV/(R**9))+(720*DV/(R**11))
U32=-N*(N+1)*(N+2)*A1*(R**-(N+3))
U3=U31+U32
BL=1-(R*U3)/(3*U2)
C -----BM-----
U42=(BBM/(ROW**2))*EXP(-R/ROW)
U4=U42+U21
U52=-(BBM/(ROW**3))*EXP(-R/ROW)
U5=U52+U31
BM=1-(R*U5)/(3*U4)
C -----VERWEY-----
U62=156*MUE*(R**14)
U6=U62+U21
U72=-2184*MUE*(R**15)
U7=U72+U31
BV=1-(R*U7)/(3*U6)
C -----VS-----
U82=2*LAMDA*K1*EXP(-K1*(R**2))
L1=4*LAMDA*K1*K1*R*EXP(-K1*(R**2))
L2=L1*R
U8=U21+U82+L2
U92=(3*L1)-(2*L2*K1*R)
U9=U31+U92
BVS=1-((R*U9)/(3*U8))

```

```

PHY=(P/R)*EXP(-PK*(R**2))
PH2=PHY/(R**2)
PH1=PHY/(R**3)
U10=U21+2*(1+PK*(R**2)+4*(PK**2)*(R**4))*PH2
U11=U31-(2*(3+(3*PK*(R*R))+(4*(PK**3)*(R**6)))*PH1)
BGT=1-(R*U11)/(3*U10)
WRITE(11,*)" BL=",BL," BM=",BM," BV=",BV," BVS=",BVS," BGT=",BGT
----- ISLAM-----

```

```

PHI=I*EXP(-MC)
PHI1=-SIG*(MC/R)*PHI
PHI21=-SIG*(MC/R)*PHI1
PHI22=-SIG*(SIG-1)*(MC/(R**2))*PHI1
PHI2=PHI21+PHI22
PHI31=-SIG*(MC/R)*PHI2
PHI32=-2*SIG*(SIG-1)*(MC/(R**2))*PHI1
PHI33=-SIG*(SIG-1)*(SIG-2)*(MC/(R**3))*PHI1
PHI3=PHI31+PHI32+PHI33
U12=U21+PHI2
U13=U31+PHI3
BI=1-((R*U13)/(3*U12))
WRITE(11,*)U12,U13,BI
----- AK-----

```

```

PHIA=(O/(R**3))*EXP(-MC1)
PHIA11=-3*PHIA/R
PHIA12=-(SIG*MC1*PHIA)/R
PHIA1=PHIA11+PHIA12
PHIA21=(12+(3*SIG*MC1))-(SIG*(SIG-4)*MC1)+((SIG**2)*(MC1**2))
PHIAK=PHIA/(R**2)
PHIA2=PHIA21*PHIAK
PHIA31=-(60+(12*SIG*MC1))
PHIA32=(3*SIG*(SIG-5)*MC1)-(3*(SIG**2)*(MC1**2))
PHIA33=-(SIG*(SIG-4)*(SIG-5)*MC1)-((SIG**2)*(SIG-4)*(MC1**2))
PHIA34=((SIG**2)*(2*SIG-5)*(MC1**2))-((SIG**3)*(MC1**3))
PHIA3=(PHIA31+PHIA32+PHIA33+PHIA34)*PHIA/(R**3)
U14=U21+PHIA2
U15=U31+PHIA3
BAK=1-((R*U15)/(3*U14))
WRITE(11,*)"BAK=",BAK," BI=",BI
-----

```

```

DI1(IROW,01)=AP
DI1(IROW,02)=AN
DI1(IROW,03)=NP
DI1(IROW,04)=SPN
DI1(IROW,05)=SPP
DI1(IROW,06)=SNN
DI1(IROW,07)=TPP
DI1(IROW,08)=TNN
DI1(IROW,09)=TPN
DI1(IROW,10)=R
DI1(IROW,11)=VM
DI1(IROW,12)=BT
DI1(IROW,13)=K
DI1(IROW,14)=SIG
-----

```

```

DI2(IROW,01)=UVT
DI2(IROW,02)=URDL
DI2(IROW,03)=URBM
DI2(IROW,04)=URV
DI2(IROW,05)=URVS
DI2(IROW,06)=URGT
DI2(IROW,07)=URI
DI2(IROW,08)=URAK
DI2(IROW,09)=UBL
DI2(IROW,10)=UBM
DI2(IROW,11)=UV

```

```

DI2(IROW,12)=LVS
DI2(IROW,13)=UCT
DI2(IROW,14)=JI
DI2(IROW,15)=LAK
DI2(IROW,16)=BL
DI2(IROW,17)=BK
DI2(IROW,18)=BV
DI2(IROW,19)=EVS
DI2(IROW,20)=ECT
DI2(IROW,21)=BI
DI2(IROW,22)=BAK
10000 CONTINUE
C
DO 1002 IROW=1,4
  WRITE(33,200) COMP, (DI2(IROW,JCOL), JCOL=1,22)
1002 CONTINUE
C
00100 FORMAT((A),14F7.0)
00200 FORMAT((A),4X,11F11.3/8X,11F11.3/)
00998 FORMAT (A)
STOP
END

```

## References:

1. M.Born and A. Lande, Verhandl. Dent. Phys. Ges 20, 210(1918).
2. M.Born and J.E.Mayer, Z.Physik 75, 1(1932).
3. E.S.Rittner, J.Chem.Phys.27,573(1951); 19,1030(1951).
4. Y.P.Varshni and R.C.Shukla, J.Mol.Spec-trose.16,63(1965).
5. M.N.Patel, V.B.Gohel and M.D. Trivedi, Indian J.Phys.41,235(1967)
6. J.Sherman, Chem.Rev.11,93(1932).
7. T.C.Waddington, Adv.Inor. Chem.1,(1959).
8. M.F.C.Ladd, and W.H.Lee, Progress in Sol-St.Chem.1,37(1937).
9. C.M.Kachhava and S.C.Saxena, Philos. Mag.8,1429(1963).
- 10 V.K.Mathur and S.P.Singh,Philos.Mag.16.1299(1967).
11. J.D.Pandey,J.Phys.Soe.Jpn. 26,579(1969).
12. J.D.Pandey and O.C.Saxena,J.Chem.Soc. 4,397(1969).
13. L.W.Barr and A.B.Lidiard, In. Phys. Chem. 10,152(1970).
14. R.L.Redington, J.Phys.Chem.74,181(1970).
15. CH. Satyanarayana, Acta ciencia India.
16. W.E.Bleick,J.Chem. Phys.2,160(1964).
17. C.S.N. Murthy and Y.V.G.S. Murthy, J.Phys. C3,L22(1970).

18. R.K.Singh and J.P.S.Rana, Nuovo. Cimento 57B, 177(1980).
19. M.F.C.Ladd and W.H.Lee, J.Inorg. Nucl. Chem. 13,218(1970).
20. D.Cubicciotti, J. Chem.Phys. 31, 1646(1959).
21. M.N.Sharma and M.P.Madam, Indian J.Phys. 38,231(1964).
22. C.M. Kachhava and S.C.Saxena, Indian J.Phys, 38,388(1964).
23. K.D.Mishra and M.N. Sharma, Indian J. Pure Appl. Phys. 10,412(1972)
24. M.N. Sharma and S.R.Tripathi, J. Phys. Chem. solids 36,45(1982).
25. J.Shanker and G.D.Jain, Phys.Stat-Sol.(b)110,257(1982).
26. W.A.Harrison, Phys. Rev. B23, 5230(1981).
27. Y.P.Varshni and R.C.Shukla, J. Chem. Phys.35,582(1961).
28. L.V.Woodcock, J.Chem.Soc.Faraday Trans.II70, 1405(1974).
29. J.Michielsen, P.Wocklee, F.V.D. Graaff, and J.A.A.-Ketelaar, J.Chem.Sosc.Faraday trans. II71, 1730(1975).
30. J.Shanker, J.P.Singh and V.C. Jain, Physica 106B, 247-250(1981)
31. H.Hellmann, Acta. Phys. USSR.1,913(1934)

32. H.Hellmann and W.Kassatotschkin, Acta. Phys USSR.5,23(1936); J.Chem.Phys.4,324(1936)
33. J.A.Wasastjerna,Soc.Sci. Fennica, Comment. Phys. Math.8,20 and 21(1935).
34. J.A.Wasastjerna, Philos.Trans.Roy.Soc.A (Lond.)237,105(1938).
35. L.Das and S.C.Saxsena, J.Chem.Phys.43,1747(1965).
36. M.E.Striefler and G.R.Barsch, Phys.Stat.Sol.(b) 59,205(1973)
37. F.A.Grant, Rev.Mod.Phys.31,646(1959).
38. D.B.Rogers,R.D.Sharma,A.W.Sleight and J.L.Gill, Inorg.Chem. 8,841(1969).
39. M.N.Sharma, A.Kant and K.D.Misra, Phys. Stat.Sol. (b)79,359(1977)
40. J. E. Mayer and L. Helmholtz, Z. Physik 75,19(1932).
41. J. E. Mayer, J. Chem.Phys. 1,270(1933).
42. S. Noor Mohammad, International J. Quantum. Chem. XV, 769-782(1979)
43. M. P. Tosi, Solid state Phys. 16,1(1964).
44. G. D. Jain and J. Shanker, Phys. Stat. Sol (b) 119,79(1983).
45. V. B. Gohel and M. D. Trivedi, Indian. J. Pure Aappl. Phys.6, 173(1968).
46. R. Narayan and S. Ramaseshan, J. Phys, Chem, Solids 37,395(1976).



47. E. Madelung, Physik. Z. 19, 524(1918).
48. P. P. Ewald, Ann. Physik 64, 253(1921).
49. H. M. Evjen, Phys. Rev. 39,675(1932); F. C. Frank, Phil. mag.41,1287(1950).
50. W. Heitler and F. London, Physic 44,455(1927).
51. L. Pauling, Z. Krist. 67,377(1928).
52. J. C. Slater, Introd. Chem. Phys. 366-367(1939).
53. A. Einstein, Ann. Physi 22, 180, 800(1906); 34,170(1911).
54. A. Krebs, Z. Physik 80, 134(1933).
55. A. Krebs, Z. Physik 81, 1(1933).
56. O. K. Rice, Electronic structure and chemical binding (Mc-Graw-Hill Book company, inc; New York, 1940), p-249.
57. R. S. Mulliken, Phys. Rev. 50,1017,1028(1936).
58. E. R. Dobbs and G.O. Jones, Rep. Prog. Phys, 20,516(1957).
59. P. Gombas, Die Statistische Theorie des Atoms and ihre Anwendungen (Springer) Verlag Berlin, (1949), 304-306.
60. E. Alntoncik, Czechosl, 5 phys, 4, 439(1954), 7,118(1957).
61. H. Preuss, Z. Naturforsch. 10a, 365(1955).
62. L. Szasz, Acta Phys. Acad. Sci. Hung. 6, 307(1957).
63. J. Callaway, Phys. Rev. 12, 322(1958).

64. M. L. Huggins and J. E. Mayer, J. Chem. 1, 643(1933); M. L. Huggin, Chem. Phys. 5, 143(1937); 15, 212(1947), J, Am. Chem. Soc. 75, 412c (1953).
65. E. J. W. Verwey, Recl. Trav. Chim. Pays-Bas Belg. 65, 527(1946).
66. R. Guecione, M. P. Tosi and M. Asdente, J. Phys. Chem. Solids, 10, 162(1959).
67. K. Tharmalinghm, J. Phys. Chem. Solids 24, 1380(1963); Ibid., 255(1664).
68. I. M. Boswarva and A. B. Lidiard, Phil. Mag. 16, 805(1967).
69. B. G. Dickand A. Overhauser, Phys. Rev. 112, 90(1958).
70. P. O. Lowdin, Adv. Phys. 5, 1(1956).
71. D. W. Hefemeister and J. D. Zahrt, J. Chem. Phys. 47, 1428(1967).
72. Y. P. Varshni and R. C. Shukla, I. Chem. Phys. 35, 582(1961)
73. G. C. Benson and E. Dempsy. Proc. Roy. Soc. A 266(1962).
74. L. Pauling, The nature of Chemical bond (Cornell Univ.Press, Ithaca, 1960).
75. O. Ra, J. Chem. Phys.52, 3765(1970).
76. D. M. Hafemeister and W. H. Flygare, J. Chem. Phys. 43, 795(1965).

77. R.K. Singh and P. Khave, Phys. Stat, Sol. (b) 23, 29(1984).
78. M. N. Sharma, A. K. Gantam and S. R. Tripattei, J. Phys Soc. Japan, 40, 651(1976).
79. R. K. Singh and S. P. Sanyal, Phys, Stat. Sol(b) 99, 771(1980).
80. A. Singh and M. N. Sharma, J. Chem. Phys, 43, 1747(1965).
81. S. Prakash and J. Behsi, Indian J. Pure appl. Phys. 7, 709(1969).
82. K. D. Mishra, K. P. Pandle and M. N. Sharma, J. Phys, Soc. Japan, 31, 977(1971).
83. M. N. Sharma and R. Jain, Phys. Soc. Japan 35, 194(1973).
84. R. S. Katiyar, J. Phys. C3, 1693(1970).
85. R. K. Singh and Shailendra Tiwary, Philosophical Magazine B, 48, 5, 411-419(1980).
86. S. Romano, C. Margheritis and C. Sinistri, Z. Naturforsch. 29a, 1202(1974).
87. M. P. Tosi and F. G. Fumi, J. Phys. Solids. 25, 45(1964).
88. K. P. Thakur, J. Phys. 29, 39-50(1976).
89. A. K. M. A. Islam, Phys. Stat. Sol. (b) 100, k5(1980).

90. R. Narayan and S. Ramaseshan, Phys. Rev. Lett. 42, 992(1979).
91. R. Narayan and S. Ramaseshan, Pramana 13, 581(1979).
92. Ch. Satyanarayana, Acta. Ciencia India; Ch. Satyanarayana and M.S.Madhava, in preceding of the second National conference on Ferroelectric Dielectrics (in Press).
93. R. B. Yadav, Solid St. Communication 46, 341(1983).
94. Y. P. Varshni, Rev. Mod. Phys. 29, 664(1957),
95. Y. P. Varshni and R. C. Shukla, Rev. Mod. Phys. 35, 130(1963).
96. Bohm, Quantum theory, 472-473(1951).
97. D. I. Blokhintsev, Quantum Mechs. 460(1963).
98. Charles Kittel, Solid St. Phys., 100(1971).
99. Kauzmann, Quantum Chemistry, 503(1967).
100. Peierls, Quantum theory of solid, 9(1955).
101. J. Shanker, G. G. Agrawal and R. P. Singh, J. Chem. Phys. 69,(1978).
102. P. Tosi, Solid Stat. Phys. 16, 34(1965).
103. F. London, Z. Phys. Chem., Abt. B11, 222(1930).
104. H. Margenau, Phys. Rev. 38, 747(1931); Rev. Mod. Phys. 11, 1(1939).
105. J. C. Slater and J. G. Kirkwood, Phys. Rev. 37, 682(1931).

106. J. G. Kirkwood, Phys. Z. 33, 57(1932).
107. A. Muller, Proc. Roy. Soc. (London) A154, 624(1936).
108. G. H. Winslow, J. Chem. Phys. 62, 4138(1975).
109. H. R. Hasse, Proc. Cambridge Philos. Soc. 27, 66(1931).
110. K. Spangenberg, Z. Krist., 57, 494(1923).
111. K. Fajans and G. Joos, Z. Physik 23, 1(1924).
112. K. Fajans, "Chemical forces" McGraw-Hill, New York, N. Y., 1931.
113. N. Baur and K. Fajans, J. Amer. Chem. Soc., 64, 3031(1942).
114. K. Fajans, "Encyclopedia of chemistry", Clarrk and Hawley Ed. Reinhold, Pub. Co. New York, N. Y., 764(1957).
115. L. Pauling, Proc. Roy. Soc. 114, 181(1927).
116. J. R. Tessmann, A. H. Kahn and W. Shockley, Phys. Rev. 92, 890(1953).
117. A. R. Ruffa, Phys. Rev., 130, 1412(1963).
118. V. V. Mitskevich, Soviet Phys. Solid State, 6, 557(1964).
119. M. I. Petrashen, L. V. Abarenkov and N. N. Kristofel, Opt Spectrose. 9, 276(1960).
120. M. Ledovskaya, Status Solidi. 31, 507(1969).

121. E. Paschalis, A. Weiss., Theor. Chim. Acta. 13, 381(1969).
122. J. Pirene and E. Karthenser, Physica, 30, 2005(1964); 31, 284(1965).
123. L. Henrich, Phys. Rev. 62, 545(1942).
124. G. Burns and C. G. Wikner, Phys. Rev. 121, 155(1961).
125. J. Yamashita, J. Phys. Soc. Jap. 7, 284(1952).
126. E. Hylleraas, Z. Physic 65, 209(1930); 27, 66(1931).
127. M. F. C. Ladd, J. Chem. Phys. 60, 5(1974).
128. J. Shanker and V. K. Jain, Phys. Stat. Sol. (a) 59, 755(1980).
129. P. H. Wackman, W. H. Hirthe and R. E. Frounfelker, J. Phys. Chem. Solids 28, 1525(1967).
130. W. H. Baur, Acta Cryst. 14, 209(1961).
131. M. F. C. Ladd, Acta Crysta. A25m 486(1968).
132. D. L. Anderson and O. R. Anderson, geo. Phys. Res. 75, 3494(1970).
133. M. E. Striefler and G. R. Barsch, Phys, Stat. Sol.(b) 67, 143(1975).
134. A. R. Ruffa, Phys. Rev. 133, 1418(1964).
135. A. K. M. A. Islam. ICTP inter. Report 1c/85/21.
136. J. C. Slater, Phys. Rev. 36, 57(1930).
137. M. Born and W. Heisenberg, Z. Phys. 23, 388,

(1924).

138. P. C. Schmidt, A. Weiss and T. P. Das, Phys. Rev. B19, 5525(1979).

139. S. D. Bisarya and J. Shanker, Pramana (India) 2.196(1974).

140. R. Narayan, J. Phys. Chem. Solids. 38, 1097(1977).

141. M. E. Striefler and G. R. Barsch, Phys. Stat. Sol. (b 67, 143(1975).

142. P. I. Kingbury, Acta Cryst. A24, 578(1968).

143. R. James and C. R. A. Catlow in Handbook of interatomic potentials by A. M. Stoneham; AERE Report No--~~2522~~<sup>9592</sup>-, p126-128.

144. A. Unsold, Z. Phys. 43, 563(1927).

145. H. Bruck, Z. Phys. 51, 707(1928).

146. J. C. Slater, Phys. Rev. 32, 349(1928).

147. W. E. Bleicke and J. E. Mayer, J. Chem. Phys. 2, 252(1934).

148. M. Kunimune, Prog. Theor. Phys. 5, 12(1950).

149. M. Sakamoto and E. Isiguro, Prog. Theor. Phys. 15, 37(1956).

150. J. G. Traylor, H. G. Smith, R. M. Nicklow and M. K. Wlikinson. J. Phys. c4, 2421(1971).